

Evaluation of Dipsol IZ-C17 LHE Zinc-Nickel Plating

By:

Stephen Gaydos
Boeing – St. Louis

for

HCAT/JCAT Meeting
January 24, 2007




Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 24 JAN 2007		2. REPORT TYPE		3. DATES COVERED 00-00-2007 to 00-00-2007	
4. TITLE AND SUBTITLE Evaluation of Dipsol IZ-C17 LHE Zinc-Nickel Plating				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Boeing P. O. Box 516, St. Louis, MO, 63166				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES 27th Replacement of Hard Chrome and Cadmium Plating Program Review Meeting, January 23-25, 2007, New Orleans, LA. Sponsored by SERDP/ESTCP.					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 27	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

Intro

- Key Attributes for Cadmium Plating Alternatives:
 - Drop-In Replacement
 - Sacrificial to Steel When It Corrodes
 - Corrodes Slowly (Long Life in Salt Water)
 - Non-Embrittling to High Strength Steel
 - Plating Process
 - Maintenance Fluids
- So Why Zinc-Nickel Plating?

Cadmium Alternatives are Limited!

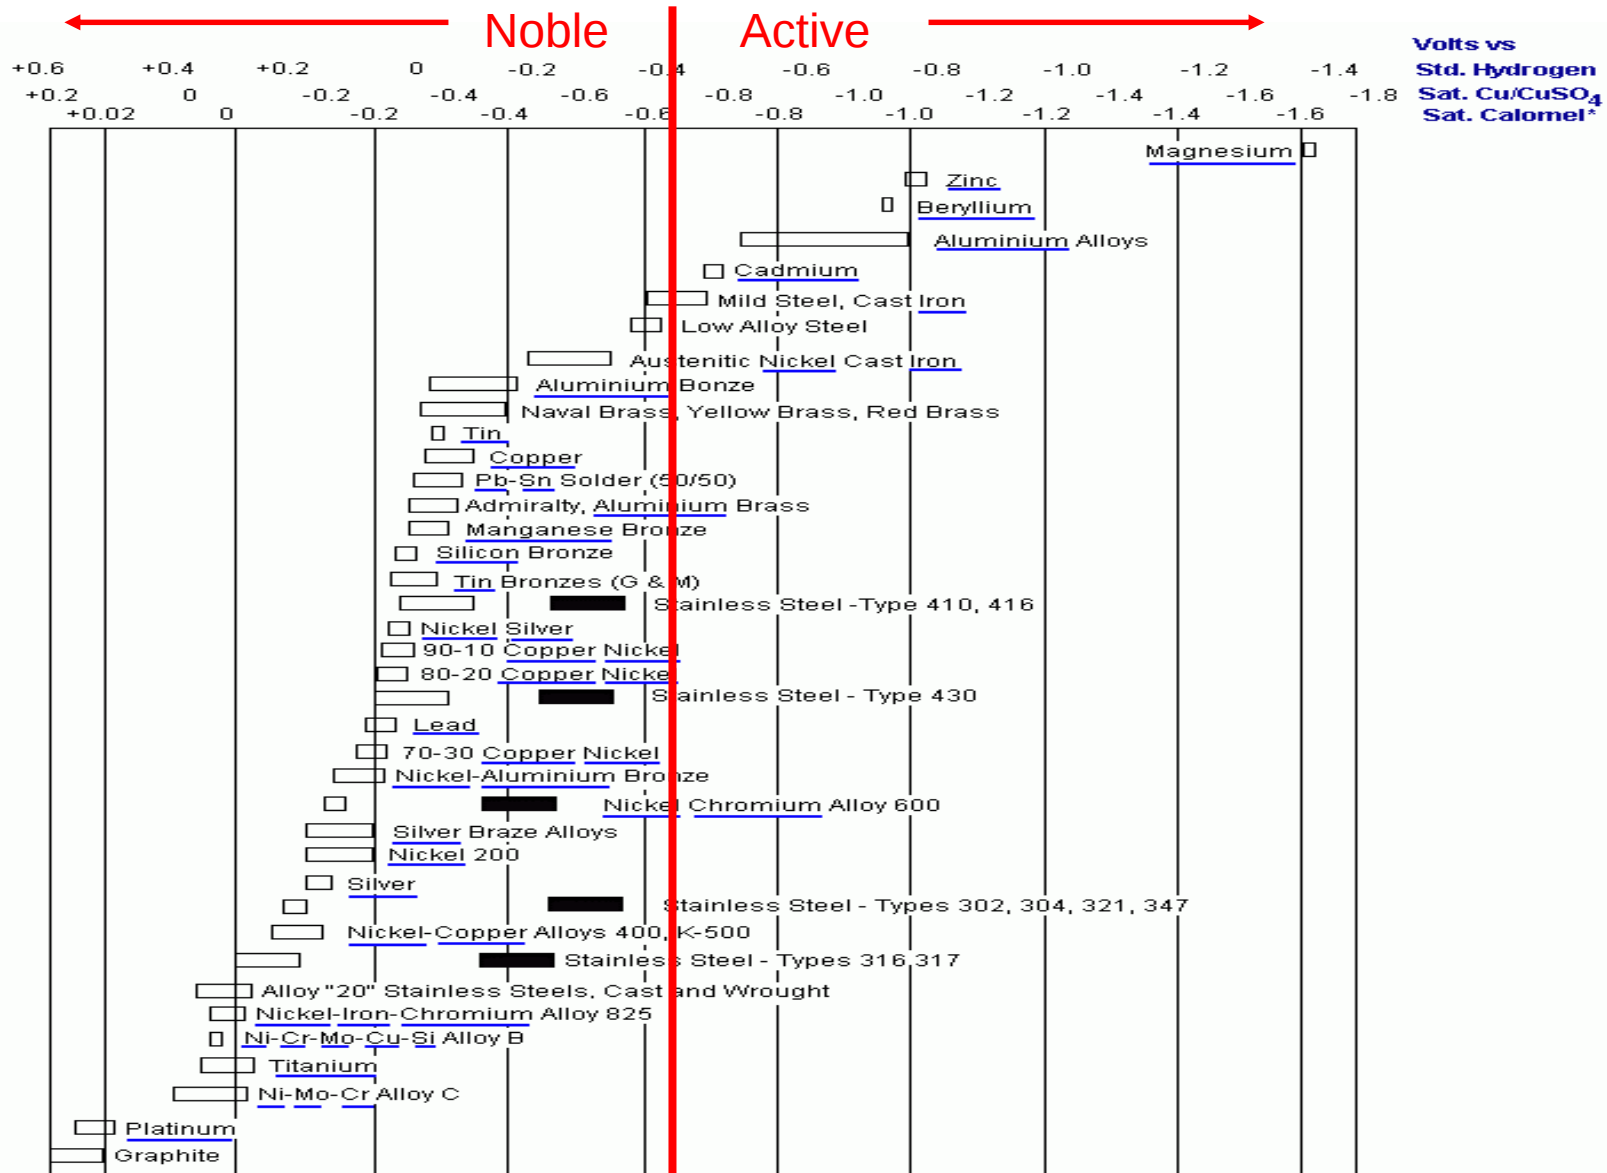

Proposed Cadmium Alternatives

- Cadmium Alternative Coatings for Steel
 - Aluminum (IVD-Sputter Aluminum, Alumiplate)
 - Beryllium (Too Toxic)
 - Zinc (Too Active – Corrodes Too Fast)
 - Magnesium (Extremely Active – Corrodes Rapidly)
- Zinc Alloys Can Reduce Activity of Zinc
 - Zinc-Nickel Preferred (Zn-Fe, Zn-Mn, Zn-Co, Zn-Sn, Sn-Zn Not Acceptable)
 - Zinc-Nickel is Sacrificial to Steel if Ni < ~18%
 - Nickel Alloyed to Zinc Has Low Corrosion Rate in Salt Water
 - No Excessive White Corrosion Products

Zinc-Nickel Alloys

- What is Best Ni Composition in Zinc-Nickel Plating?
 - 4 to 18% Appears to Give Good Corrosion Resistance and Sacrificial Protection to Steel
 - High % Ni Appears to Create a Non-Embrittling Plating Process
- What is Best pH for Zinc-Nickel Plating?
 - Alkaline Plating Appears to Be Easier to Use
 - Bath Easier to Maintain
 - Throwing Power Good and No Variance in % Ni

Zn-Ni Versions for Aerospace and Automotive Industry

- Aerospace Needs a Different Version of Automotive Zn-Ni Plating
 - High Strength Steel Used In Aerospace
 - Hydrogen Embrittlement
 - Fatigue Life
 - Corrosion Performance
 - Aerospace Parts Required to Have a Longer Service Life and Higher Reliability Than Automotive

Pre 2003 Zinc-Nickel Plating

- Pre 2003 There Were Two Zinc-Nickel Processes Being Considered at Boeing
 - Boeing Acid Zn-Ni Plating (with BoeNiz)
 - Passes ASTM F 519 Embrittlement Tests - BUT
 - Plating Process is Not Operator Friendly
 - ASTM F 346 Electronic Hydrogen Measurement (or Similar Method) Cannot Be Used
 - Dipsol IZ-260 Alkaline Zinc-Nickel Plating
 - Occasionally Fails ASTM F 519 Embrittlement Test
 - Plating Process is Operator Friendly - BUT
 - Needed a Nickel Strike to Pass ASTM F 519 on a Consistent Basis

LHE Alkaline Zn-Ni Plating

- C-17 Pollution Prevention Project - 2003 to 2005
 - Develop an LHE (Low Hydrogen Embrittlement) Version of Alkaline Zn-Ni Plating
 - Look at Different Zn-Ni Formulas with Nickel Composition of 5 to 17%
 - Remove Brighteners and Other Additives to Make Plating Dull (Porous)
 - Vary the Current Density

LHE Alkaline Zn-Ni Plating

- Boeing Teamed with Dipsol of America to Develop an LHE Alkaline Zn-Ni Plating
 - Dipsol Produces IZ-260 Alkaline Zn-Ni Plating
 - Used by Several DoD and Aerospace Subcontractors
 - IZ-260 Has 5 to 8% Nickel – Balance Zinc
 - Dedicated R&D Laboratory in Tokyo, Japan
 - Excellent Technical Support at Laboratory in Livonia, MI
 - Dipsol Understands Zn-Ni Plating Chemistry

2003-05 Test Results

- Based on Successful Test Results an LHE Alkaline Zn-Ni Formula was Selected for Further Development
 - Identified as Dipsol IZ-C17 (13 to 17% Ni)
- IZ-C17 Had Good Corrosion Performance
- IZ-C17 Passed Hydrogen Embrittlement and Re-Embrittlement Testing with 1a.1 and 2a
 - Re-Embrittlement Test Specimens Exposed to Distilled Water and 3.5% Salt Water

Zinc-Nickel Corrosion Test



IZ-C17 LHE Zn-Ni



Cadmium

ASTM B 117 – 816 Hours Exposure

IZ-C17 – HE Test Results

Test Description	Specimen Type	ID No.	200 Hour Result (Pass/Fail)	ISL After 200 Hour Test (% NFS)
Set #1 - Plate Entire Specimen	1a.1	AQ3789	Pass	80
Set #1 - Plate Entire Specimen	1a.1	AQ5767	Pass	85
Set #1 - Plate Entire Specimen	1a.1	AQ3623	Pass	90
Set #1 - Plate Entire Specimen	1a.1	AQ3675	Pass	80
Set #2 - Plate at 3 Times Current Density	1a.1	AS1279	Pass	80
Set #2 - Plate at 3 Times Current Density	1a.1	AS1487	Pass	90
Set #2 - Plate at 3 Times Current Density	1a.1	AS1026	Pass	85
Set #2 - Plate at 3 Times Current Density	1a.1	AS1248	Pass	85
Set #3 - Plate with No Preplate Acid Activation	1a.1	AS1385	Pass	95
Set #3 - Plate with No Preplate Acid Activation	1a.1	AS1085	Pass	90
Set #3 - Plate with No Preplate Acid Activation	1a.1	AS1040	Pass	90
Set #3 - Plate with No Preplate Acid Activation	1a.1	AS1281	Pass	95
Set #4 - Plate with Preplate Acid Activation	1a.1	AS1264	Pass	90
Set #4 - Plate with Preplate Acid Activation	1a.1	AS1198	Pass	90
Set #4 - Plate with Preplate Acid Activation	1a.1	AS1421	Pass	90
Set #4 - Plate with Preplate Acid Activation	1a.1	AS1148	Pass	85
Set #5 - Plate with Preplate Acid Activation	2a	44911-12	Pass	-
Set #5 - Plate with Preplate Acid Activation	2a	44911-47	Pass	-
Set #5 - Plate with Preplate Acid Activation	2a	44911-54	Pass	-
Set #5 - Plate with Preplate Acid Activation	2a	44911-1	Pass	-

Hydrogen Embrittlement Results for IZ-C17



IZ-C17 – Re-Embrittlement Tests

Re-Embrittlement Test Fluid	Specimen Type	ID No.	150 Hour Result (Pass/Fail)
Distilled Water	1a.1	AS1224	Pass
Distilled Water	1a.1	AS1166	Pass
Distilled Water	1a.1	AS1368	Pass
Distilled Water	1a.1	AS1169	Pass
3.5% Salt (NaCl) Water	1a.1	AS1001	Pass
3.5% Salt (NaCl) Water	1a.1	AS1415	Pass
3.5% Salt (NaCl) Water	1a.1	AS1328	Pass
3.5% Salt (NaCl) Water	1a.1	AS1286	Pass
Distilled Water	2a	44911-42	Pass
Distilled Water	2a	44911-134	Pass
Distilled Water	2a	44911-41	Pass
Distilled Water	2a	44911-76	Pass
3.5% Salt (NaCl) Water	2a	44911-42	Pass*
3.5% Salt (NaCl) Water	2a	44911-134	Pass*
3.5% Salt (NaCl) Water	2a	44911-41	Pass*
3.5% Salt (NaCl) Water	2a	44911-76	Pass*


* 2a Test Specimens that passed the 150 hour distilled water test were used for the salt water test.

Hydrogen Re-Embrittlement Results for IZ-C17



IZ-C17 Thickness and Adhesion

- IZ-C17 Has Good Adhesion
 - Passes Bend-To-Break Tests
- Thickness Control is Very Good

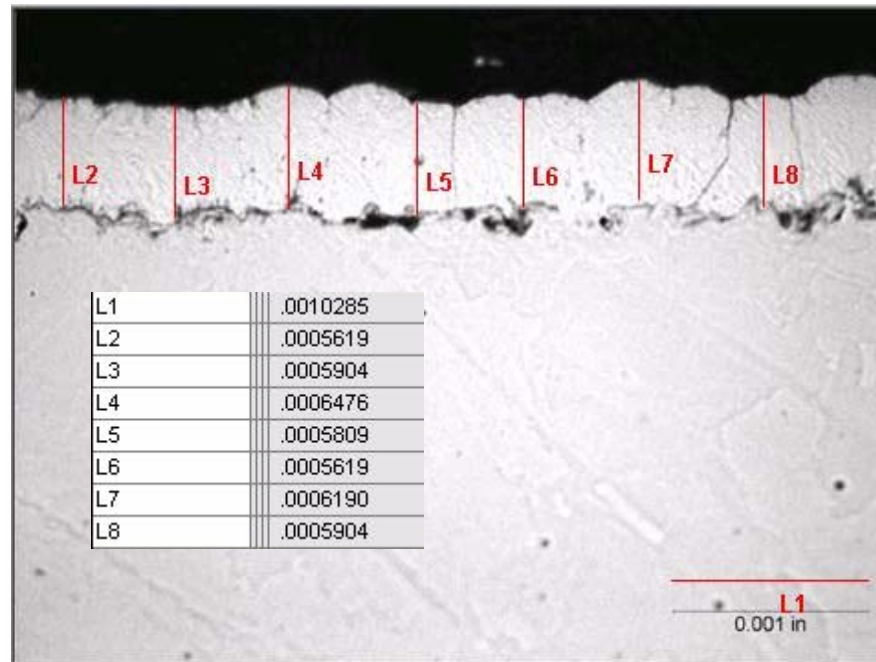

2006 – 2007 Test Objectives

- Install Plating Tank at Boeing – St. Louis with Dipsol IZ-C17
 - Perform More Hydrogen Embrittlement Tests
 - Perform Fatigue Tests
 - Perform Lubricity Tests
 - Optimize Operating Parameters
 - Verify Operating Limits of Plating Bath
 - Plate Parts with Complex Geometries
 - Determine Need for Auxiliary Anodes and Special Tooling
 - Plate ID of Tubular Parts
- Qualify IZ-C17 for C-17 Program
 - Create Draft DPS for IZ-C17
 - Identify Process Controls
 - Hydrogen Embrittlement Test Methods
 - Select Repair Procedures

2006 Status

- IZ-C17 Tech Bulletin (Draft) Prepared
 - Information Provided by Dipsol and Boeing
- Purchased and Installed Plating Tank and Support Equipment
 - IZ-C17 Chemical Received From Dipsol of America – Livonia, MI
 - Original Zn-Ni Chemicals Came From Dipsol – Japan
- Bare Test Specimens Prepared

IZ-C17 Tech Bulletin



DIPSOL OF AMERICA, INC.

34005 Schoolcraft Road, Livonia, MI 48150
TEL (734) 261-0633, TOLL FREE: 1-866-DIPSOL-1
FAX (734) 261-0655, E-mail: main@dipsolamerica.com
www.dipsolamerica.com

TECHNICAL BULLETIN

ZINC AND ZINC ALLOY PLATING PROCESSES

LHE Zinc Nickel system

DIPSOL IZ-C17

Low Hydrogen Embrittlement Alkaline Zinc Nickel Alloy Plating



IZ-C17 Zn-Ni Plating Process

1. TCE Vapor Degrease or Solvent Clean with MPK
2. Grit Blast with aluminum oxide (120 grit or finer) at ~ 60 psig
3. Rinse in water to remove loose grit
4. Apply LHE zinc-nickel plate: IZ-C17 – 3 A/dm^2 – RT – 30 to 45 minutes (produces 0.3 to 0.6 mils)
5. Rinse
6. Embrittlement Relief Bake at $375 \pm 25^\circ\text{F}$ for 24 hours. Bake within 4 hours after plating
7. Rinse
8. Chromate Conversion Coating: Apply IZ-258 @ 140°F , 60 seconds
9. Rinse
10. Dry @ $< 140^\circ\text{F}$ – 10 minutes


IZ-C17 Plating Tank

- 60 L Plating Tank Installed in Laboratory



Conversion Coat Tank

- Installed IZ-258 Chromate Conversion Coating Tank

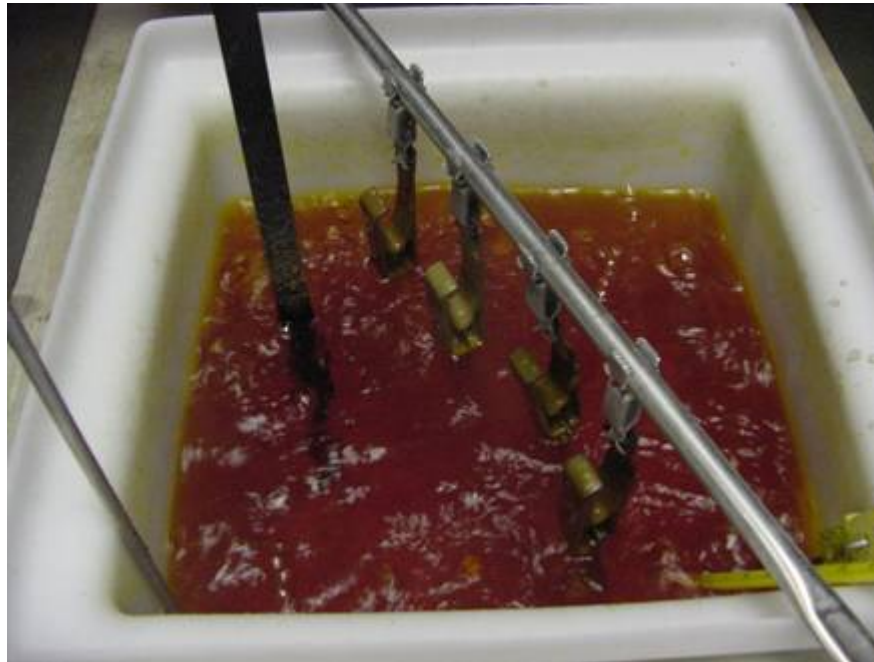

IZ-258

2006 Status (Cont.)

- IZ-C17 Test Plan Prepared
 - Hydrogen Embrittlement (1a.1, 1a.2, 2a)
 - Adhesion and Metallurgy
 - Corrosion Testing (Salt Spray and Galvanic)
 - Fluid Immersion (ASTM F 483)
 - Lubricity (Fasteners)
 - Strippability (BCA – Ammonium Nitrate pH 10)
 - Throwing Power (JCAT Method and Tubes)
 - Fatigue

2006 Status (Cont.)

- IZ-C17 Tank Up and Running Since 8-18-06
 - Chemistry Meets Specifications
 - Need to Use only Nickel Anodes (or Ni Plated Steel)
 - Passed Thickness, Composition and Adhesion Tests
 - Passed Hydrogen Embrittlement for Type 1a.1, 1a.2 and 2a Specimens
- Prepared Corrosion Specimens (4"x6" Steel)
- Prepared Fatigue Bars
- Prepared Fluid Immersion Test Specimens (ASTM F 483 1"x2" Steel Specimens)
- Prepared Throwing Power Test Specimens

Type 2a HE Testing






Fatigue Test Specimens



Throwing Power Test



Throwing Power Test

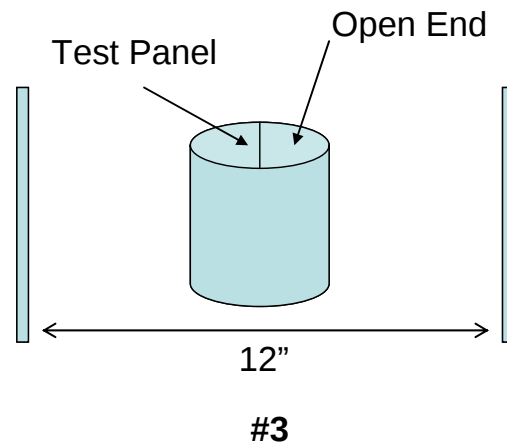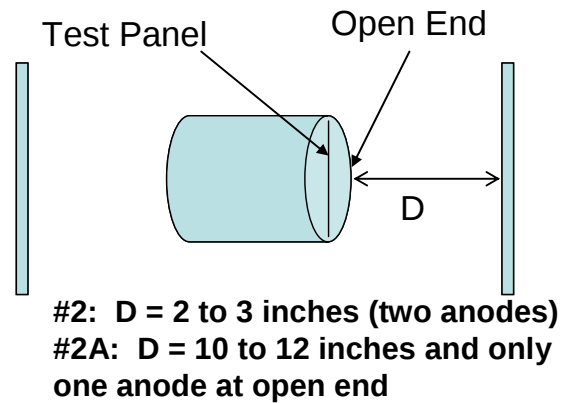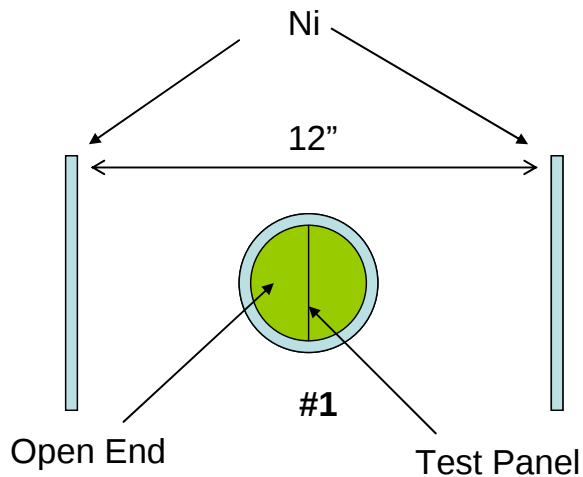

2007 Activity

- Prepare Zn-Ni Plated Fasteners (In Work)
- Perform Tests on Zn-Ni Plated Specimens
- Plate Tube IDs With Internal Anodes
- Prepare Specimens with Different Zinc – Nickel Ratios in Plating Bath
- Prepare DPS Draft Specification for LHE Zn-Ni Plating
- Support JCAT Phase II and III JTP