



AFRL-OSR-VA-TR-2014-0188

Quantum Optics in Diamond Nanophotonic Chips

Dirk Englund

THE TRUSTEES OF COLUMBIA UNIVERSITY IN THE CITY OF NEW YORK INC NEW YORK NY

07/01/2014

Final Report

DISTRIBUTION A: Distribution approved for public release.

Air Force Research Laboratory
AF Office Of Scientific Research (AFOSR)/ RTD
Arlington, Virginia 22203
Air Force Materiel Command

REPORT DOCUMENTATION PAGE					Form Approved OMB No. 0704-0188	
The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to the Department of Defense, Executive Service Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number. PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.						
1. REPORT DATE (DD-MM-YYYY)		2. REPORT TYPE			3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE				5a. CONTRACT NUMBER		
				5b. GRANT NUMBER		
				5c. PROGRAM ELEMENT NUMBER		
6. AUTHOR(S)				5d. PROJECT NUMBER		
				5e. TASK NUMBER		
				5f. WORK UNIT NUMBER		
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)					8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)					10. SPONSOR/MONITOR'S ACRONYM(S)	
					11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT						
13. SUPPLEMENTARY NOTES						
14. ABSTRACT						
15. SUBJECT TERMS						
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON	
a. REPORT	b. ABSTRACT	c. THIS PAGE			19b. TELEPHONE NUMBER (Include area code)	

PROGRESS REPORT

Program Manager: Dr. Gernot Pomrenke

QUANTUM OPTICS IN DIAMOND NANOPHOTONIC CHIPS

AFOSR Directorate: Physics and Electronics

Research Areas:

Complex Electronics and Fundamental Quantum Processes
Optics, Electromagnetics, Communication, and Signal Processing

June 1, 2014

Principal Investigator: Dirk R. Englund

Assistant Professor of Electrical Engineering and Computer Science
Massachusetts Inst. of Technology, Cambridge, MA 02139
P: (617) 324-7014, E: englund@mit.edu

Abstract

This report summarizes our recent progress on the development of photonic nanostructures for sensing and information processing. We have developed a nitrogen vacancy (NV) spin qubit-cavity system in the strong Purcell regime in which the spin qubit predominantly interacts with the cavity mode. This system is realized in a single-crystal diamond photonic crystal nanocavity with quality factors (Q) up to 10^4 . Furthermore, we measure electron spin coherence times of cavity-coupled NVs of 200 μ s. We have also developed techniques for NV-based super-resolution imaging and precision sensing, using high-speed parallel readout on a microscope camera; and we have developed techniques for precision clocks based on collective oscillation of ensembles of NVs. We also report on graphene electro-optic devices and sensors.

1 Progress towards on-chip quantum network in diamond

The field of quantum information processing (QIP) takes advantage of the properties of quantum mechanics to perform tasks that are classically impossible, including exponentially faster computational algorithms, unconditionally secure communication, and efficient simulation of complex physical and biological models [1, 2]. A number of recent theoretical and experimental advances have identified promising candidate systems for the implementation of quantum information technologies. A key requirement of such a system is the ability to create shared quantum entanglement among a large number of quantum memories that are individually addressable. This entanglement can be created through atom-photon interactions, allowing the establishment of quantum networks for the implementation of theoretical protocols, including the teleportation of distant stationary qubits via photons [3], the conversion of quantum states of light and motional states of atoms [4], and quantum computation through cavity-assisted interactions [5]. The quantum network requires long-lived quantum memories, such as particle spins, that can be efficiently mapped to photons through high-fidelity quantum interfaces. While several atomic systems, such as trapped ions, now fulfill these requirements, there is strong interest in solid-state implementations for scalability, stability, and device integration.

Among solid-state qubits, the negatively charged nitrogen vacancy (NV^-) center in diamond has in recent years emerged as one of the most promising systems. The NV center consists of a nitrogen atom adjacent to a vacancy in the diamond lattice. This lattice point defect creates an atom-like electronic wavefunction with well-defined spin and orbital angular momentum. Spin-selective optical transitions allow individual NV electron spins to be easily observed using standard confocal microscopy. The NV has two unpaired electrons that naturally provide a ground state with three electron spin sublevels. Two sublevels are employed to encode a quantum bit (qubit). Because of the nearly nuclear spin-free carbon lattice and weak spin-lattice interactions, these electronic ground states have extremely long coherence: milliseconds-scale phase coherence times have recently been reported [6] at room temperature, longer than any other solid state electron spin qubit. Furthermore, the electronic spin state may be coupled to proximal nuclear spins, providing additional degrees of freedom that have been employed as quantum logic gates [7]. A primary goal of this

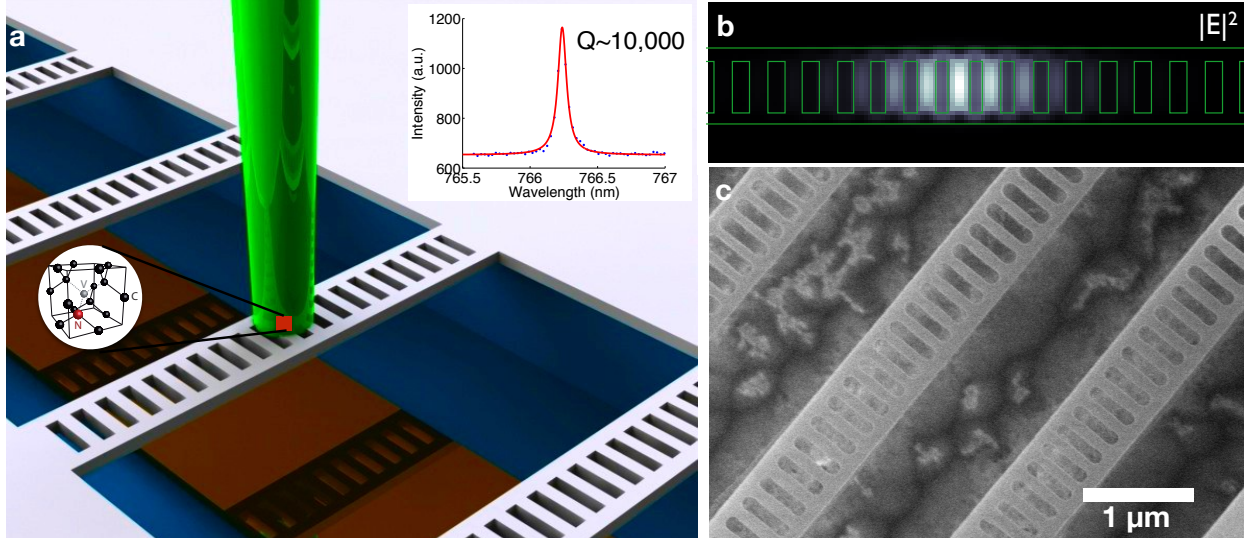


Figure 1: (a) The single-crystal diamond cavities are suspended over a microwave wire for spin manipulation. Fluorescence excitation and collection is from top through a confocal microscope. (b) The cavity design results in a maximum electric field in the diamond at the center to optimize coupling to the NV. (c) Scanning electron microscopy images of the cavities.

program is to develop techniques to entangle distant NV spin qubits by optical interactions. To this end, we have developing techniques to incorporate NV centers with long spin lifetime into optical resonators, and to efficiently interface these with photons. However, the lack of thin film technologies for crystalline diamond with low impurity levels hampers development of photonic interfaces to such diamond-based qubits. Over the course of this program, we have developed several methods for manufacturing slabs of diamond of 200 nm thickness and several microns in extent from high purity single crystal CVD diamond [8, 9, 10].

1.1 On-chip Quantum Control of a Cavity-Coupled NV system in Diamond

In recent months, we have also succeeded in a primary goal of this program – the fabrication of high-quality photonic crystal nanocavities in single crystal diamond. These cavities and related structures, such as waveguides, were fabricated by first thinning 10- μm thick diamond membranes (produced by mechanical polishing by Element 6) and then thinned using Cl and oxygen reactive ion etching chemistries to ~ 200 nm.

We employ a one-dimensional ladder PhC cavity design for maximal emitter enhancement and increased collection efficiency of cavity-coupled ZPL photons. The ladder PhC device consists of a suspended diamond waveguide patterned with a one-dimensional lattice of rectangular air gaps that defines a periodic dielectric profile, as shown in Fig.1. Low-temperature measurements indicate a Purcell enhancement of the zero-phonon-line (ZPL) of cavity-coupled NVs in excess of 60. An example of such a spectrum is shown in Fig. 2, where the spectrally selective enhancement of the ZPL is estimated at 122. This results in

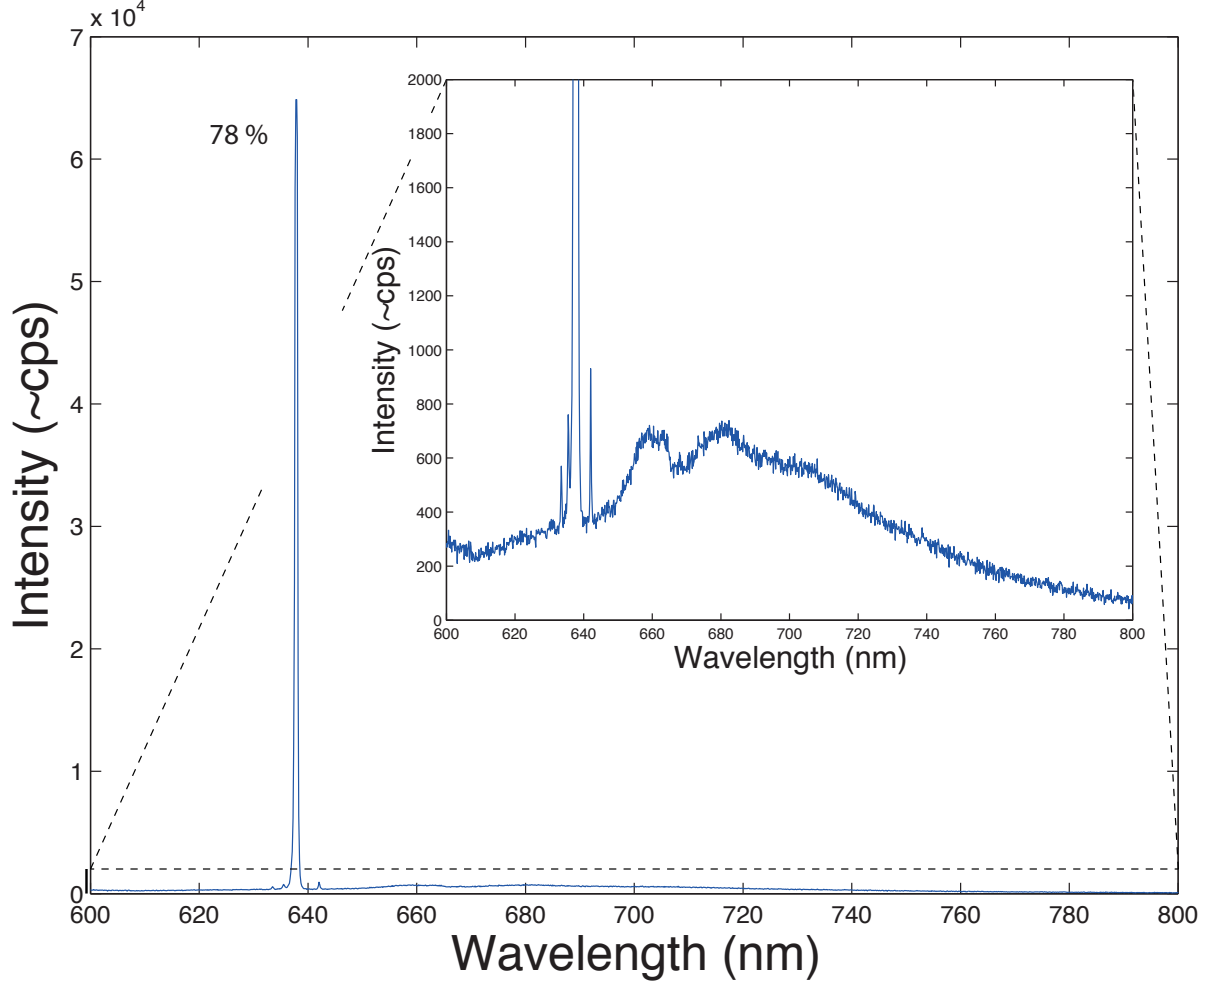


Figure 2: Coupled NV-cavity spectrum, showing an enhancement of the NV ZPL transition rate of ~ 62 .

more than 80% emission into the ZPL, compared to just $\sim 3\%$ for naturally occurring NVs.

The spin coherence times of NVs coupled to such cavities is similar to that observed in high-purity bulk diamond. We measured the coherence times using a confocal microscope setup and a microwave strip line integrated directly underneath the diamond cavities, as illustrated in Fig. 1. Our measurements indicate a phase coherence time in excess of $200\mu\text{s}$, as evaluated using a Hahn-echo protocol [10]. This represents a two order of magnitude improvement in the coherence time of solid state quantum memories coupled to cavity-based spin-photon interfaces. We are currently implementing dynamic decoupling spin protocols, which puts the spin coherence times of such emitters beyond 1 ms.

1.2 Scalable Fabrication of High Purity Diamond Nanocrystals with Long-Spin-Coherence Nitrogen Vacancy Centers

The nitrogen vacancy (NV) center in nanodiamond has been the focus of many recent investigations across a broad range of applications, including its use as a spin qubit in a hybrid photonic architecture and as highly localized sensor of temperature and magnetic fields that can be integrated with biological systems. The performance of the NV for these applications depends crucially on its electron spin phase coherence time, which is limited to microseconds in high-pressure high-temperature (HPHT) diamond nanocrystals due to a high concentration of paramagnetic impurities. With PECASE support, we have demonstrated a top-down fabrication process using a porous metal mask and a self-guiding reactive ion etching process that enables rapid nanocrystal creation across the entirety of a high-quality chemical vapor deposited (CVD) diamond substrate. High-purity CVD nanocrystals produced in this manner exhibit NV phase coherence times in excess of 200 μs . This record-long spin coherence time enabled record-precision magnetometry with diamond nanocrystals [11].

1.3 Wide-Field Multispectral Super-Resolution Imaging Using Spin-Dependent Fluorescence in Nanodiamonds

Recent advances in fluorescence microscopy have enabled spatial resolution below the diffraction limit by localizing multiple temporally or spectrally distinguishable fluorophores. With PECASE support, we introduced a super-resolution technique that deterministically controls the brightness of uniquely addressable, photostable NV centers, whose brightness is modulated deterministically by optically detected magnetic resonance techniques [12]. Using a CCD camera, this “deterministic emitter switch microscopy” (DESM) technique enables super-resolution imaging with localization down to 12 nm across a $35 \times 35 \mu\text{m}^2$ area. DESM is particularly well suited for biological applications such as multispectral particle tracking since fluorescent nanodiamonds are not only cytocompatible but also nonbleaching and bright. We observe fluorescence count rates exceeding 1.5×10^6 photons per second from single NV centers at saturation. When combined with emerging NV-based techniques for sensing magnetic and electric fields, DESM opens the door to rapid, super-resolution imaging for tracking and sensing applications in the life and physical sciences.

2 Graphene Photonics

Graphene features unique optical properties. Strong light-matter coupling yields an unexpectedly high opacity for an atomic monolayer with a startlingly simple value: it absorbs $\pi\alpha \approx 2.3\%$ of white light, where $\alpha = e^2/\hbar c \approx 1/137$ is the fine-structure constant. This is “a consequence of the unusual low-energy electronic structure of monolayer graphene that features electron and hole conical bands meeting each other at the Dirac point.” [13] Graphene’s optical absorption, and generally the light-graphene interaction, can be further increased by enhancing the light-matter interaction using waveguides or cavities. With support of this PECASE program, we have developed high-contrast graphene opto-electronic modulators [14, 15] based on graphene integrated in photonic crystal nanocavities. We have reported

operating speed in excess of 1 GHz [16], and are currently working on a new generation of devices that indicate substantially faster modulation speed.

Graphene photodetectors have recently attracted much attention because of the material's fast carrier dynamics and the possibility of photodetection as fast as 500 GHz, as well as intrinsic carrier multiplication effects in graphene. A remaining problem concerns the limited optical absorption in graphene, which results in a low optical responsivity. We addressed this problem by coupling a graphene photodetector to a silicon-on-insulator waveguide, see Fig. 4. The extended interaction between graphene and the silicon waveguide enables a high responsivity of photodetection of 0.108 A/W, competitive with current non-avalanche Ge detectors for silicon photonics integration [17, 18]. Owing to the high mobility of both electrons and holes, the photodetector displays a high frequency response (up to 20 GHz) even under zero bias operation with a responsivity of 16 mA/W. We have also demonstrated data transmission at up to 12.5 Gbps [19]. We recently also demonstrated a photonic cavity-integrated high-responsivity graphene photodetector [20], which enables wavelength-selective receivers with ultra-small footprint on photonic integrated circuits.

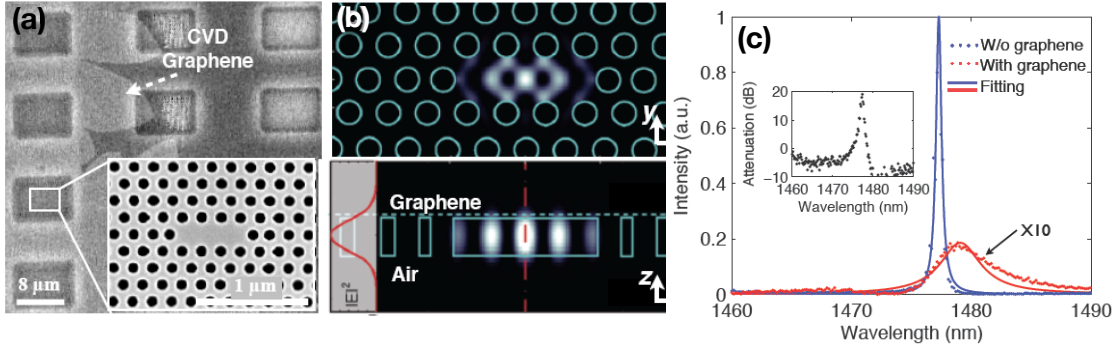


Figure 3: Enhancement of coupling from free space modes to graphene. (a) Scanning electron microscope image of PPC cavities integrated with single-layer graphene. The darker shade defines the edges of the graphene monolayer. (b) Simulated energy distribution of fundamental resonant mode of the L3 cavity, shown in plane (top) and in cross-section (bottom). The graphene layer interacts with the evanescent field. (c) The single atomic layer of graphene couples strongly to the cavity field, sharply reducing the cavity quality factor by over $100\times$. The strong interaction allows for cavity-enhanced Raman spectroscopy on sub-wavelength regions of a graphene sample [14] as well as high-contrast electro-optic modulation [15].

3 Polymer Photonics for Information Processing and Sensing

Polymers have appealing optical, biochemical, and mechanical qualities, including broadband transparency, ease of functionalization, and biocompatibility. However, their low refractive indices have precluded wavelength-scale optical confinement and nanophotonic applications in polymers. With PECASE support, we developed a suspended polymer photonic crystal (SPPC) architecture that enables the implementation of nanophotonic structures typically limited to high-index materials [21]. We demonstrated nanophotonic band-edge filters, waveguides, and nanocavities featuring quality (Q) factors exceeding 2,300 and mode

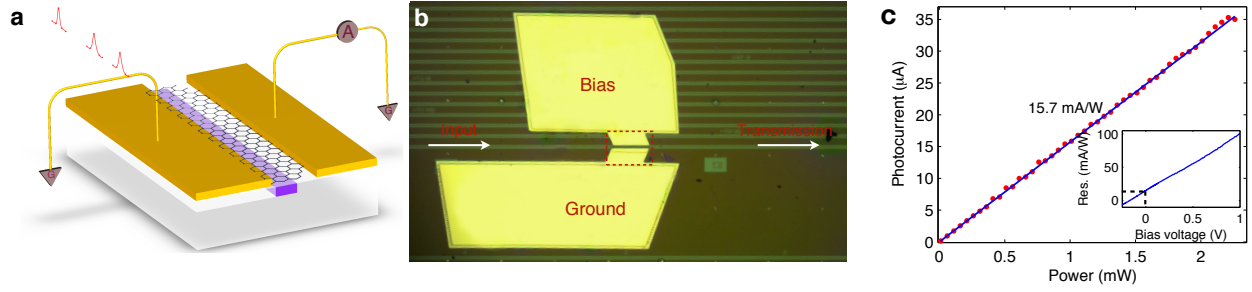


Figure 4: A waveguide-integrated graphene photodetector. (a) Illustration of the device. The silicon bus waveguide with cross-section of 220 nm by 520 nm is fabricated on a SOI wafer and then planarized using SiO_2 . A graphene layer is transferred onto the planarized waveguide and is separated from the waveguide by a ~ 10 nm-thick SiO_2 layer. Two metal electrodes contact the graphene and conduct the generated photocurrent. One of the electrodes is closer to the waveguide to create a potential difference on graphene coupling with the evanescent field of the waveguide, which enables the ultrafast and efficient photodetection. **b**, Optical micrograph of the device with a bi-layer graphene covering on the waveguide. Two Ti/Au (1/40 nm) paddles are evaporated onto the graphene sheet. **(c)** Measured photocurrent of the device with respect to the incident power at zeros bias, showing a photoresponsivity of 15.7 mA/W. Inset: Bias dependence of the photoresponsivity. The used laser has a wavelength of 1550 nm.

volumes below $1.7(\lambda/n)^3$. The unprecedentedly high Q/V_{mode} ratio results in a spectrally selective enhancement of radiative transitions of embedded emitters via the cavity Purcell effect with an enhancement factor exceeding 100. Moreover, the SPPC architecture allows straightforward integration of nanophotonic networks, shown here by a waveguide-coupled cavity drop filter with sub-nanometer spectral resolution. The nanoscale optical confinement in polymer promises new applications ranging from optical communications to organic opto-electronics.

Following on our recent demonstration of high- Q cavities and networks in polymer photonic crystals [21], we have also developed nanophotonic 1D polymer photonic crystal resonators that confine light at the wavelength scale with extremely low losses, enabling quality factors Q in excess of 8000 (limited by our detector resolution) at 600-700 nm. These are, to our knowledge, the highest quality factors achieved in photonic crystal cavities in this wavelength range. We have now employed these cavities for precision sensing of gases and volatile liquids [22].

4 Summary of Publications under this Program

Journal Papers (published and under review):

1. Hannah Clevenson, Pierre Desjardins, Xuetao Gan, and Dirk Englund. High- Q suspended polymer photonic crystal cavities for gas sensing. under review (2014)
2. Scalable Fabrication of High Purity Diamond Nanocrystals with Long-Spin-Coherence Nitrogen Vacancy Centers, Matthew E. Trusheim, Luozhou Li, Edward H. Chen, Ophir Gaathon, Hassaram Bakhru, and Dirk Englund, Nano Letters 14 (2013)

-
3. Enhanced Photodetection in Graphene-Integrated Photonic Crystal Cavity, Ren-Jye Shiue, Xuetao Gan, Yuanda Gao, Luozhou Li, Xinwen Yao, Attila Szep, Dennis Walker, Jr., James Hone, and Dirk Englund, *Appl. Phys. Lett.* 103, 241109 (2013)
 4. Chip-integrated ultrafast graphene photodetector with high responsivity, X. Gan, R.J. Shiue, Y. Gao, I. Meric, T. F. Heinz, K. Shepard, J. Hone, S. Assefa, & D. Englund, *Nature Photonics AOP* (2013). In the news: MIT News, Nature, Nature Photonics News and Views, Nanowerk, Gizmodo, Photonics.com, LiveMint, IEEE Spectrum, Phys.org, RD Magazine, NanotechWeb,
 5. Controlled light-matter interaction in graphene electro-optic devices using nanophotonic cavities and waveguides, Xuetao Gan, Ren-Jye Shiue, Yuanda Gao, Solomon Assefa, James Hone and Dirk Englund, *IEEE JOURNAL OF SELECTED TOPICS IN QUANTUM ELECTRONICS on Graphene Optoelectronics* (2013)
 6. Reactive ion etching: optimized diamond membrane fabrication for transmission electron microscopy, L. Li, M. Trusheim, O. Gaathon, K. Kisslinger, C.-J. Cheng, M. Lu, D. Su, X. Yao, H.-C. Huang, I. Bayn, A. Wolcott, R. M. Osgood, Jr., and D. Englund, *Journal of Vacuum Science and Technology B*, Vol. 36 (2013). Among July 2013 Top 20 Most Downloaded articles
 7. Wide-field multispectral super-resolution imaging using spin-dependent fluorescence in nanodiamonds, E. H. Chen, O. Gaathon, M. E. Trusheim, and D. Englund, *Nano Lett.*, 2013, 13 (5), pp 20732077
 8. Nanophotonic Filters and Integrated Networks in Flexible 2D Polymer Photonic Crystals, X. Gan, H. Clevenston, C.-C. Tsai, L. Li, and D. Englund, *Nature Scientific Reports* 3, Article number: 2145(2013).
 9. High-Contrast Electro-Optic Modulation of a Photonic Crystal Nanocavity by Electrical Gating of Graphene, Xuetao Gan, Ren-Jye Shiue, Yuanda Gao, Kin Fai Mak, Xinwen Yao, Luozhou Li, Attila Szep, Dennis Walker Jr., James Hone, Tony F. Heinz, and Dirk Englund, *Nano Lett.*, 2013, 13 (2), pp 691696. In the news: NanoTech Technology Update
 10. Timekeeping with electron spin states in diamond, J. S. Hodges, N. Y. Yao, D. Maclaurin, C. Rastogi, M. D. Lukin, and D. Englund, *Physical Review A* 87, 032118 (2013). In the news: PRA Highlight, Nature research highlight
 11. Strong enhancement of light-matter interaction in graphene coupled to a photonic crystal nanocavity, X. Gan, K. F. Mak, Y. Gao, Y. You, F. Hatami, J. Hone, T. F. Heinz, and D. Englund, *Nano Letters*, 12(11):56265631 (2012). In the News: NanoTechWeb Research Update
 12. Long-lived nitrogen vacancy spin coherence in high-purity diamond membranes, Jonathan Hodges, Luozhou Li, Ming Lu, Edward H Chen, Matthew E Trusheim, S Allegri, Xinwen Yao, O Gaathon, Hassaram Bakhru, and Dirk Englund, *New Journal of Physics* 14 (2012).

-
13. A high-resolution spectrometer based on a compact planar two dimensional photonic crystal cavity array, Xuetao Gan, Nadia Pervez, Ioannis Kymissis, Fariba Hatami, and Dirk Englund, Appl. Phys. Lett. 100, 23 (2012) Nature Photonics Highlight
 14. Ion-Exfoliated Single-Crystal-Diamond Membranes Exhibiting Nitrogen-Vacancy Color Centers, O. Gaathon, J. S. Hodges, E. H. Chen, L. Li, S. Bakhru, H. Bakhru, D. Englund, and R. M. Osgood, Jr., Volume 35, Issue 3, 361365 (2013)
 15. Ultrafast photon-photon interaction in a strongly coupled quantum dot-cavity system, D. Englund, A. Majumdar, M. Bajcsy, A. Faraon, P. Petroff & J. Vuckovic, Phys. Rev. Lett. 108:093604 (2012).

Patent applications:

1. D. Englund et al, Ultra-high-resolution conformal lithography for patterning arbitrary samples
2. X. Gan and D.Englund, Graphene Photonics for resonator-enhanced ultrafast electro-optic processes and all-optical interactions (2012)
3. X. Gan and D. Englund, Chip-integrated Infrared Detector Employing Cavity-Enhanced Upconversion (2012)
4. X. Gan and D. Englund, Ultra-compact, high quality photonic devices in a planar polymer-on-air architecture” (2011)
5. E. Chen and D. Englund, Deterministic Emitter Switch Microscopy (DESM)” (2011)
6. D Englund, Conjugates Of Nano-Diamond And Magnetic Or Metallic Particles, Wo Patent 2,013,066,446
7. D Englund And E Chen, Systems And Methods For Deterministic Emitter Switch Microscopy, Wo Patent 2,013,059,404
8. D Englund And C Rastogi, Ultracompact Fabry-Perot Array For Ultracompact Hyperspectral Imaging, Wo Patent 2,013,059,665
9. D Englund, J Hodges, M Lukin, N Yao, High-Precision Ghz Clock Generation Using Spin States In Diamond, Wo Patent 2,013,040,446

References

- [1] M. A. Nielsen and I. L. Chuang. *Quantum Computation and Quantum Information*. Cambridge Univ. Press, Cambridge, 2000.
- [2] D. Bouwmeester, editor. *The physics of quantum information: quantum cryptography, quantum teleportation, quantum computation*. Springer-Verlag, London, UK, 2000.

-
- [3] J. I. Cirac, P. Zoller, H. J. Kimble, and H. Mabuchi. Quantum State Transfer and Entanglement Distribution among Distant Nodes in a Quantum Network. *Phys. Rev. Lett.*, 78(16):3221–24, April 1997.
 - [4] A S Parkins and H J Kimble. Quantum state transfer between motion and light. *Journal of Optics B: Quantum and Semiclassical Optics*, 1(4):496, 1999.
 - [5] L.-M. Duan and H. J. Kimble. Scalable photonic quantum computation through cavity-assisted interactions. *Phys. Rev. Lett.*, 92(12):127902, 2004.
 - [6] G. Balasubramanian, P. Neumann, D. Twitchen, Matthew Markham, Roman Kolesov, Norikazu Mizuochi, Junichi Isoya, Jocelyn Achard, Johannes Beck, Julia Tissler, Vincent Jacques, P. R. Hemmer, F. Jelezko, and J. Wrachtrup. Ultralong spin coherence time in isotopically engineered diamond. *Nat. Mater.*, 8:383–387, apr 2009.
 - [7] P. Neumann, N. Mizuochi, F. Rempp, P. Hemmer, H. Watanabe, S. Yamasaki, V. Jacques, T. Gaebel, F. Jelezko, and J. Wrachtrup. Multipartite Entanglement Among Single Spins in Diamond. *Science*, 320(5881):1326–1329, 2008.
 - [8] Luozhou Li, Edward Chen, Jonathan Hodges, Ming Lu, Ophir Gaathon, Jr. Richard Osgood, and Dirk Englund. Reactive ion etching: optimized diamond thin-membrane fabrication for transmission electron microscopy. *Journal of Vacuum Science and Technology B*, 35, 2013.
 - [9] O. Gaathon, J.S. Hodges, E.H. Chen, L. Li, S. Bakhru, H. Bakhru, D. Englund, and R.M. Osgood Jr. Planar fabrication of arrays of ion-exfoliated single-crystal-diamond membranes with nitrogen-vacancy color centers. *Optical Materials*, 35(3):361 – 365, 2013.
 - [10] Luozhou Li, Tim Schroder, Edward H. Chen, Michael Walsh, Igal Bayn, Jordan Goldstein, Ophir Gaathon, Matthew E. Trusheim, Ming Lu, Hannah Clevenson, Sara Mouradian, Jacob Mower, Hassaram Bakhru, Matthew L. Markham, Daniel J. Twitchen, and Dirk Englund. On-chip quantum control of a cavity-coupled nv system in diamond. *to be submitted*, 2014.
 - [11] Matthew E. Trusheim, Luozhou Li, Abdelghani Laraoui, Edward H. Chen, Ophir Gaathon, Hassaram Bakhru, Carlos A. Meriles, and Dirk Englund. Scalable fabrication of high purity diamond nanocrystals with long-spin-coherence nitrogen vacancy centers. *Nano Letters*, 14(1):32–36, 2013.
 - [12] E. Chen, O. Gaathon, M. Trusheim, and D. Englund. Wide-field multispectral super-resolution imaging using spin-dependent fluorescence in nanodiamonds. *Nano Letters*, 13(5):2073–2077, 2013.
 - [13] R. R. Nair, P. Blake, A. N. Grigorenko, K. S. Novoselov, T. J. Booth, T. Stauber, N. M. R. Peres, and A. K. Geim. Fine structure constant defines visual transparency of graphene. *Science*, 320(5881):1308, 2008.

-
- [14] Xuetao Gan, Kin Fai Mak, Yuanda Gao, Yumeng You, Fariba Hatami, James Hone, Tony F. Heinz, and Dirk Englund. Strong enhancement of light–matter interaction in graphene coupled to a photonic crystal nanocavity. *Nano Letters*, 12(11):5626–5631, 2012.
 - [15] Xuetao Gan, Ren-Jye Shiue, Yuanda Gan, Kin Fai Mak, Xinwen Yao, Luozhou Li, Attila Szep, James Hone Dennis Walker Jr., Tony F. Heinz, and Dirk Englund. High-Contrast Electro-Optic Modulation of a Photonic Crystal Nanocavity by Electrical Gating of Graphene. *Nano Letters*, 13(2):691–696, 2013.
 - [16] X. Gan, R.-J. Shiue, Y. Gao, S. Assefa, J. Hone, and D. Englund. Controlled light-matter interaction in graphene electrooptic devices using nanophotonic cavities and waveguides. *Selected Topics in Quantum Electronics, IEEE Journal of*, 20(1):6000311–6000311, 2013.
 - [17] V. Sorianoello, M. Balbi, L. Colace, G. Assanto, L. Socci, L. Bolla, G. Mutinati, and M. Romagnoli. Guided-wave photodetectors in germanium on soi optical chips. *Physica E: Low-dimensional Systems and Nanostructures*, 41(6):1090 – 1093, 2009. `proceedings of the E-MRS 2008 Symposium C: Frontiers in Silicon-Based Photonics`.
 - [18] Jian Wang and Sungjoo Lee. Ge-photodetectors for si-based optoelectronic integration. *Sensors*, 11(1):696–718, 2011.
 - [19] Xuetao Gan, Ren-Jye Shiue, Yuanda Gao, Inanc Meric, Tony F. Heinz, Kenneth Shepard, James Hone, Solomon Assefa, and Dirk Englund. Chip-integrated ultrafast graphene photodetector with high responsivity. *Nature Photonics*, 7(883–887), 2013.
 - [20] Ren-Jye Shiue, Xuetao Gan, Yuanda Gao, Luozhou Li, Xinwen Yao, Attila Szep, Dennis Walker, James Hone, and Dirk Englund. Enhanced photodetection in graphene-integrated photonic crystal cavity. *Applied Physics Letters*, 103(24):–, 2013.
 - [21] Xuetao Gan, Hannah Clevenston, Pierre Desjardins, Luozhou Li, and Dirk Englund. Nanophotonic filters and integrated networks in flexible 2d polymer photonic crystals. *Nature Scientific Reports*, 3(2145), 2013.
 - [22] Hannah Clevenston, Pierre Desjardins, Xuetao Gan, and Dirk Englund. High-q suspended polymer photonic crystal cavities for gas sensing. *under review at Applied Physics Letters*, 2014.