

WAL TR 401/300
TECHNICAL REPORT

WATERTOWN ARSENAL
WATERTOWN 72, MASS.

COPY NO. 2

401/300



WATERTOWN ARSENAL LABORATORIES

AD-300193

THE HOT HARDNESS OF TITANIUM AND TITANIUM ALLOYS

BY

F. R. LARSON

O.O. PROJECT: TB4-003, MATERIALS FOR
LIGHTWEIGHT CONSTRUCTION
D/A PROJECT: 583-32-003
REPORT NO.: WAL TR 401/300
FILING SUBJECT: TITANIUM

DTIC
ELECTE
SEP 28 1983
A

This document has been approved
for public release and sale; its
distribution is unlimited.

JULY 1958

88 09 22 270

WATERTOWN ARSENAL
WATERTOWN 72, MASS.

DTIC FILE COPY

ADA 952258

TITANIUM

THE HOT HARDNESS OF TITANIUM AND TITANIUM ALLOYS

TECHNICAL REPORT

By

F. R. Larson

O.O. Project: TB4-003, Materials for
Lightweight Construction
D/A Project: 593-32-003
Report No.: WAL TR 401/300
Filing Subject: Titanium

WATERTOWN ARSENAL
WATERTOWN 72, MASS.

WATERTOWN ARSENAL LABORATORIES

TITLE

THE HOT HARDNESS OF TITANIUM AND TITANIUM ALLOYS

ABSTRACT

The hot hardness of 27 different heats of titanium and titanium alloys was studied. Tests were conducted on a modified Rockwell machine in an argon atmosphere. Results indicate that low alloy heats lose their hardnesses at a fairly high even rate. On the other hand, high alloy heats hold their hardnesses well up to about 1100°F, and then the hardness drops off very sharply with increasing temperature.

The influence of alloying elements in promoting resistance to softening was evaluated at 900°F. Iron was found to be the most effective with the other elements being arranged in order of decreasing effect, as follows: manganese, molybdenum, aluminum, zirconium, and chromium.

Frank R. Larson

F. R. LARSON
Physical Metallurgist

APPROVED:

J. F. Sullivan

J. F. SULLIVAN
Director
Watertown Arsenal Laboratories



Accession For	
NTIS GRA&I	☒
DTIC TAB	☐
Unannounced	☐
Justification	
By	
Distribution/	
Availability Codes	
Avail and/or	
Dist	Special
A	

UNANNOUNCED

INTRODUCTION

Of all the mechanical tests at our disposal, hardness is probably the most commonly used for it is both convenient and economical.^{1,2} Because of these reasons, along with others, engineers and process metallurgists use this test extensively. Of particular interest in hot fabrication and elevated temperature service is the dependence of hardness upon temperature. Justification of such interest is based upon the correlations that have been established between tensile strength properties and hardness.^{3,4} That is, if the temperature dependence of hardness is known for any alloy, it is possible to predict the approximate tensile strength at equivalent temperatures. Furthermore, it is known that when there are sharp changes in the hardness temperature curves there are usually marked changes in the formability or forming forces. It is therefore quite evident that considerable valuable information may be obtained at a minimum of cost. It was for these reasons that a study of the hot hardness of titanium and titanium alloys was undertaken. Furthermore, the tensile, creep, and rupture properties of titanium at elevated temperatures have been summarized by Battelle Memorial Institute,⁵ but no hot hardness data have been yet reported.

The hot hardness testing was done at Mallory-Sharon Titanium Corporation under Contract Numbers DA-33-008-ORD-887 and DA-33-008-ORD-196 on samples supplied by this laboratory. The results of these hot hardness tests were reported in the form of separate letter reports, one for each alloy tested. Furthermore, no attempt was made to analyze the data. It is therefore the purpose of this report to compile all of the data in one document and, of greater importance, to interpret the results.

MATERIALS

Fifteen commercially available titanium and titanium alloys selected for the experiment were chosen as representative of production composition. Twelve experimental compositions were included particularly because of reported interest in them for one reason or another. The chemical analysis of these materials is listed in Table I. The microstructures and true stress-true strain properties for Lots 1 through 12 and the impact properties of Lots 1 through 4, 6, 9, 10, and 12 have been previously reported.^{6,7} The tensile properties of the remainder of the materials are listed in Table II. All materials were annealed for one hour at 1300°F in argon prior to testing.

TEST PROCEDURE

The details of the test apparatus employed by the contractor are presented in Figures 1 and 2. Equipment consisted of a modified Rockwell hardness tester. The modifications were mainly a furnace mounted on an elevating anvil, in which a protective atmosphere, in this case argon, could be provided, and an extension on the indenter so that it could be located above the specimen in the furnace. In addition, there was also a provision for locating the specimen from outside of the furnace so that several tests could be run on the same sample without opening the furnace.

The hardness was measured on the Rockwell "A" scale at room temperature, 300°F, and then in increments of 100°F until the readings went off scale or 1300°F whichever was reached first. Time of load application and time at temperature were not reported and is not considered important if equilibrium was reached as was required in the contract. Furthermore, all specimens were annealed at or above the highest testing temperature. Four specimens that were checked for room temperature hardness after a run had been made, revealed that no change had occurred, indicating no influence of contamination or tempering. The results of this testing are portrayed in Figures 3 through 29.

DISCUSSION OF RESULTS

Examination of the above curves, plotted on the conventional log of hardness versus linear temperature basis, will reveal that there are considerable differences in the behavior patterns for the various alloys. The different compositions are softened in a variety of ways. The important observation to make from a fabrication standpoint is that the main drop in hardness, especially for the more heat-resistant alloys, occurred at approximately 1200°F. Furthermore, when 1300°F was reached many alloys were so soft that it was impossible to obtain hardness readings.

Apparently this sharp change in slope is the equi-cohesive break⁸ corresponding to the recrystallization temperature and also the maximum useful temperature for medium and long-time service applications for these alloys. There is, of course, another possibility based on the fact that the hot strength of the hexagonal close-packed alpha phase exceeds by a considerable margin that of body-centered cubic phase (see Reference 8). This possibility exists in the alloys that contain beta-stabilizing elements in sufficient quantity to lower the alpha to alpha plus beta phase boundary into the temperature range in which the hardness tests were conducted so that the softer beta sharply reduced the hot hardness of the mixed alpha plus beta structure.

Another important point to study is the relative resistance to softening of the various compositions, or more ideally, to discover the separate effects of the various alloy elements. Finlay and Snyder,⁹ while working on alpha titanium interstitial alloys containing carbon, nitrogen, and oxygen, reported a linear relationship between the tensile strength and the equivalent nitrogen (atomic percent). In their investigation, it was established that nitrogen was the most powerful strengthener, and the other interstitials were converted to equivalent nitrogen by a ratio, such as oxygen being only 0.82 percent as effective as nitrogen. This approach was utilized to evaluate the influence of alloying elements upon the hot hardness of these alloys. First, 900°F was chosen as the temperature for study mainly because it is the maximum temperature just below the lowest known for these alloy's alpha to beta reaction. For the establishment of the factors, main consideration was given to those elements that appeared to produce the most effect, mainly the metallic elements. Oxygen, nitrogen, and carbon were not considered because their influence was small, and the atomic

percentages when compared with the metallic elements were also small. It became immediately obvious that iron produced the most powerful effect, and, therefore, by comparing compositions at equivalent hot hardness levels the influence of the remaining alloying elements was determined in terms of iron, with the following equation covering the conditions for this experiment as illustrated by Figure 30:

$$\text{Equivalent \%Fe} = \%Fe + \frac{\%Mn}{3.38} + \frac{\%Mo}{5.10} + \frac{\%Al}{6.40} + \frac{\%Zr}{7.47} + \frac{\%Cr}{13.66}$$

The elements in this equation are arranged in order of decreasing effect, with iron equal to one. Manganese was found to be approximately 1/3.4, molybdenum 1/5.1, aluminum 1/6.4, zirconium 1/7.4, and chromium 1/13.6 as effective as the iron.

CONCLUSIONS

The results of this hot hardness program reveal that titanium and titanium alloys exhibit similar behavior patterns to other metals, as follows:

1. Low alloy compositions lose their hardnesses fairly evenly with increasing temperatures with no sharp breaks occurring in the hardness versus temperature curves.
2. High alloy compositions hold their hardnesses with increasing temperature fairly well depending upon the alloy; and finally when the temperature is sufficiently high (1000 to 1200°F) the hardness drops off very sharply at or near a temperature that appears to be the equi-cohesive temperature.
3. The effect of alloying elements upon the hot hardness at 900°F was studied, and it was found that iron exhibited the most potent effect. The other alloying elements were rated in terms of equivalent iron, and the following equation expresses the results:

$$\text{Equivalent \%Fe} = \%Fe + \frac{\%Mn}{3.38} + \frac{\%Mo}{5.10} + \frac{\%Al}{6.40} + \frac{\%Zr}{7.47} + \frac{\%Cr}{13.66}$$

* % refers to atomic percent.

ACKNOWLEDGMENT

The author would like to express his thanks to Mr. S. V. Arnold* who arranged the hot hardness contract, to Mr. J. Nunes** who helped in analyzing the data, and to Mr. D. C. Buffum* who supplied the zirconium alloys.

* Physical Metallurgist, Watertown Arsenal Laboratories

** Physical Science Aide, Watertown Arsenal Laboratories

REFERENCES

1. GAROFALO, F., SMITH, G. V. and MARSDEN, D. C., "The Temperature Dependence of the Hardness of 'Pure' Iron and Various Ferritic Steels," *Trans ASM* 49 (1957) 372.
2. WESTBROOK, J. H., "Temperature Dependence of the Hardness of Pure Metals," *Trans ASM* 45 (1953) 221.
3. BENS, F. P., "Hardness Testing of Metals and Alloys at Elevated Temperatures," *Trans ASM* 38 (1947) 505.
4. GAROFALO, F., MALENOCK, P. R. and SMITH, G. V., "Hardness of Steels at Elevated Temperatures," *Trans ASM* 45 (1953) 377.
5. "The Properties of Titanium Alloys at Elevated Temperatures," TML Report No. 82, Sept. 10, 1957 Titanium Metallurgical Laboratory, Battelle Memorial Institute.
6. KULA, E. B., and LARSON, F. R. "True Stress-True Strain Properties of Titanium and Titanium Alloys," Watertown Arsenal Laboratories Report No. WAL 401/241, 2 Sept. 1955.
7. KULA, F. B. and LARSON, F. R., "Effect of Vacuum Annealing on the Impact Properties of Titanium and Titanium Alloys," Watertown Arsenal Laboratories Report No. WAL 401/259, 19 April 1956.
8. LUNSFORD, J. and GRANT, N. J., "Relative High Temperature Properties of the Hexagonal Close-Packed and Body-Centered Cubic Structures in Iodide-Titanium," *Trans ASM* 49 (1957) 328.
9. FINLAY, W. L., and SNYDER, J. A., "Effects of Three Interstitial Solutes (Nitrogen, Oxygen, and Carbon) on the Mechanical Properties of High Purity Alpha Titanium," *Trans AIME* 108 (1950) 277.

TABLE I

CHEMICAL ANALYSIS

Mark	Grade	Heat No.	O	H	N	C	Fe	Al	Cr	Mn	Mo	Sb	Zr	Test Specimen No.
RH1G4	A55	T5-3328	.119	.0052	.034	.02	.24	-	-	-	-	-	-	1
TH1F2	A55	T5-3303	.096	.0030	.022	.01	.26	-	-	-	-	-	-	2
SXA7	RS55	U*	.164	.013	.036	.09	.10	-	-	-	-	-	-	3
TH1G2	Ti100A	-	.127	.0090	.054	.05	.48	-	-	-	-	-	-	4
SXA4	4Mn	RLA-506	.203	.0068	.034	.06	.15	-	-	3.36	-	-	-	5
RH1G5	CL10M	A-3278	.137	.0062	.040	.03	.26	-	-	6.44	-	-	-	6
RXG5	CL10M	B-3275	.156	.0079	.024	.03	.19	-	-	6.18	-	-	-	7
RJ1A2	CL10M	AW3477B	.112	.009	.024	.032	.09	-	-	6.86	-	-	-	8
RH1B2	CL30AM	B3198	.135	.0062	.030	.06	.16	3.34	-	3.40	-	-	-	9
TH1J2	Ti150A	-	.437	.025	.046	.014	.84	-	1.27	-	-	-	-	10
TXF2	Ti150A	L-903	.335	.012	.058	.04	1.5	-	2.61	-	-	-	-	11
TH1L5	Ti150B	L-1038	.163	.016	.054	.05	4.6	-	4.66	-	4.8	-	-	12
RH1C1	A55	-	-	-	-	.10	-	-	-	-	-	-	-	13
RH1E2	CL10M	-	-	-	-	.13	-	-	-	7.9	-	-	-	14
RH1O1	RC70	-	-	-	-	.09	-	-	-	-	-	-	-	15
RS14	-	-	-	-	.034	.115	1.52	-	3.85	.088	-	1.53	-	16
R26	-	-	-	-	.045	.03	.27	3.37	-	-	-	-	-	17
R110	-	-	-	-	.064	.09	-	-	3.93	6.77	4.26	-	-	18
A25	-	-	.125	.008	.036	.04	.06	-	3.77	-	2.48	-	-	19
K100	-	-	.15	.023	.040	Tr	5.35	-	11.84	-	-	-	-	20
TiZ1	-	-	.104	.0034	.014	.02	.08	-	-	-	-	-	>.01	21
TiZ2	-	-	.115	.0034	.016	.025	.09	-	-	-	-	-	5.22	22
TiZ3	-	-	.111	.0033	.015	.025	.11	-	-	-	-	-	9.45	23
TiZ4	-	-	.100	.0042	.008	.025	.09	-	-	-	-	-	13.8	24
TiZ5	-	-	.104	.0065	.010	.03	.10	-	-	-	-	-	24.9	25
TiZ6	-	-	.103	.0054	.013	.03	.10	-	-	-	-	-	26.3	26
TiZ7	-	-	.104	.0031	.016	.04	.11	-	-	-	-	-	31.5	27

*Denotes experimental alloy.

TABLE I


TABLE II
MECHANICAL PROPERTIES
(Room Temperature)


EXPERIMENTAL ALLOYS						
Mark	Specimen Direction	Yield Strength		Tensile Strength	% Elong.	% R.A.
		.01%	.1%			
RS-14	L	75,800	89,000	114,600	19.3	34.5
	T	87,000	97,000	118,800	15.0	25.1
A-25	L	92,000	99,000	106,400	25.0	68.3
	T	97,000	101,000	108,000	24.3	67.3
R22	L	88,000	96,000	119,000	20.7	51.7
	T	83,000	99,000	124,500	19.3	45.3
R26	L	68,500	76,000	89,000	19.3	52.1
	T	51,500	59,500	76,000	22.9	49.8
R110	L	134,100	139,000	139,500	16.4	48.0
	T	136,000	141,000	141,500	20.7	51.4
K100	L	141,000	149,500	155,000	12.1	43.2
	T	141,000	-	144,250	*	*

COMMERCIAL ALLOYS						
	Grade					
RH1-C1	A55	68,000	**	86,500	27.0	**
RH1-D1	RC70	85,400	**	98,600	24.3	45.2
RH1-E2	C110M	126,900	**	132,800	23.2	**


*Broke on gage mark.

**Not reported.

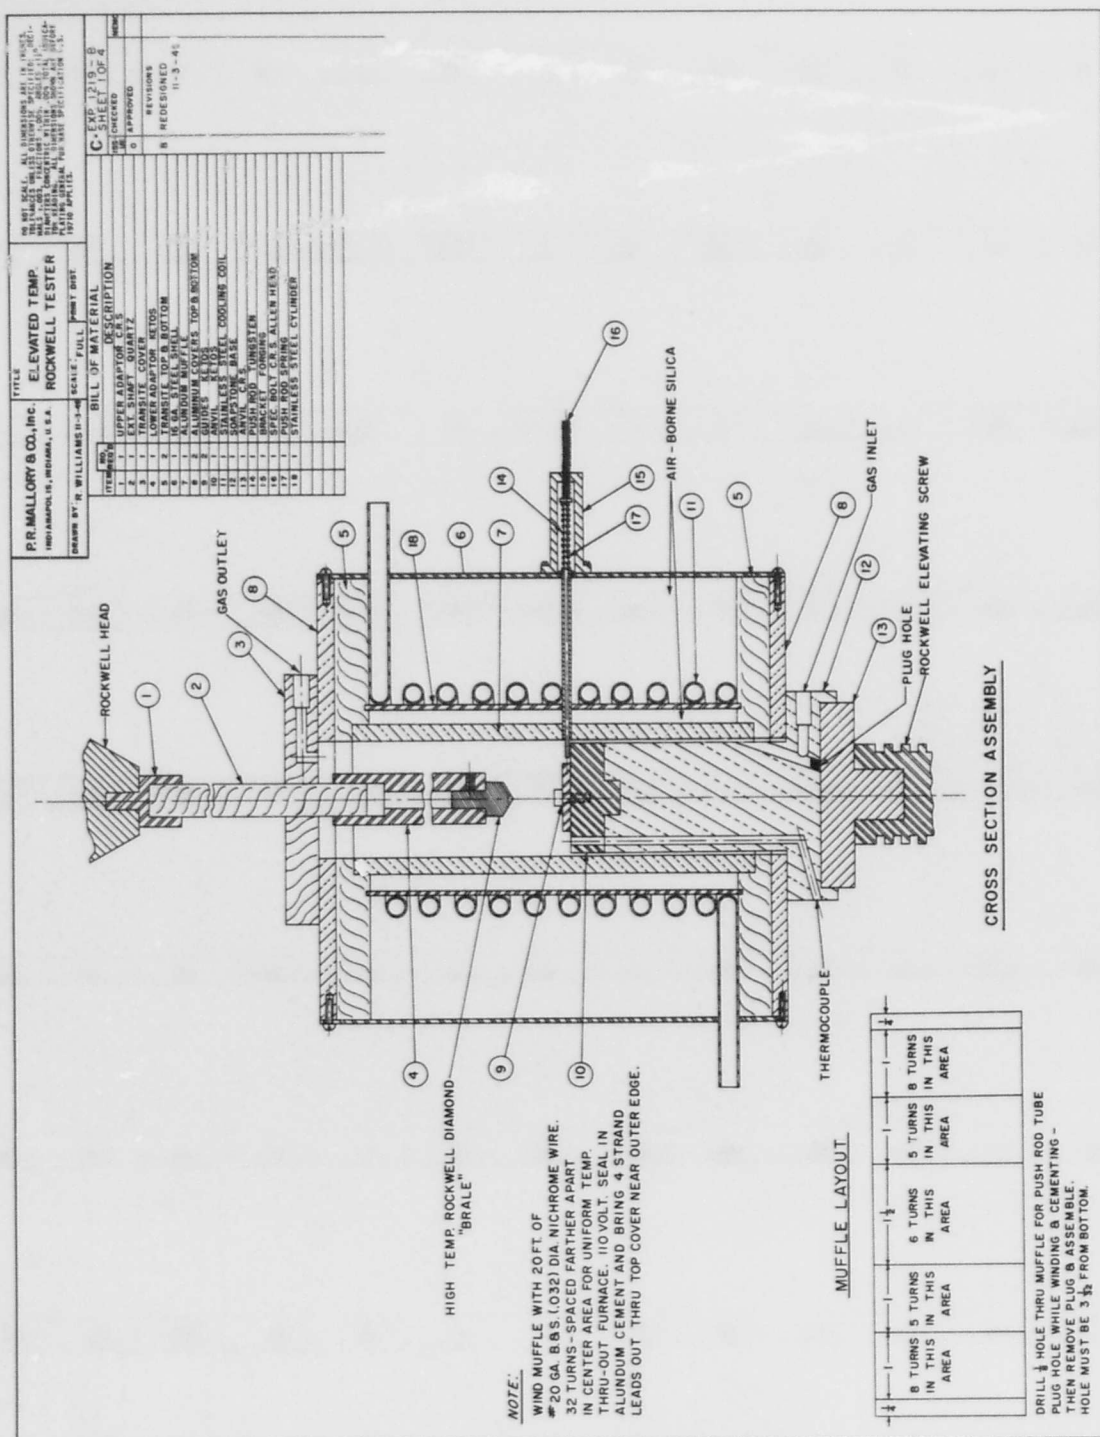

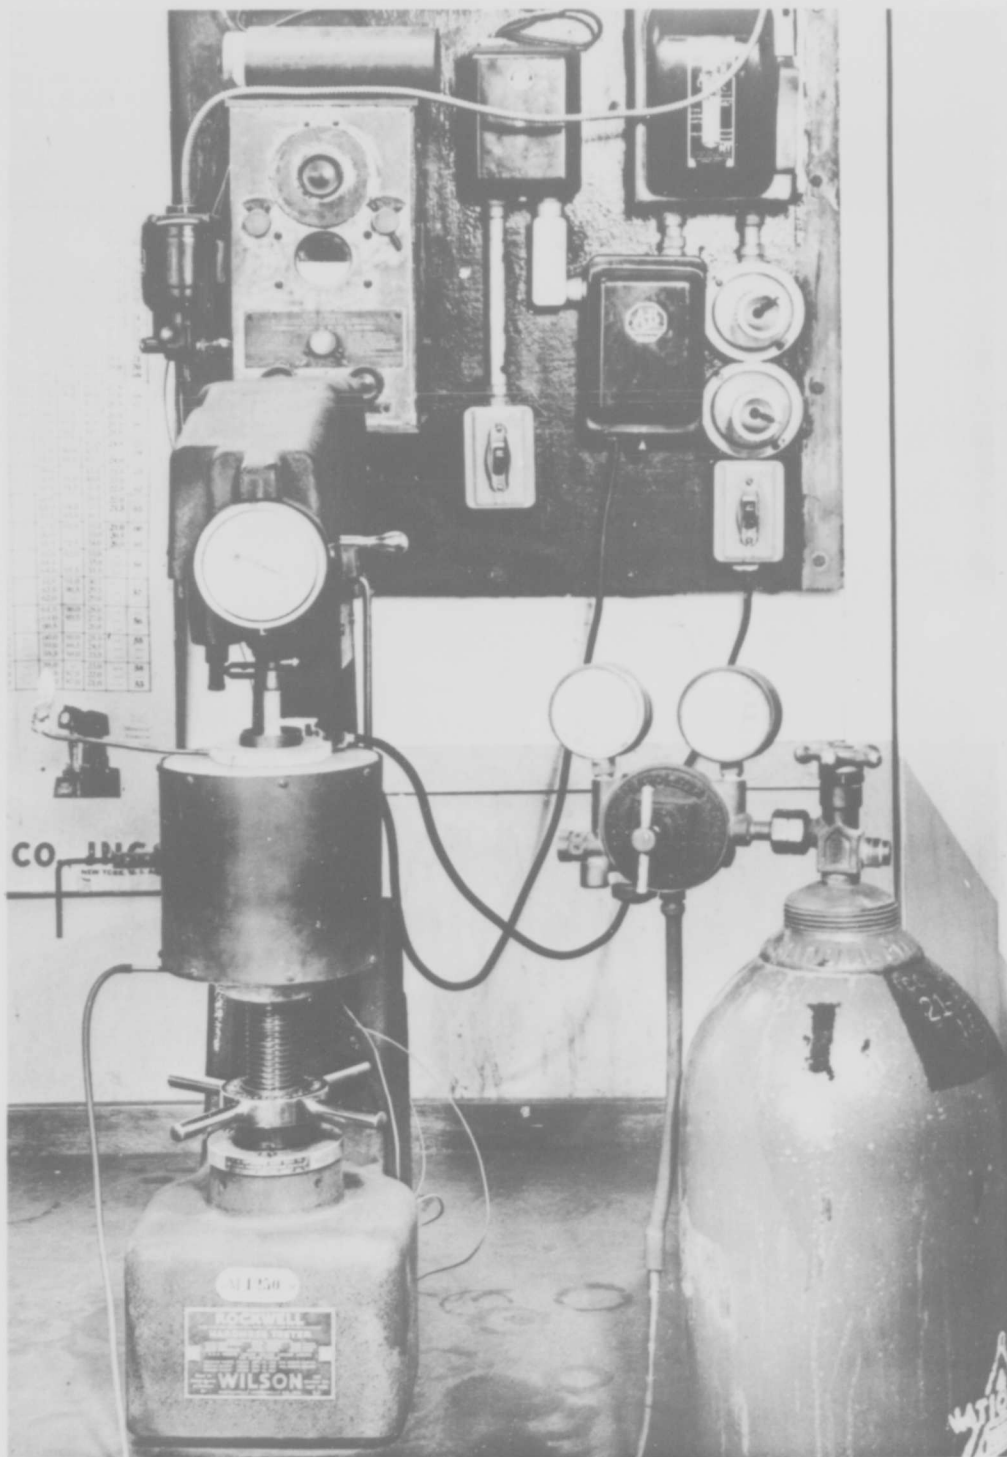


PHOTOGRAPH OF HOT HARDNESS SET-UP

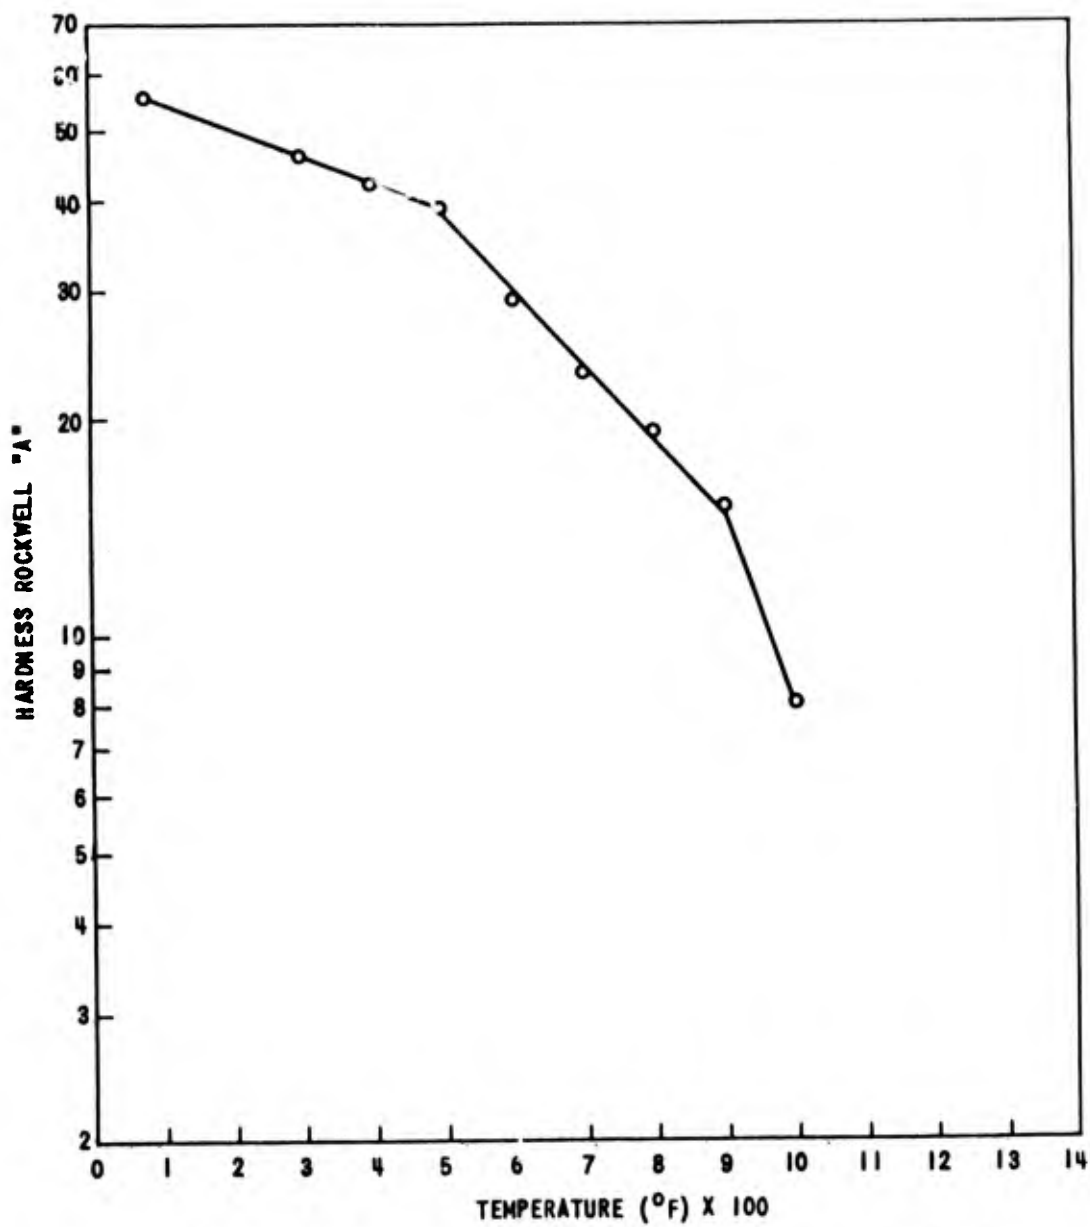


EFFECT OF TEMPERATURE ON THE HARDNESS OF A55 (RHIG4)

FIGURE 3

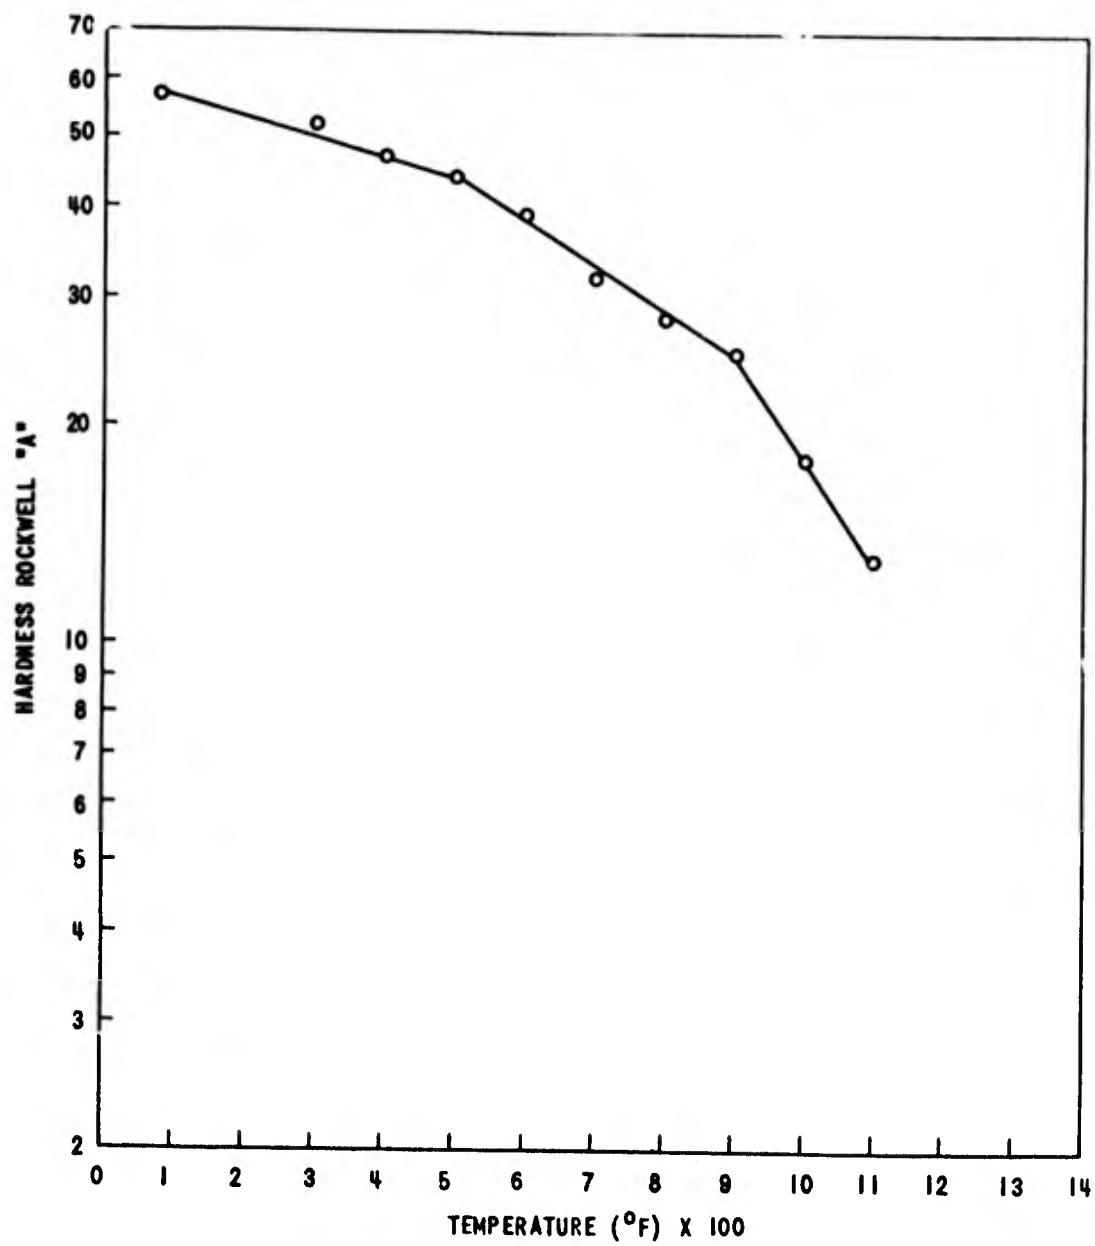


EFFECT OF TEMPERATURE ON THE HARDNESS OF A55 (TH1F2)

FIGURE 4

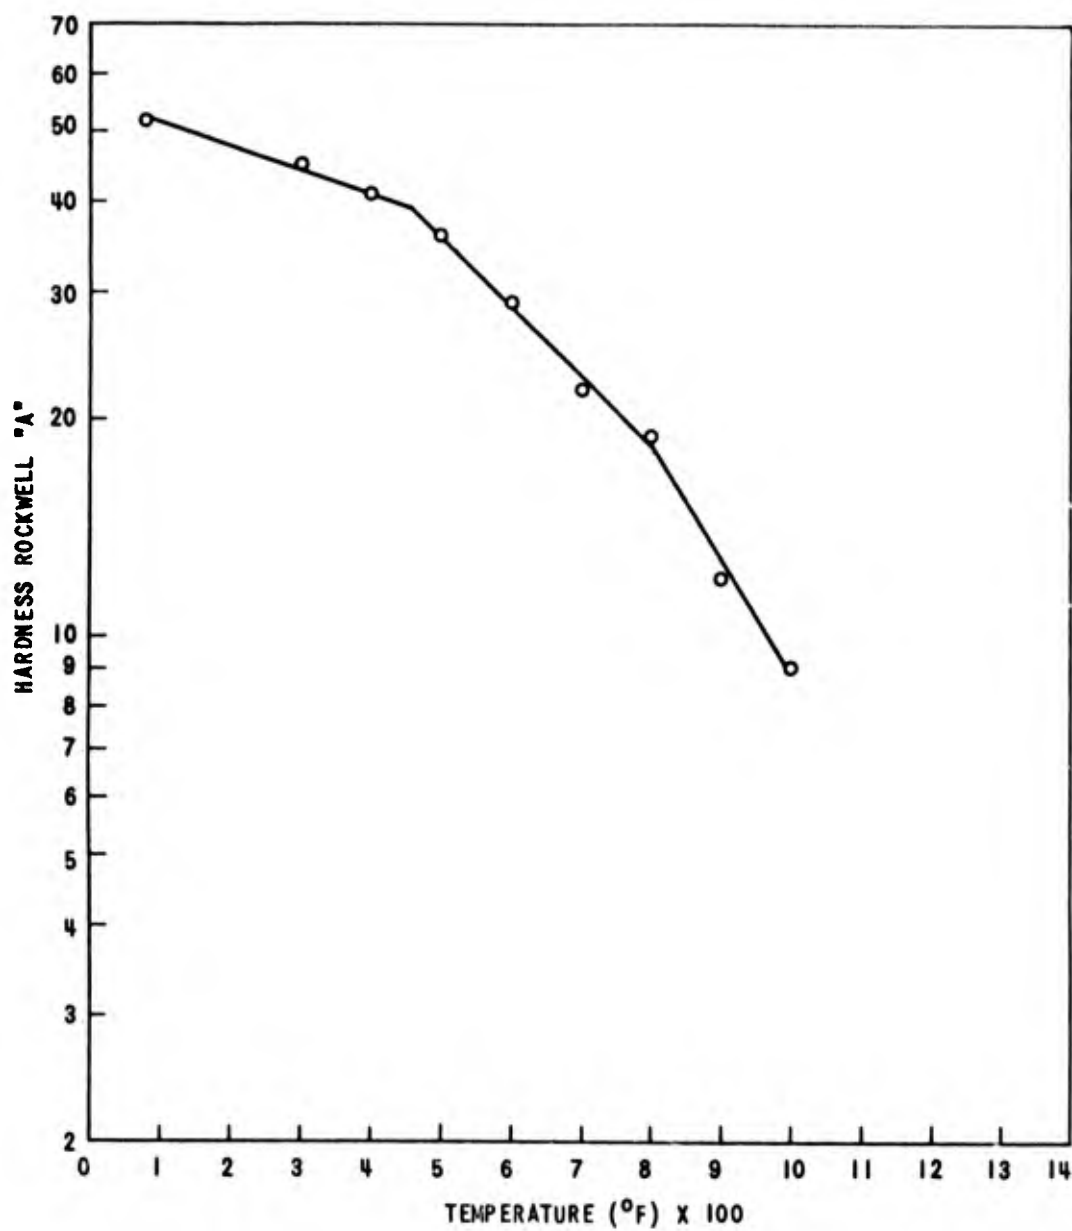


EFFECT OF TEMPERATURE ON THE HARDNESS OF RS55(SXA7)

FIGURE 5

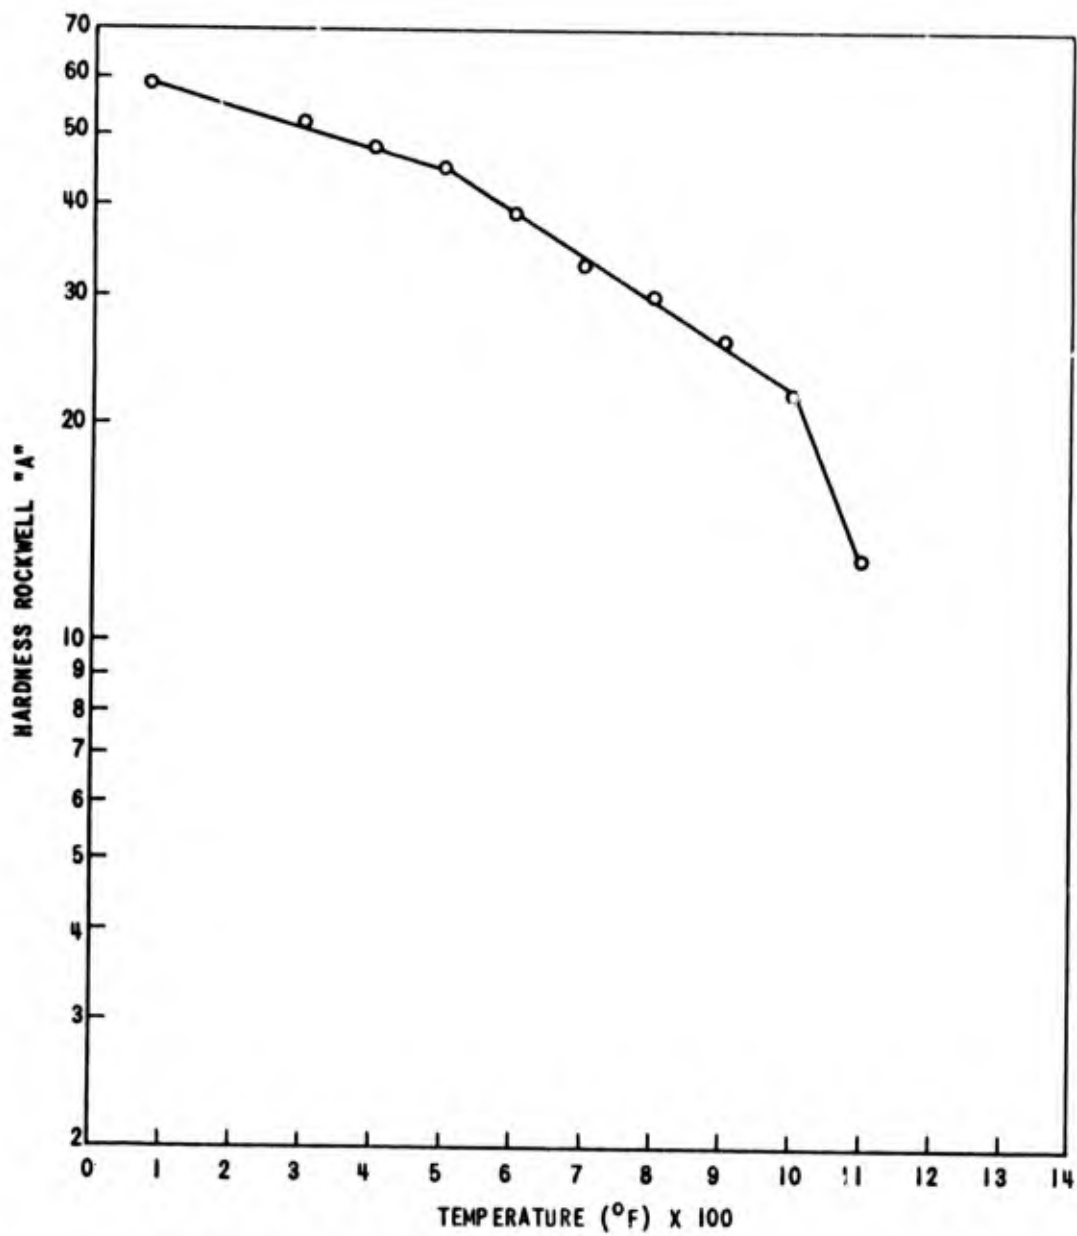


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti100A (THIG2)

FIGURE 6

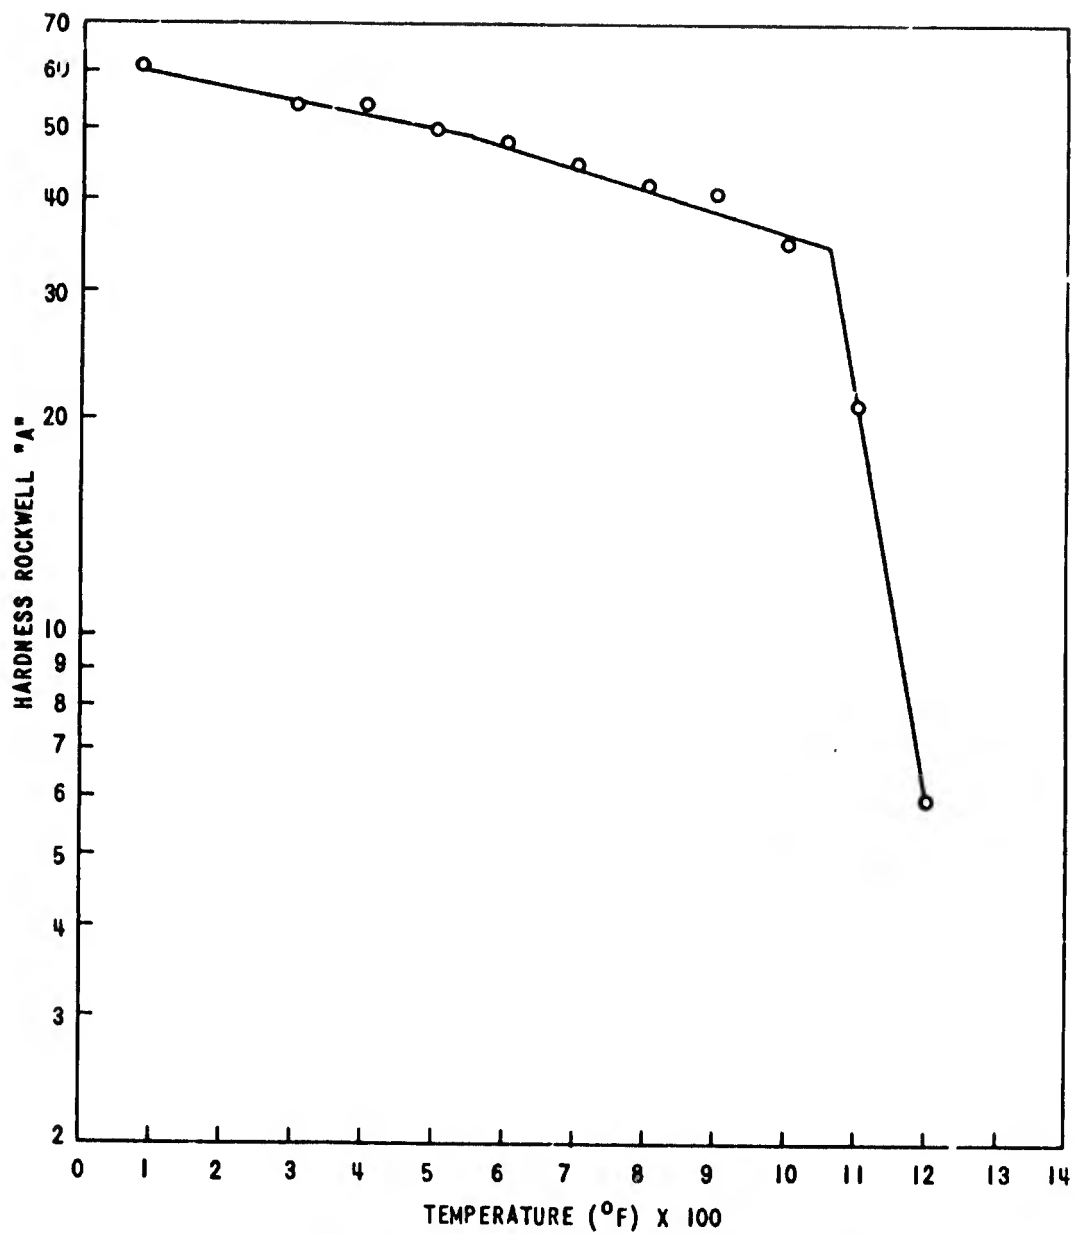


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-4Mn (SXE4)

FIGURE 7

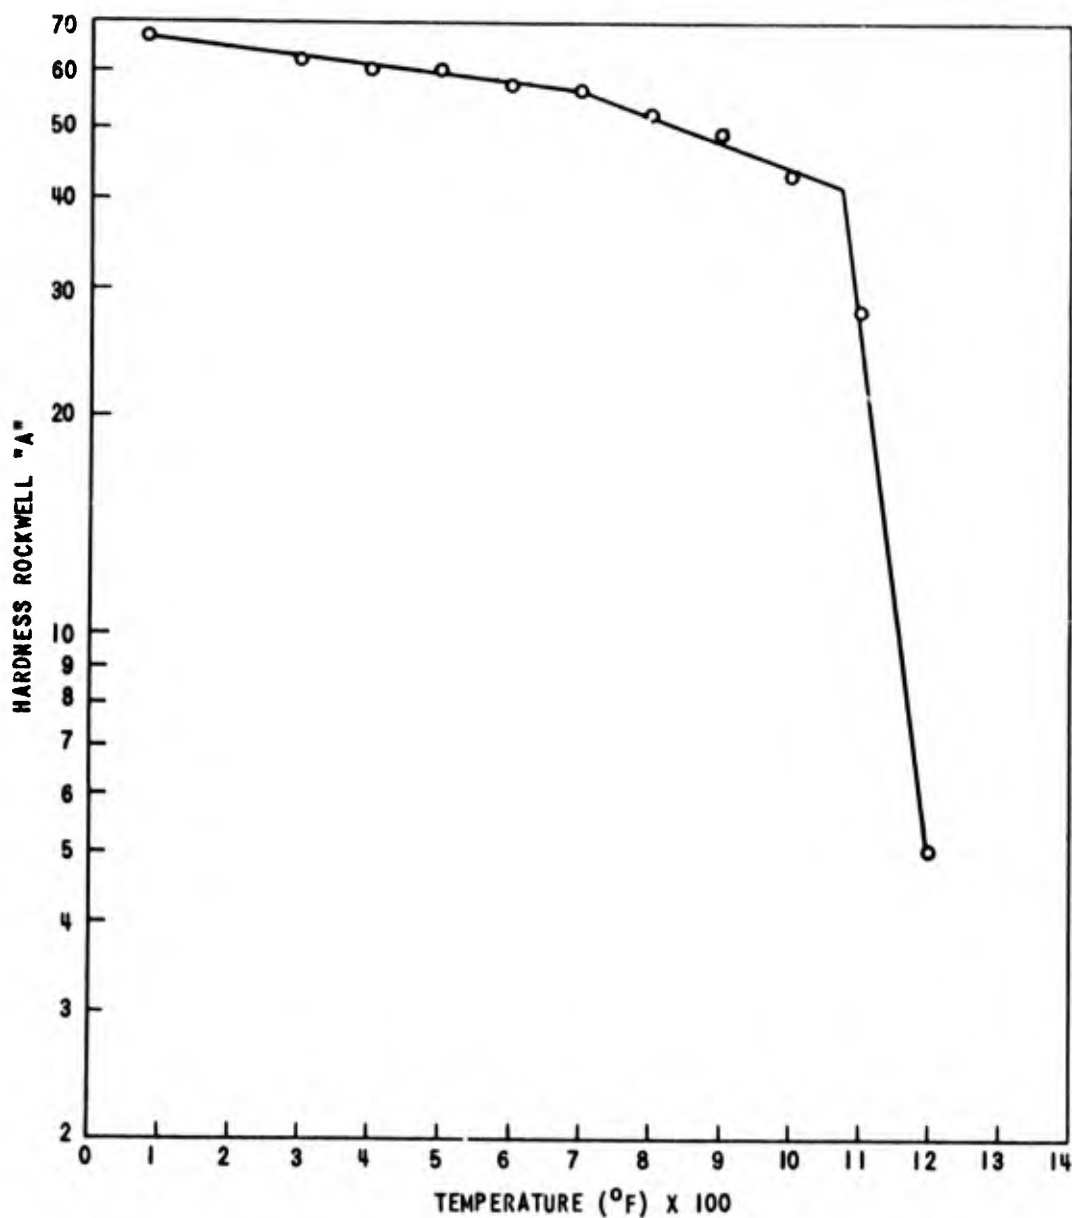


EFFECT OF TEMPERATURE ON THE HARDNESS OF C110M (RHIG5)

FIGURE 8

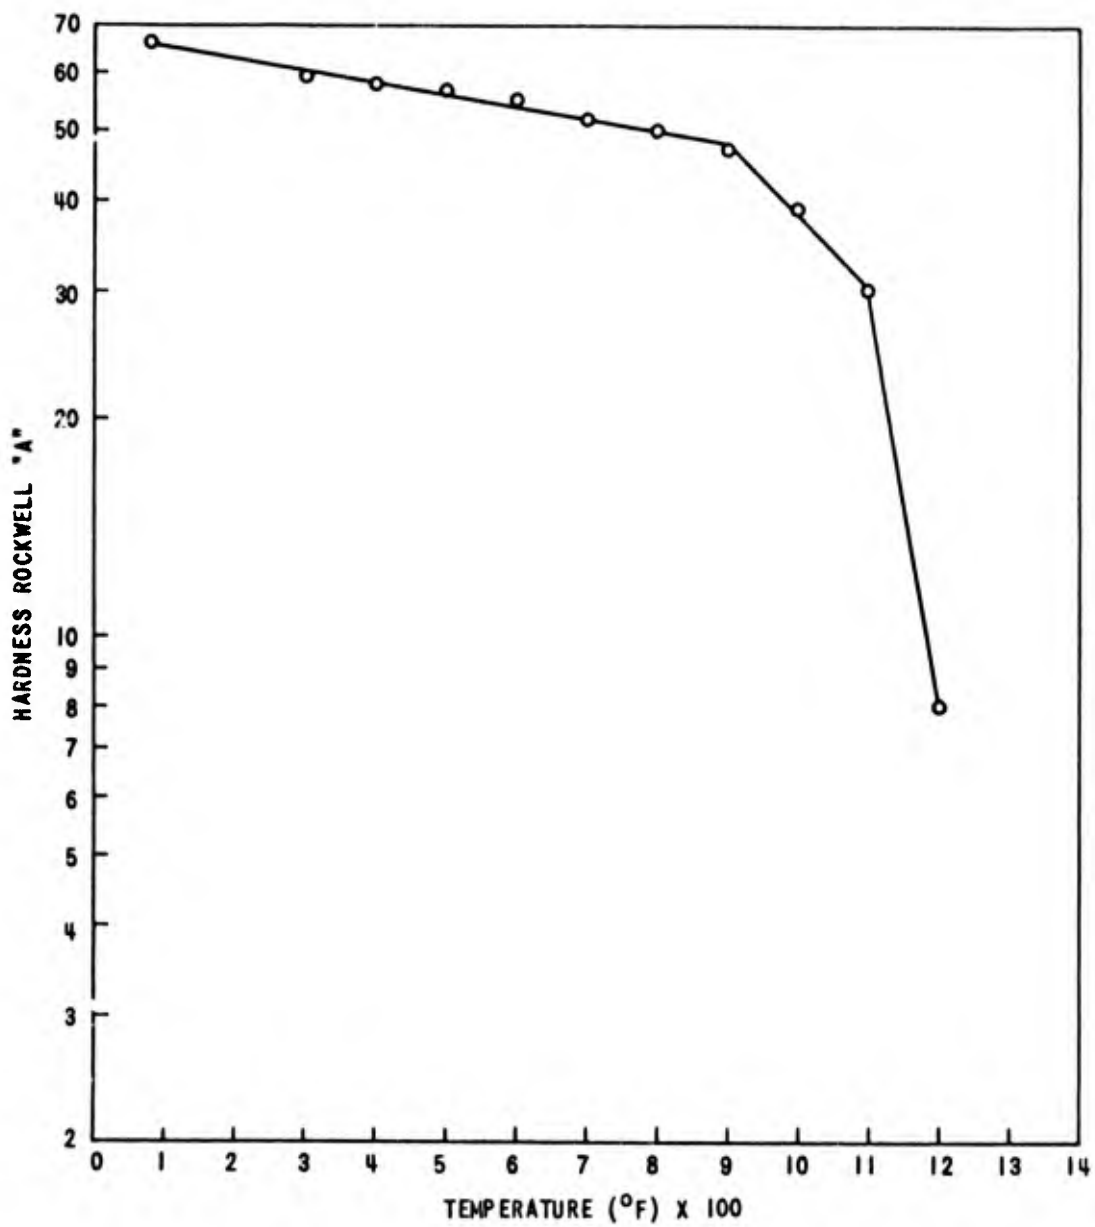


EFFECT OF TEMPERATURE ON THE HARDNESS OF C110M (RXG5)

FIGURE 9

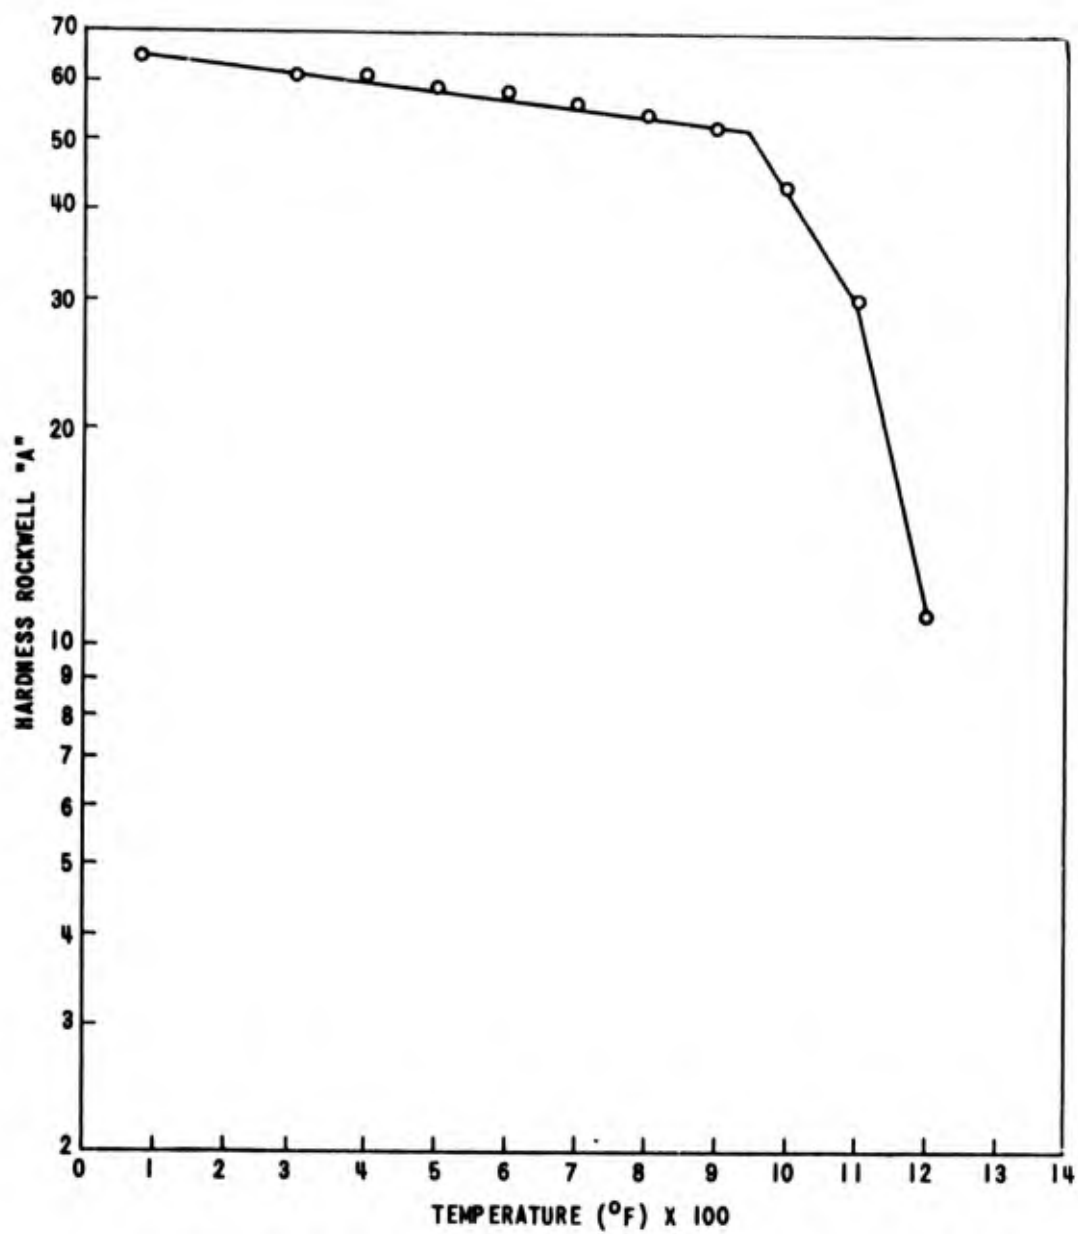


EFFECT OF TEMPERATURE ON THE HARDNESS OF CI10M (RJ1A2)

FIGURE 10

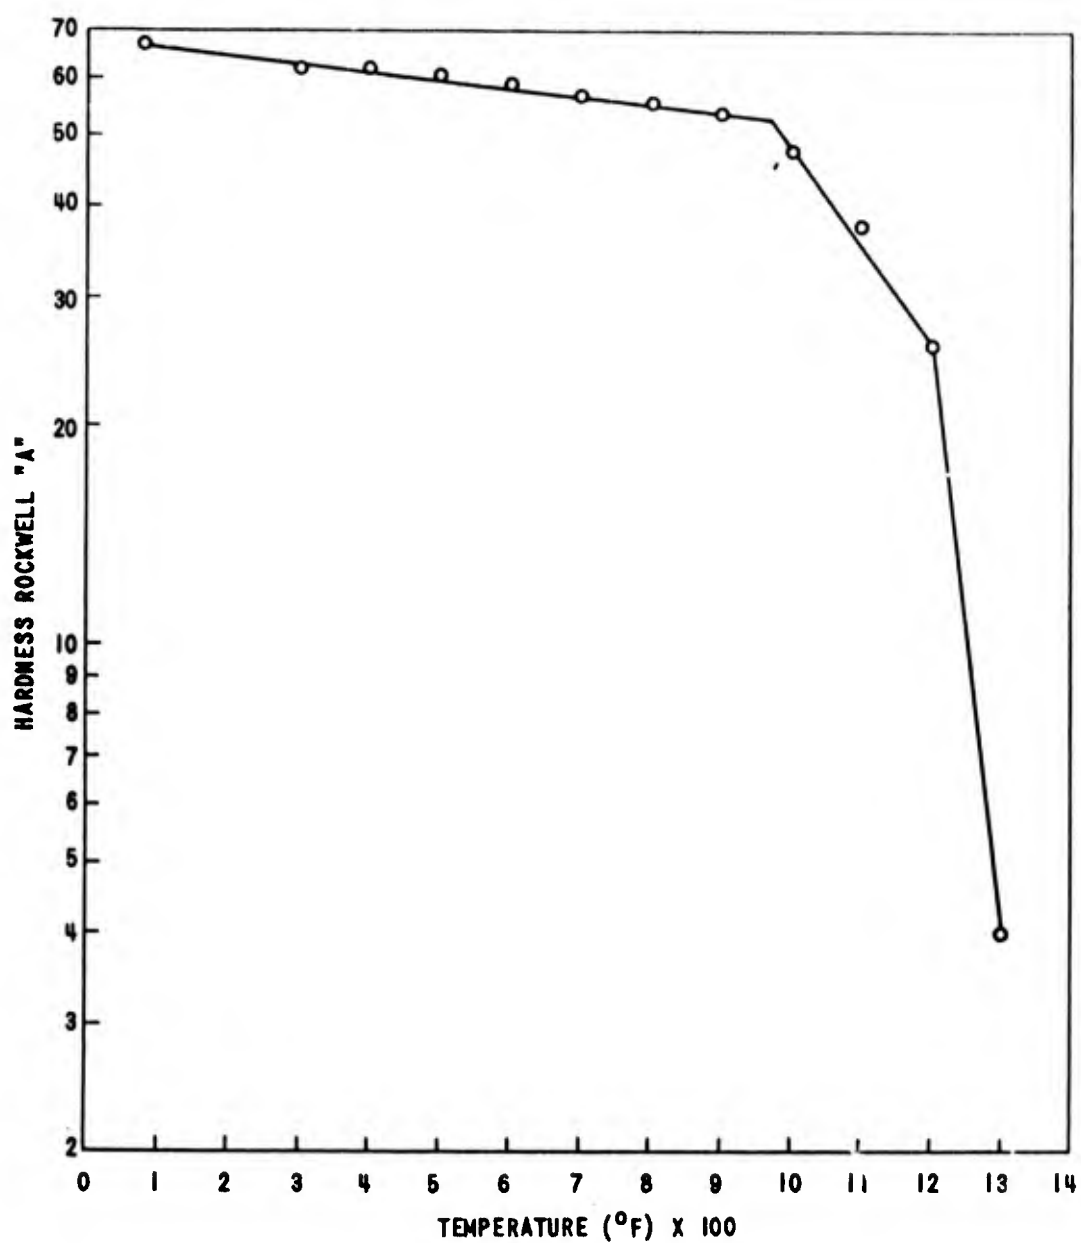


EFFECT OF TEMPERATURE ON THE HARDNESS OF C130AM (RH1B2)

FIGURE 11

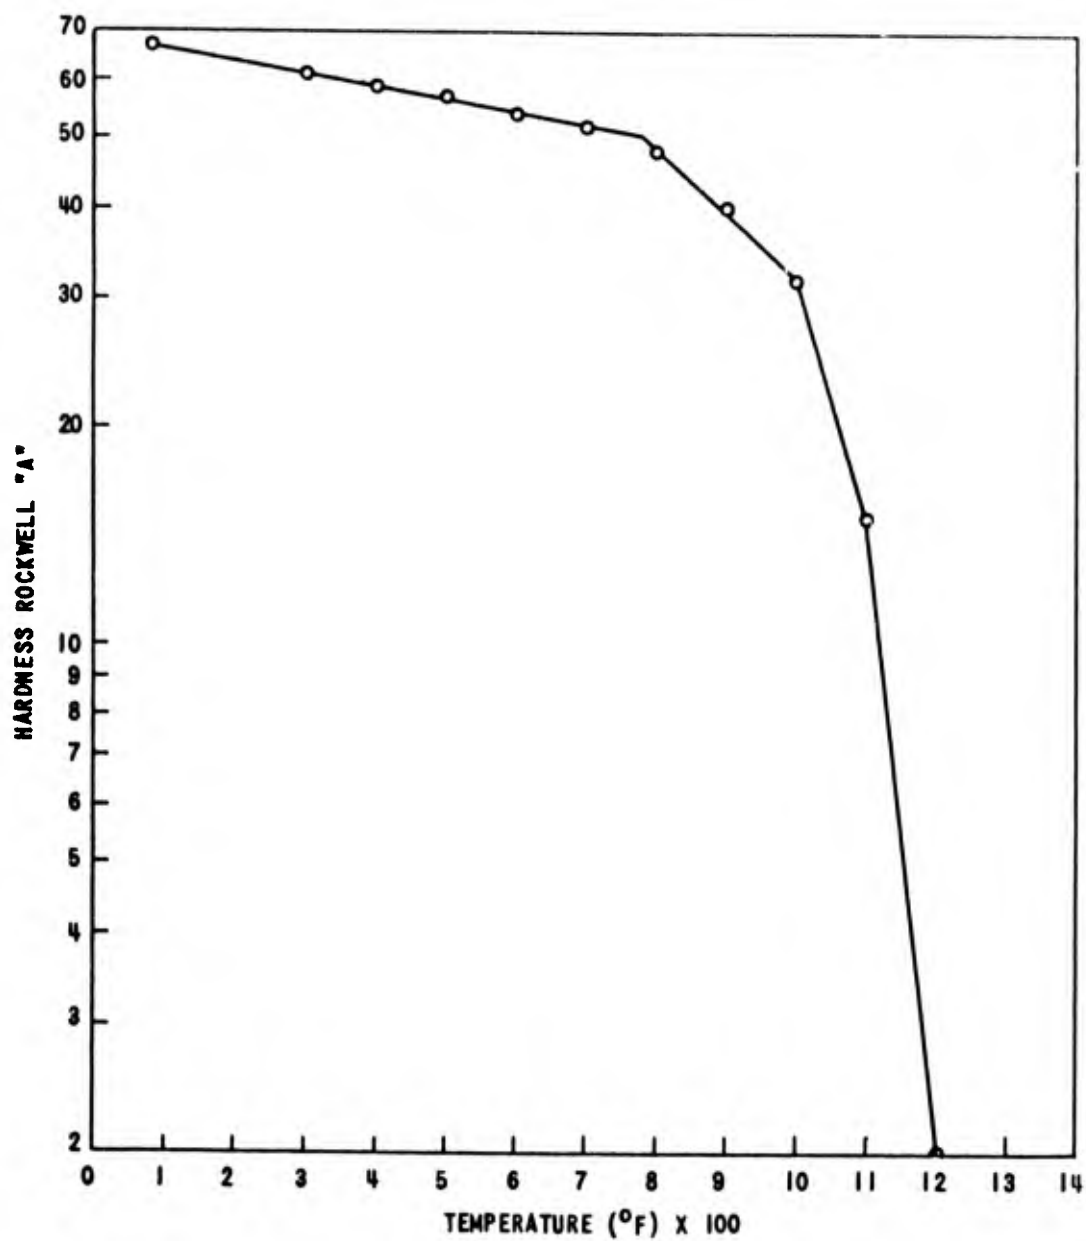


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti150A (TH1J2)

FIGURE 12

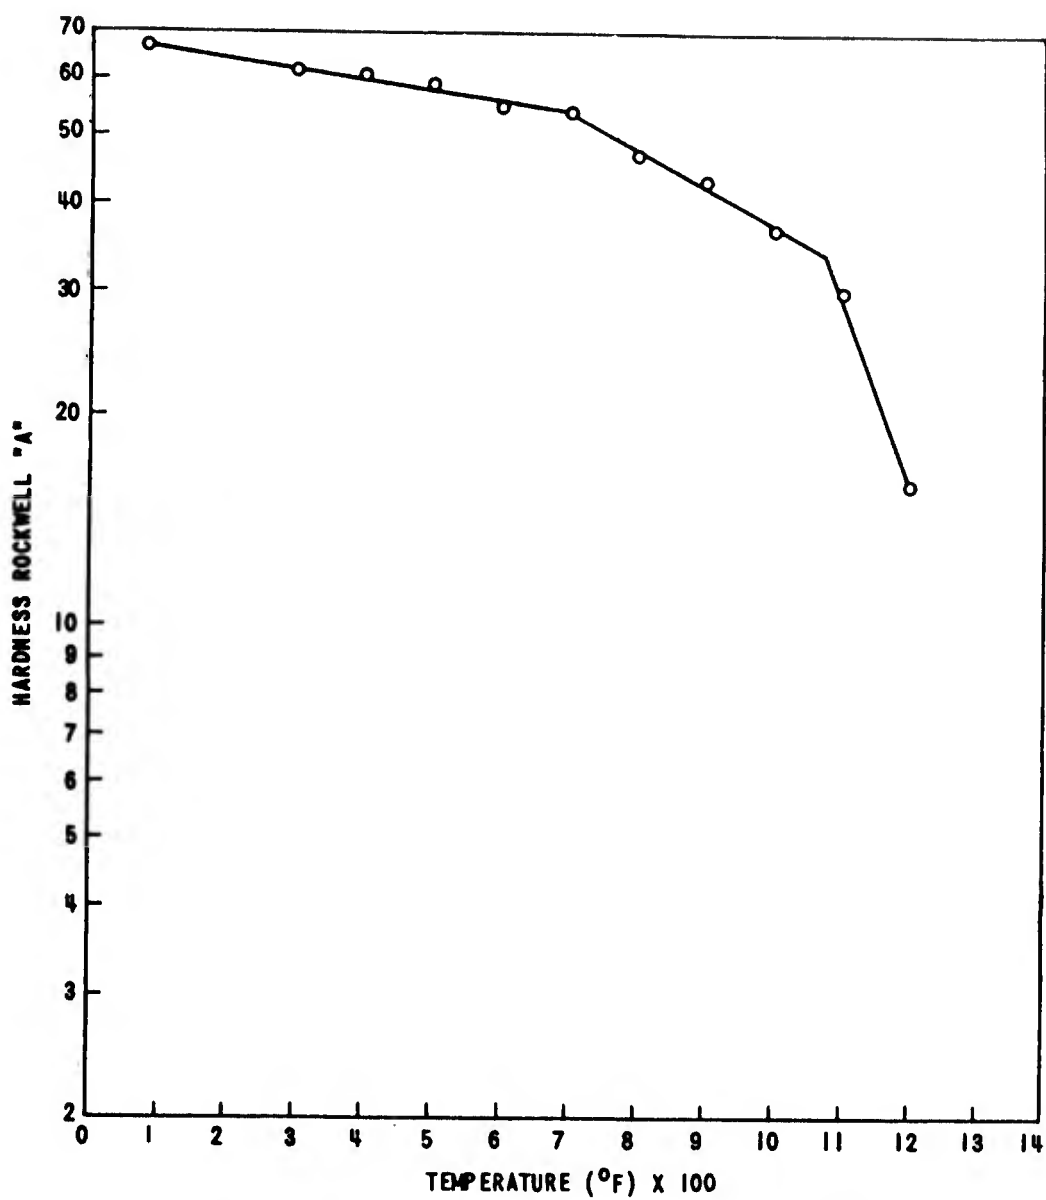


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti150A (TXF2)

FIGURE 13

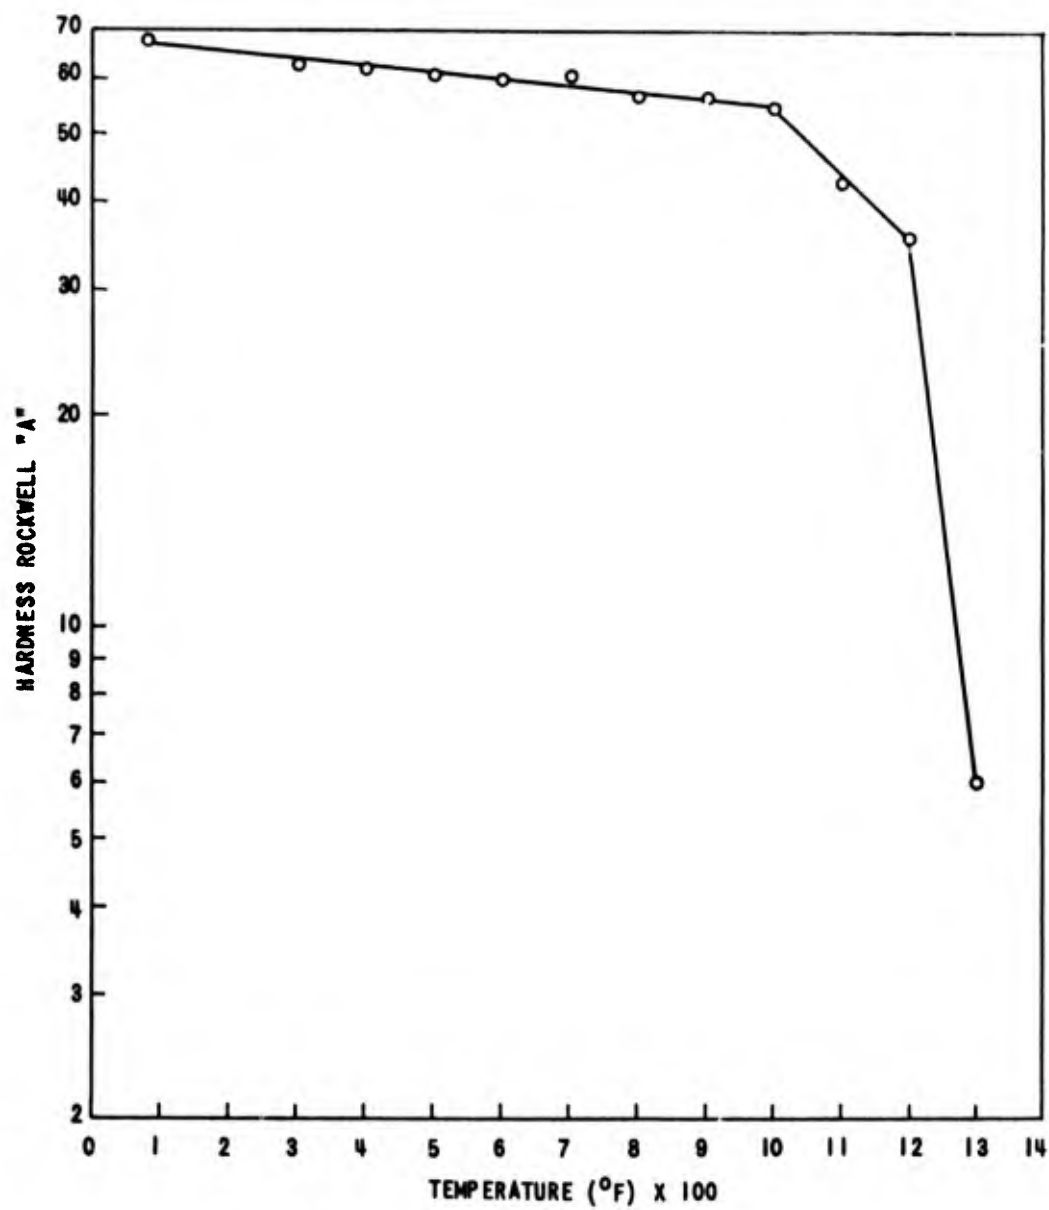


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti150B (TH15)

FIGURE 14

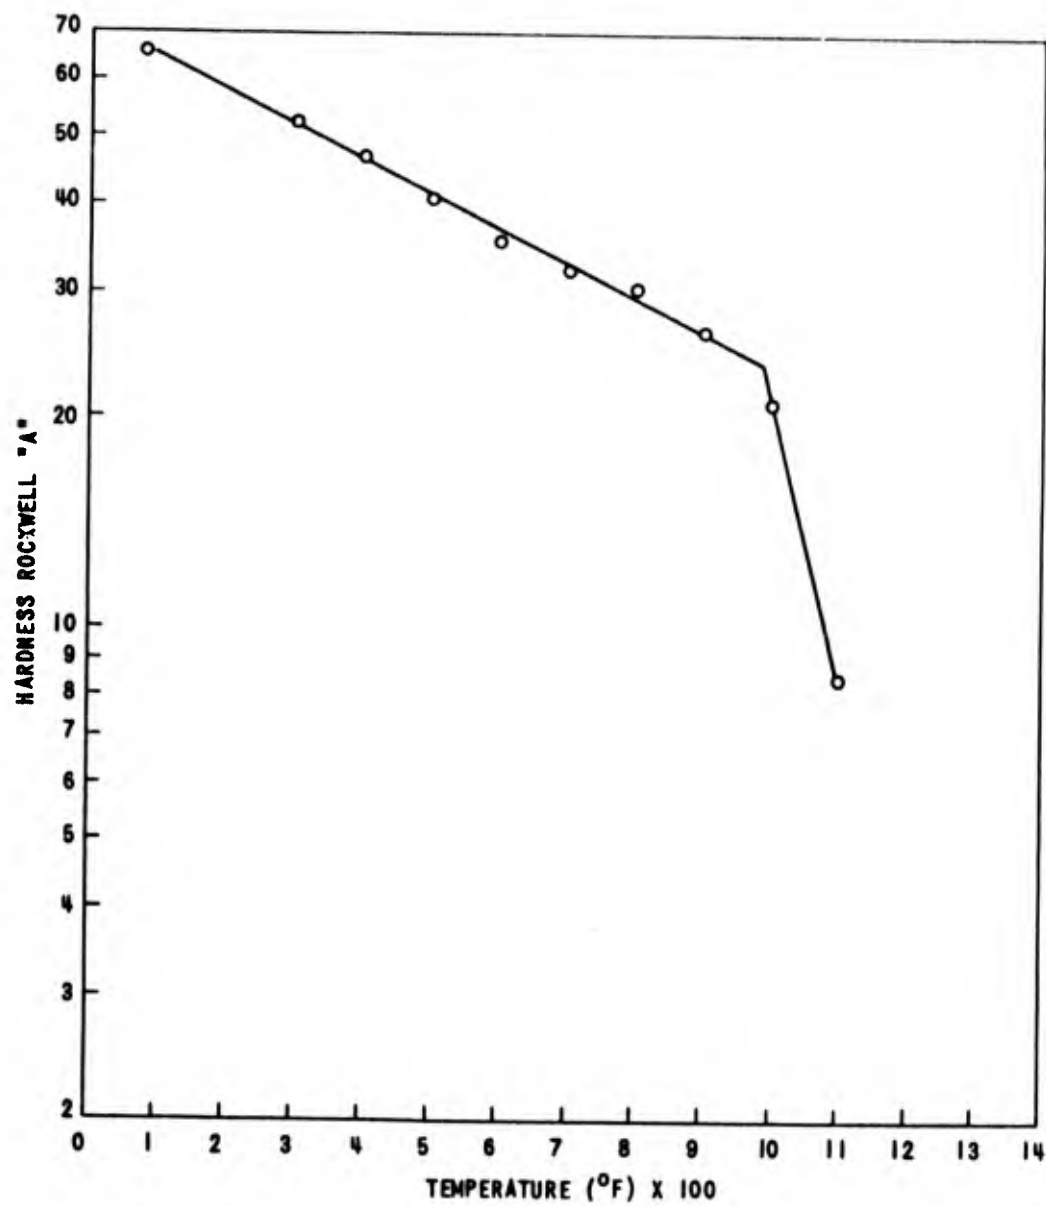


EFFECT OF TEMPERATURE ON THE HARDNESS OF A55 (RH1C1)

FIGURE 15

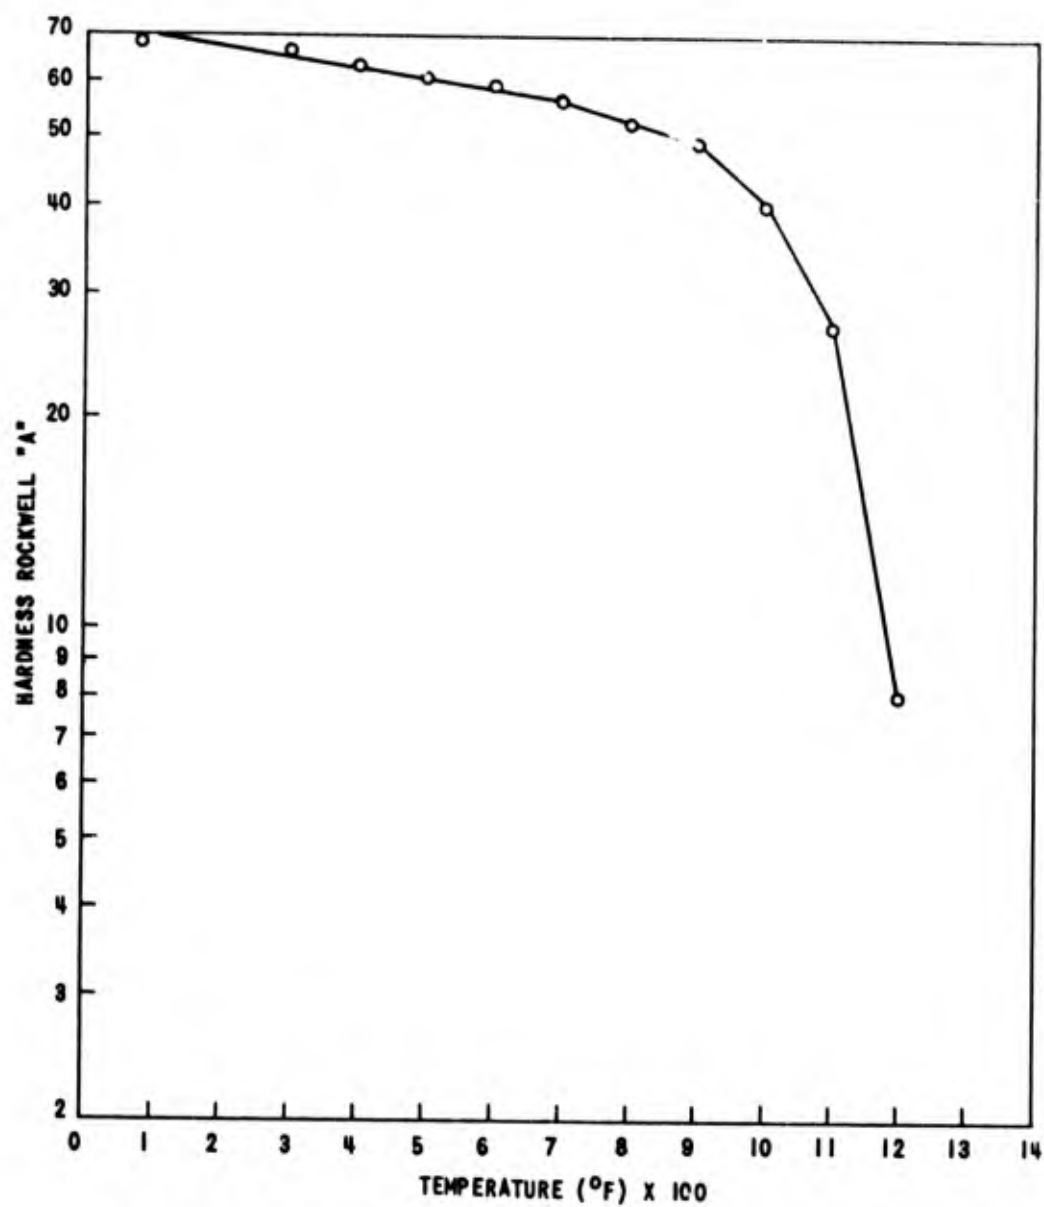


EFFECT OF TEMPERATURE ON THE HARDNESS OF C110M (RH1E2)

FIGURE 16

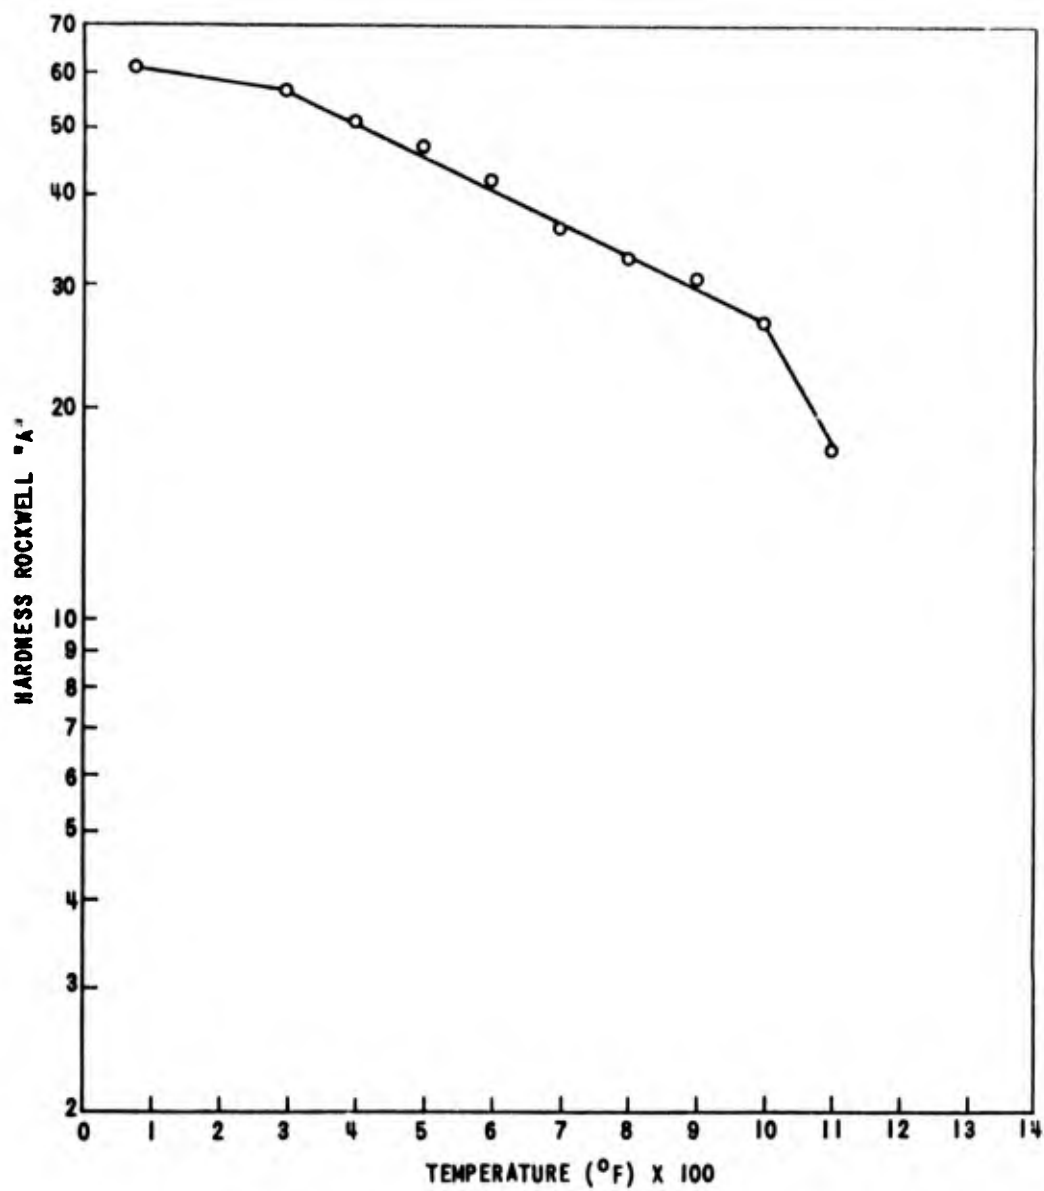


EFFECT OF TEMPERATURE ON THE HARDNESS OF RC70 (RHIDI)

FIGURE 17

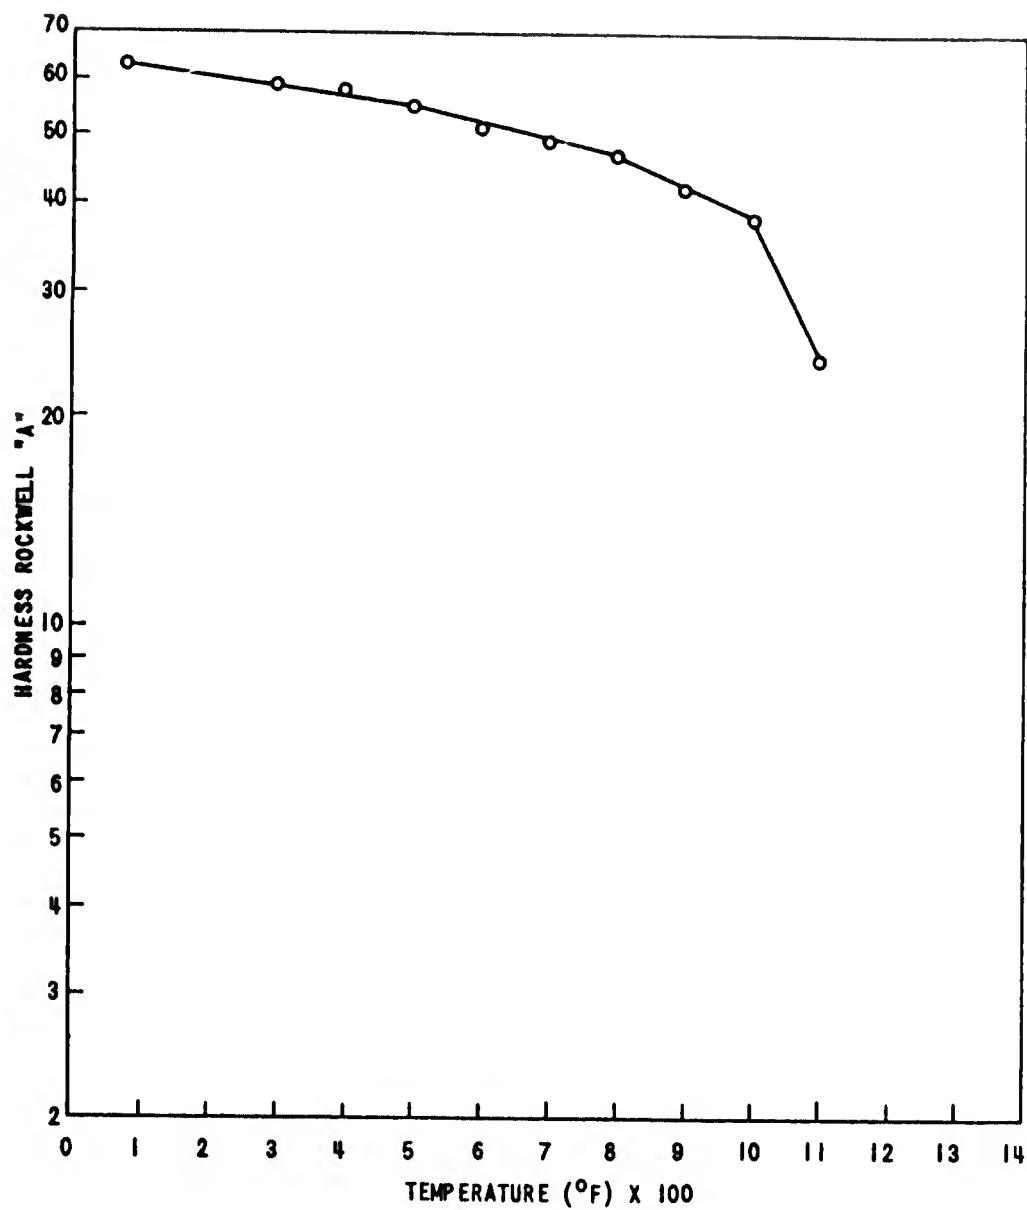


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-3.8Cr-1.5Fe (RS14)

FIGURE 18

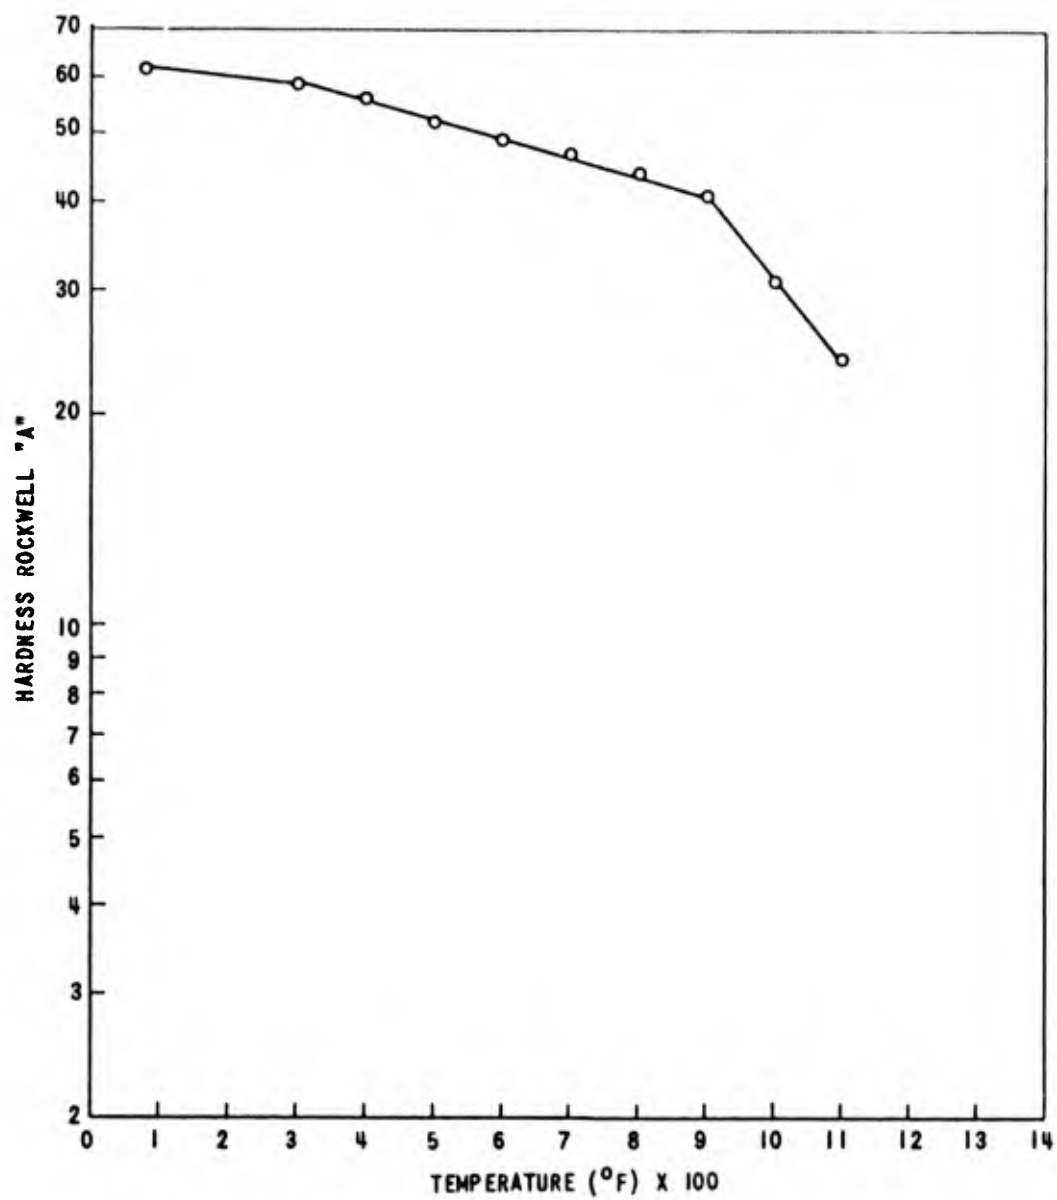


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-3.4Al-1.5Sn (R26)

FIGURE 19

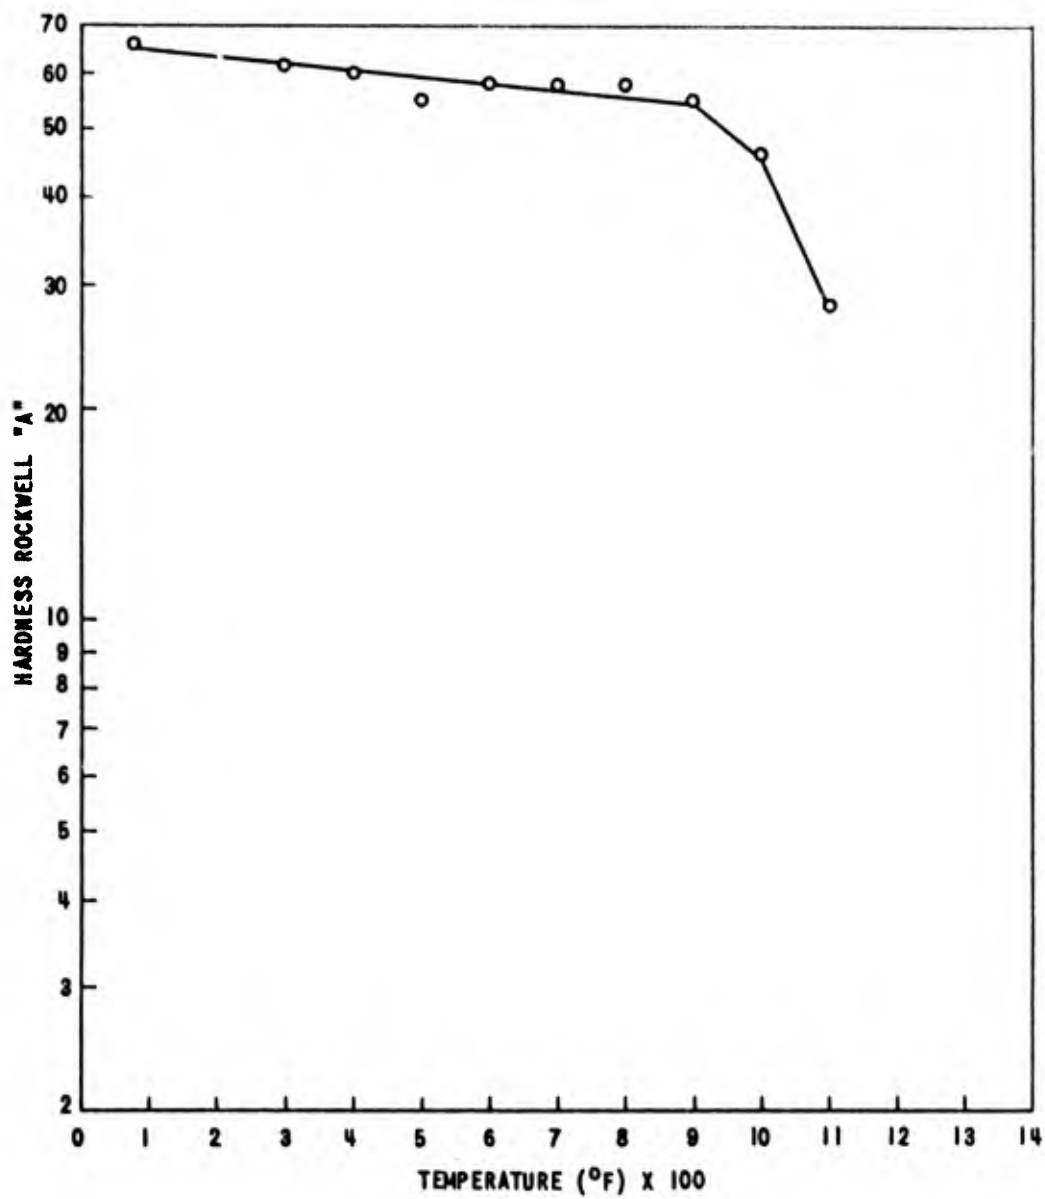


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-6.8Mn-4.3Mo-3.9Cr (R110)

FIGURE 20

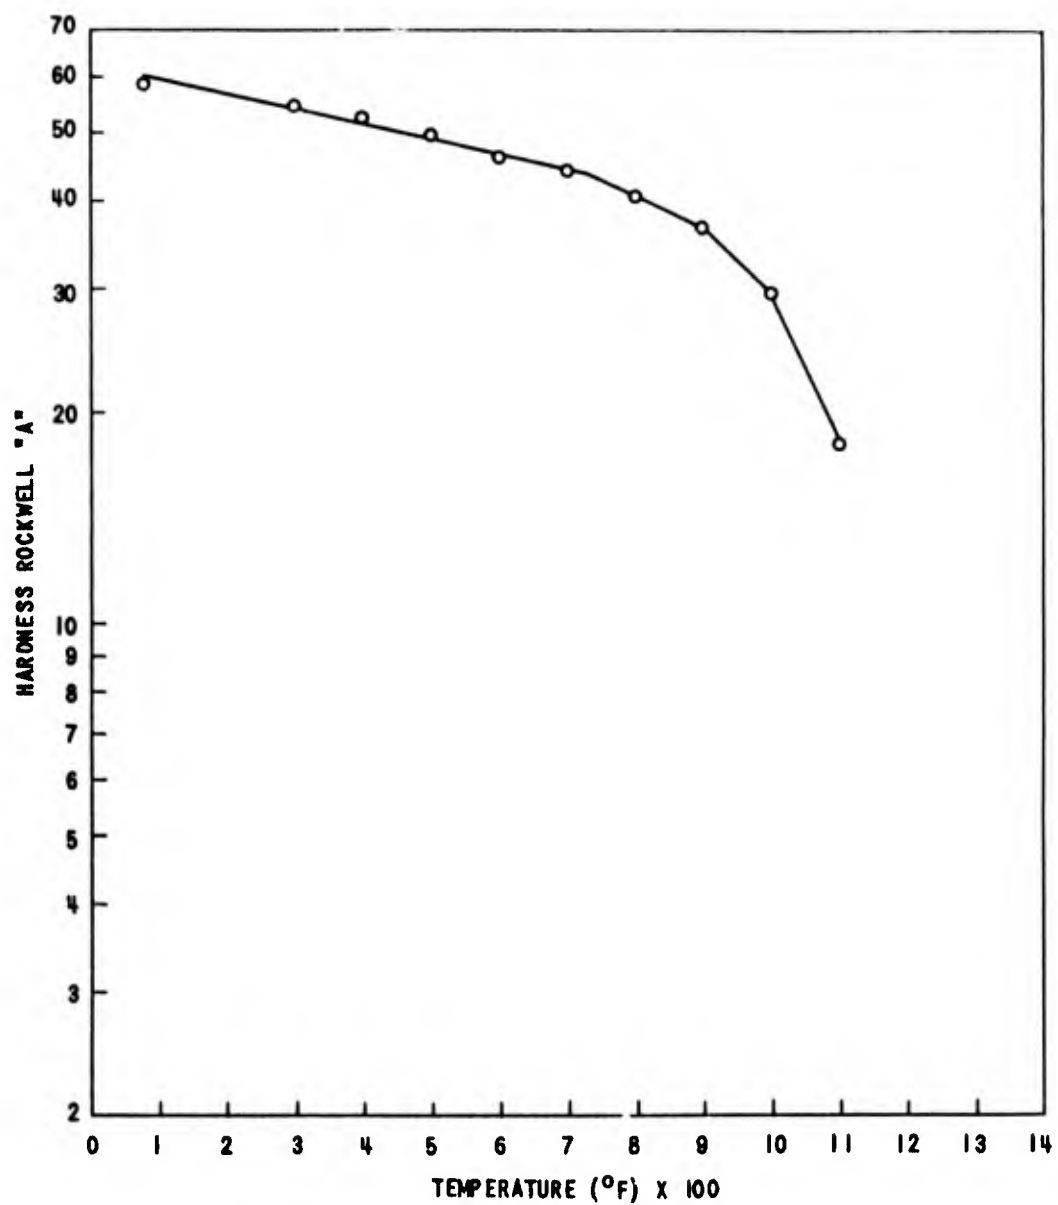


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-3.8Cr-2.5Mo (AZ5)

FIGURE 21

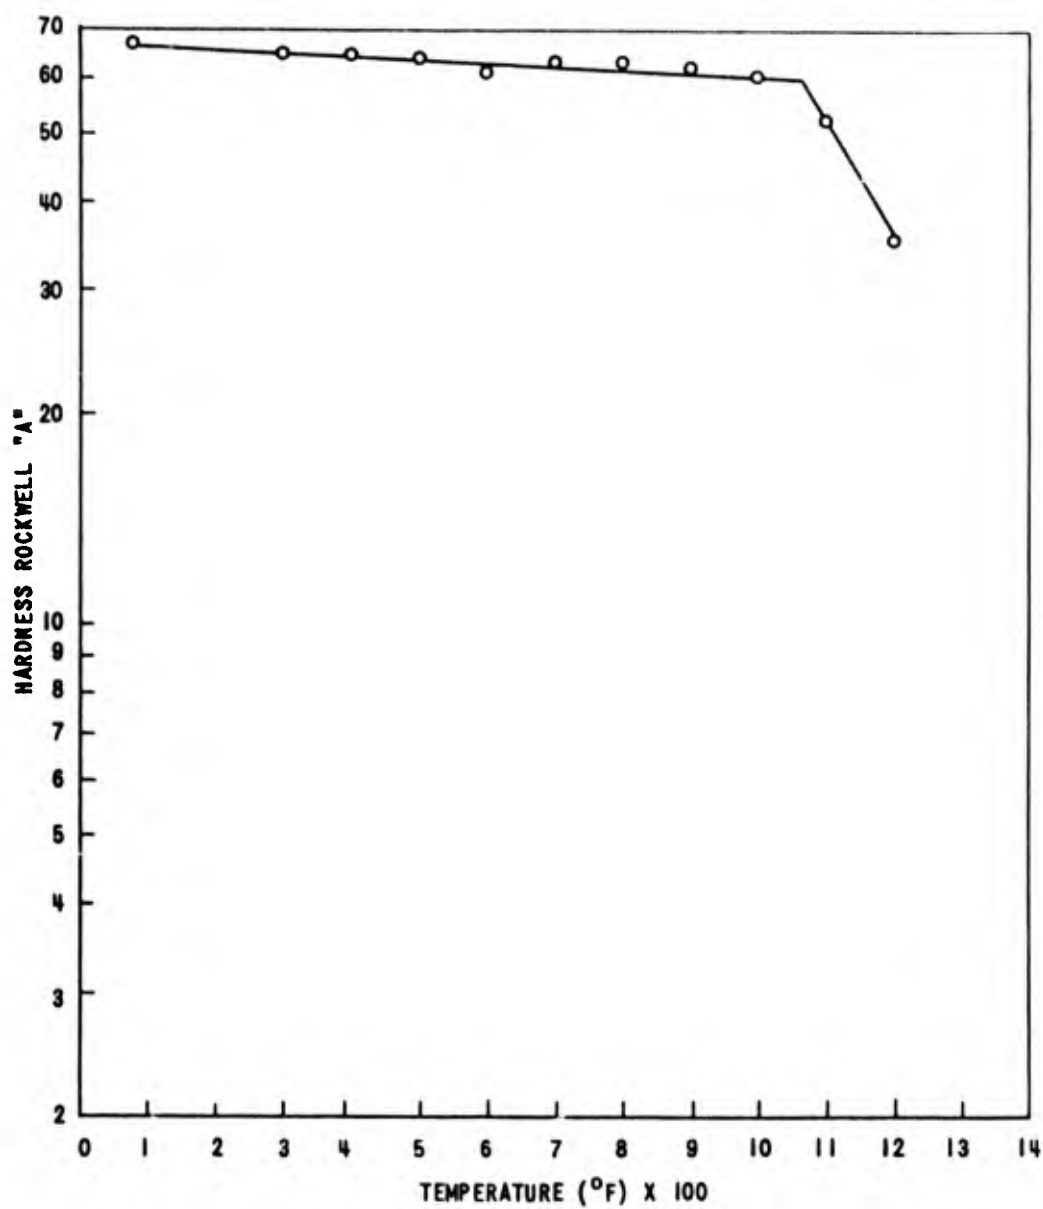


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-5.4Fe-11.8Cr (K100)

FIGURE 22

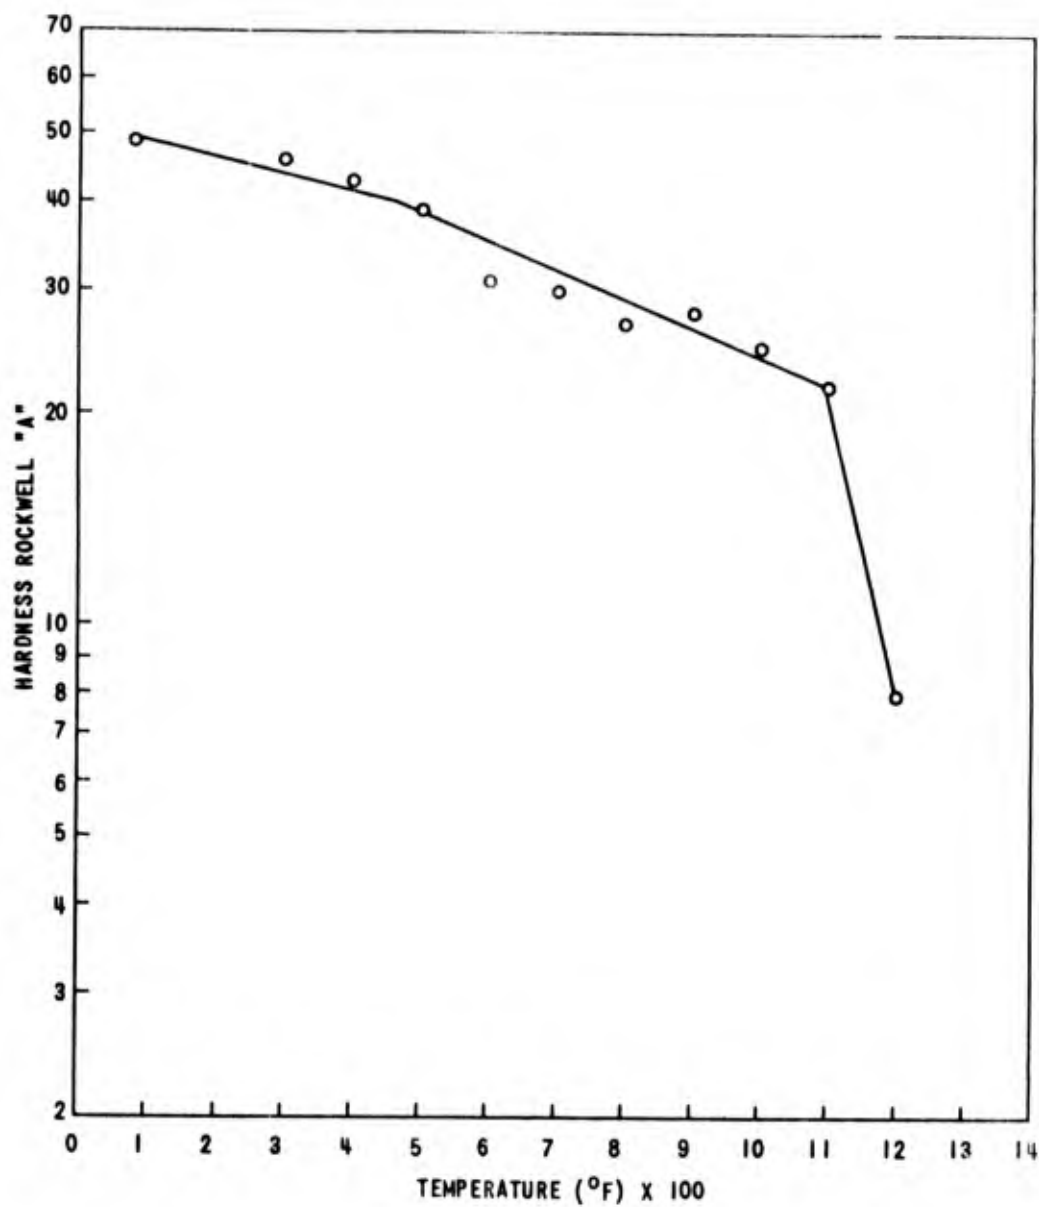


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-0Zr (TZI)

FIGURE 23

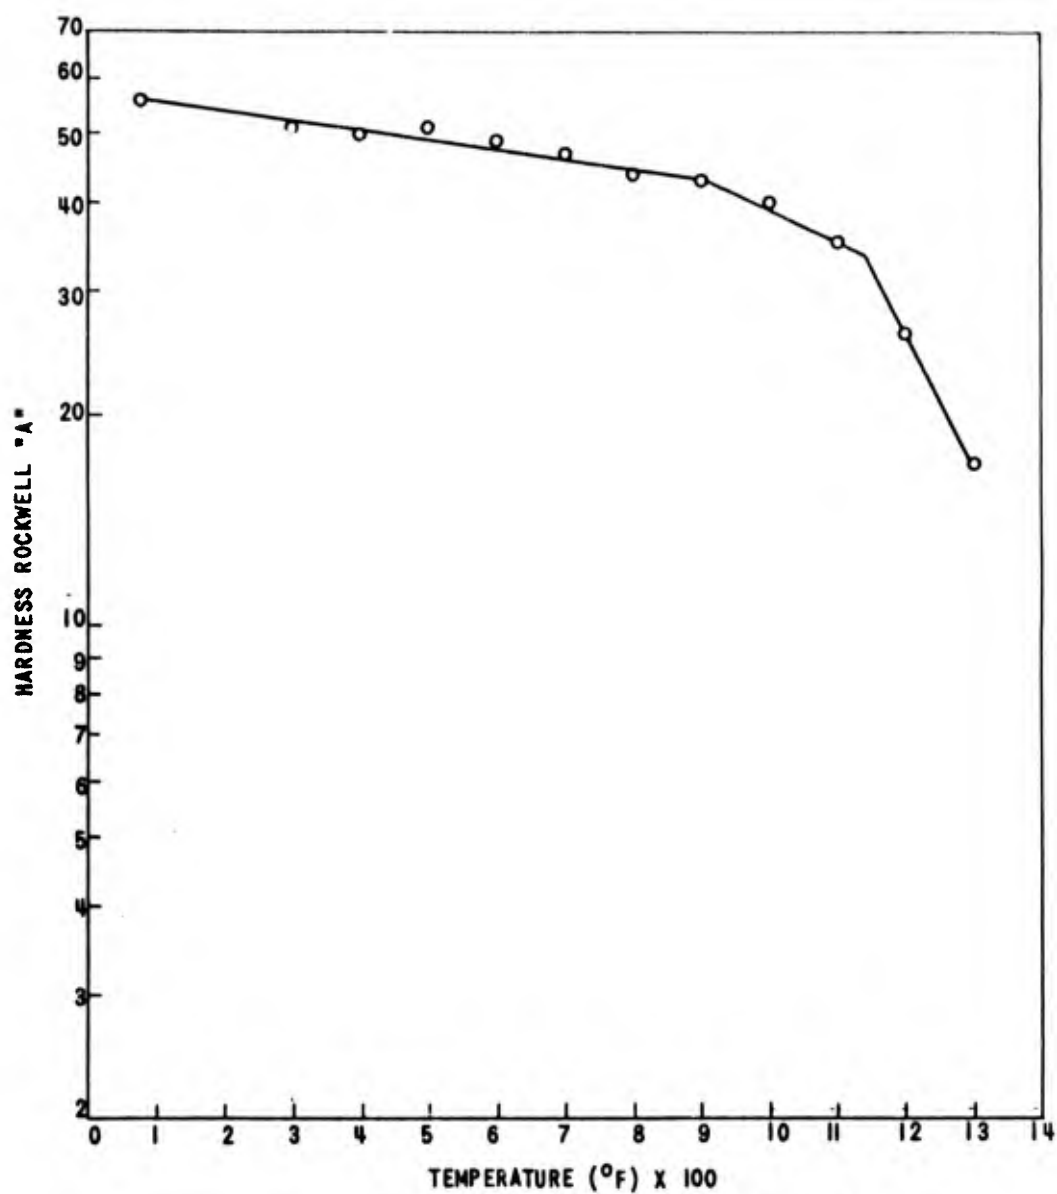


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-5Zr (TZ2)

FIGURE 24

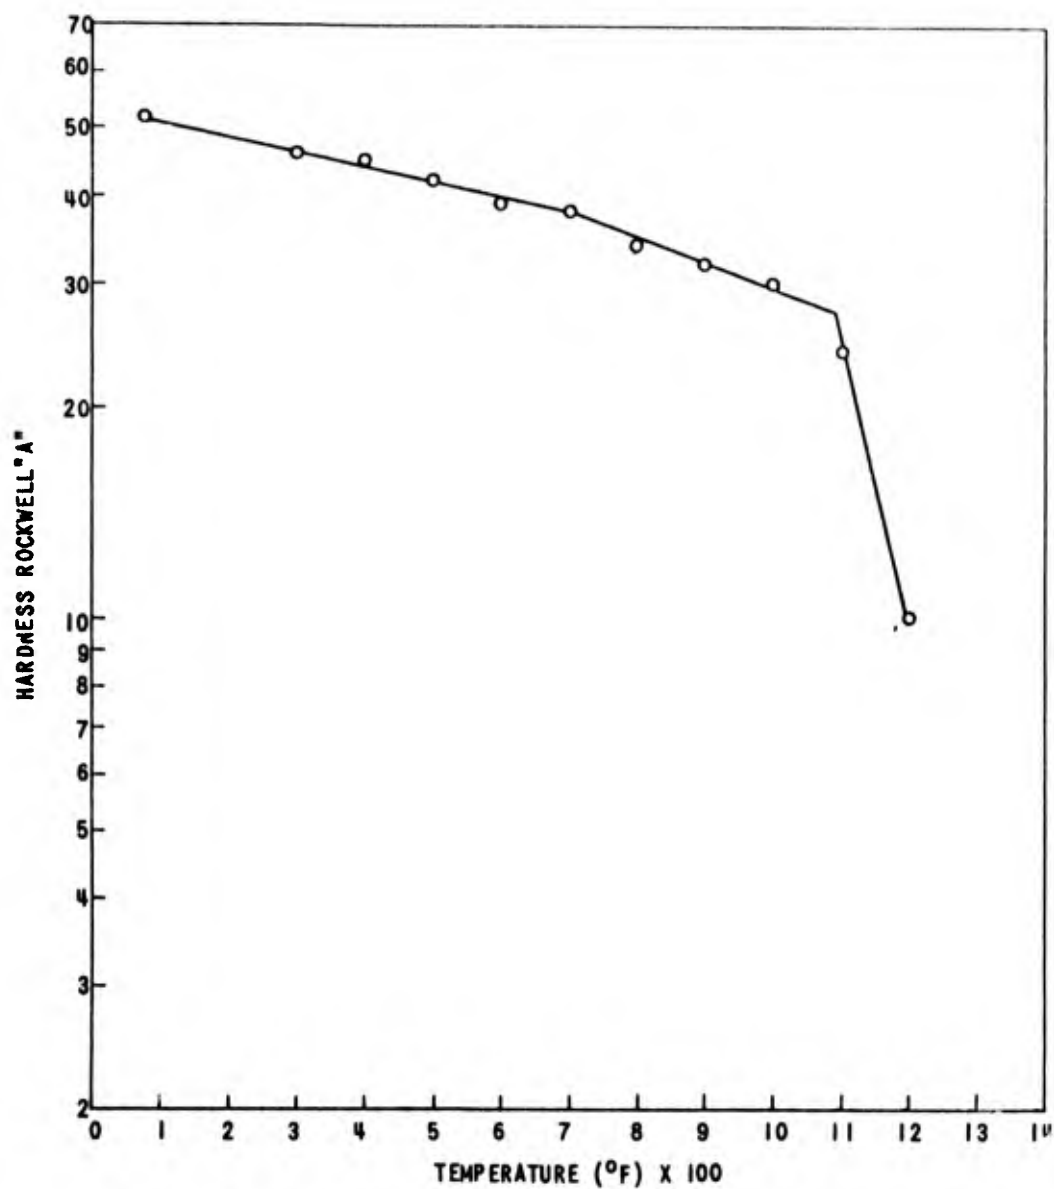


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-9.4Zr (723)

FIGURE 25

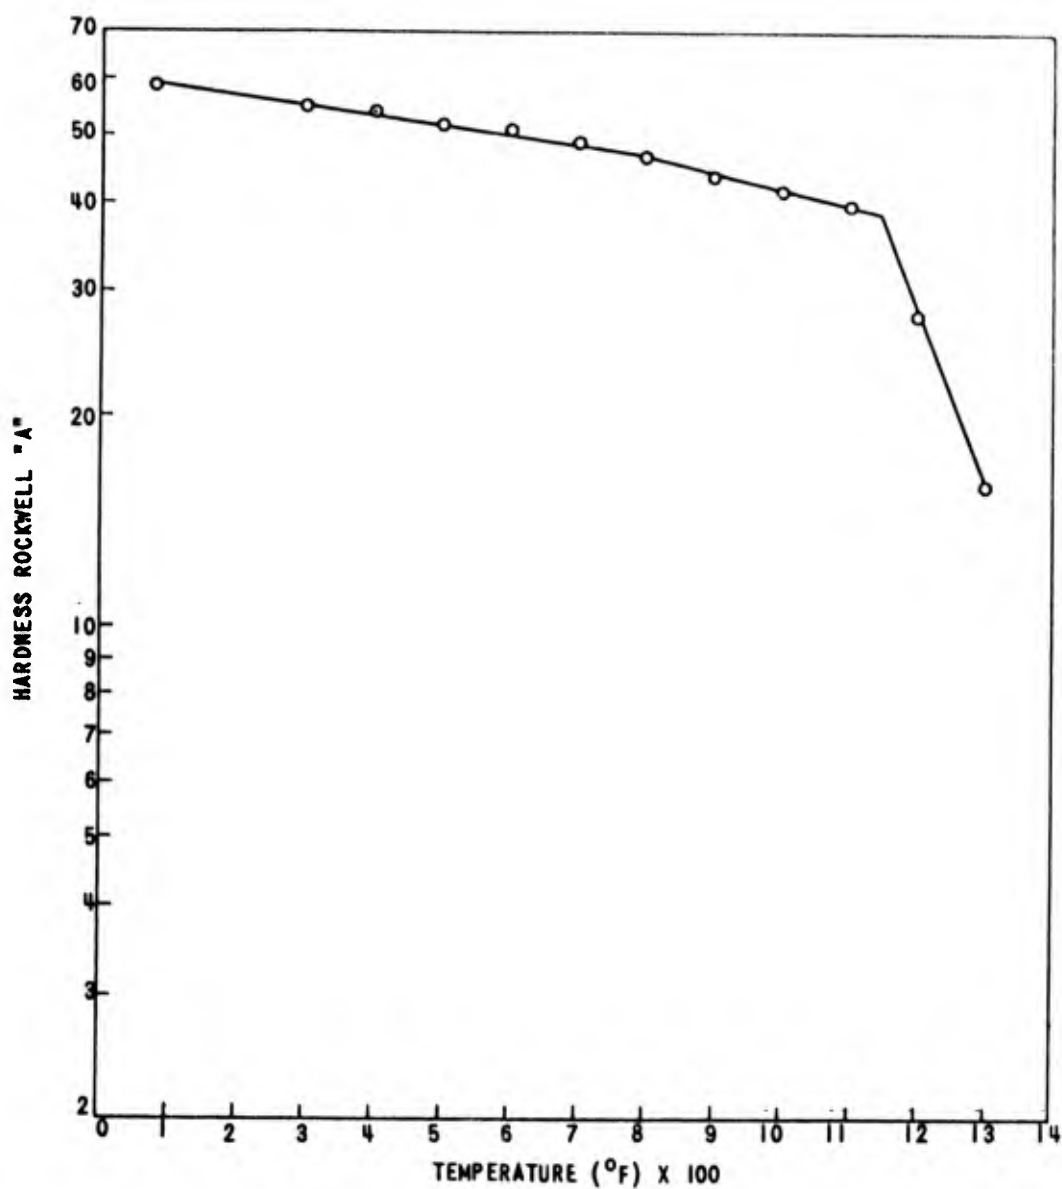


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-13.8Zr (TZ4)

FIGURE 26

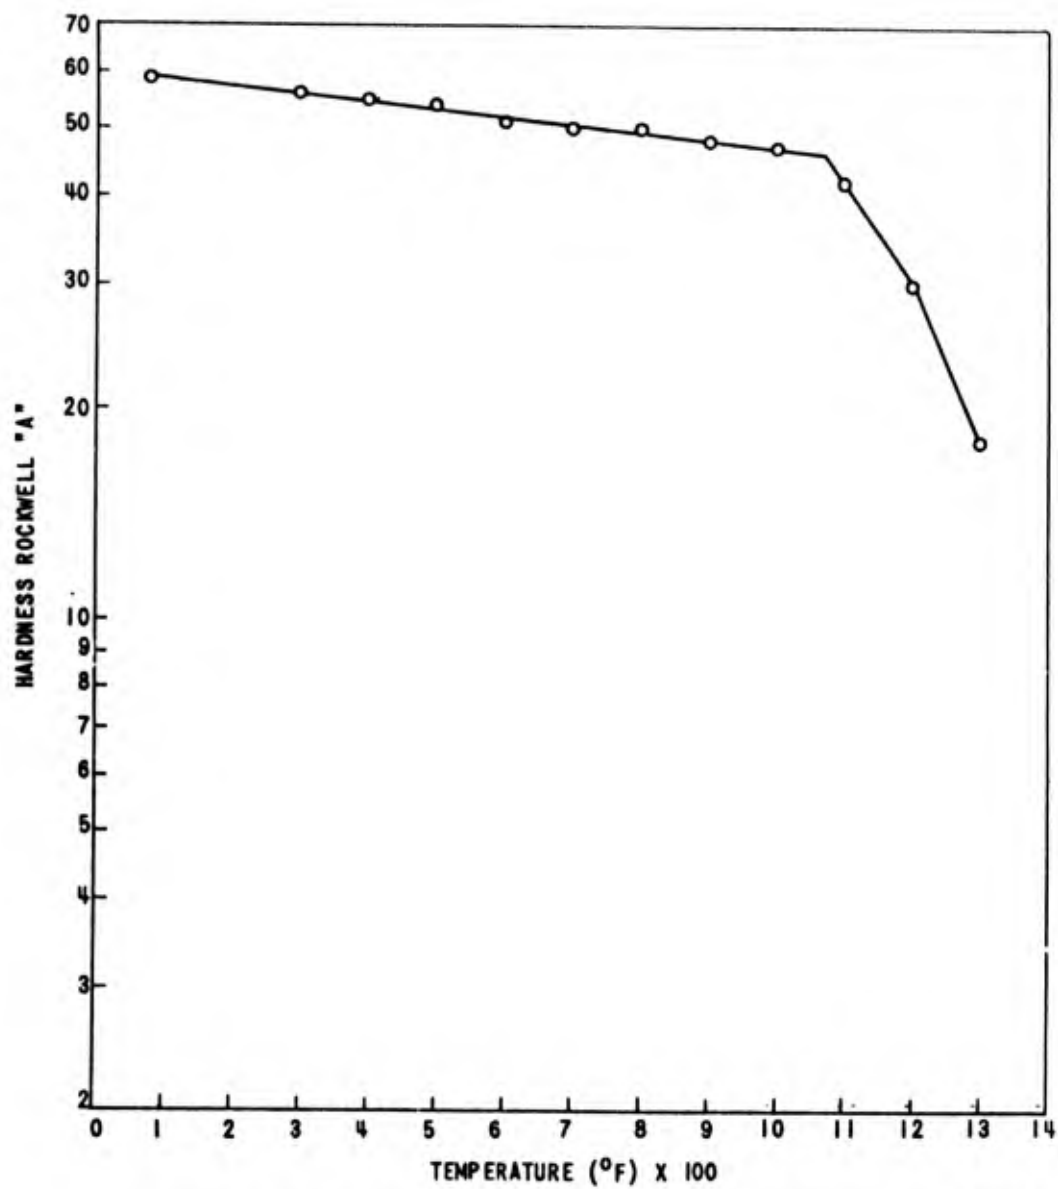


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-24.9Zr (TZ5)

FIGURE 27

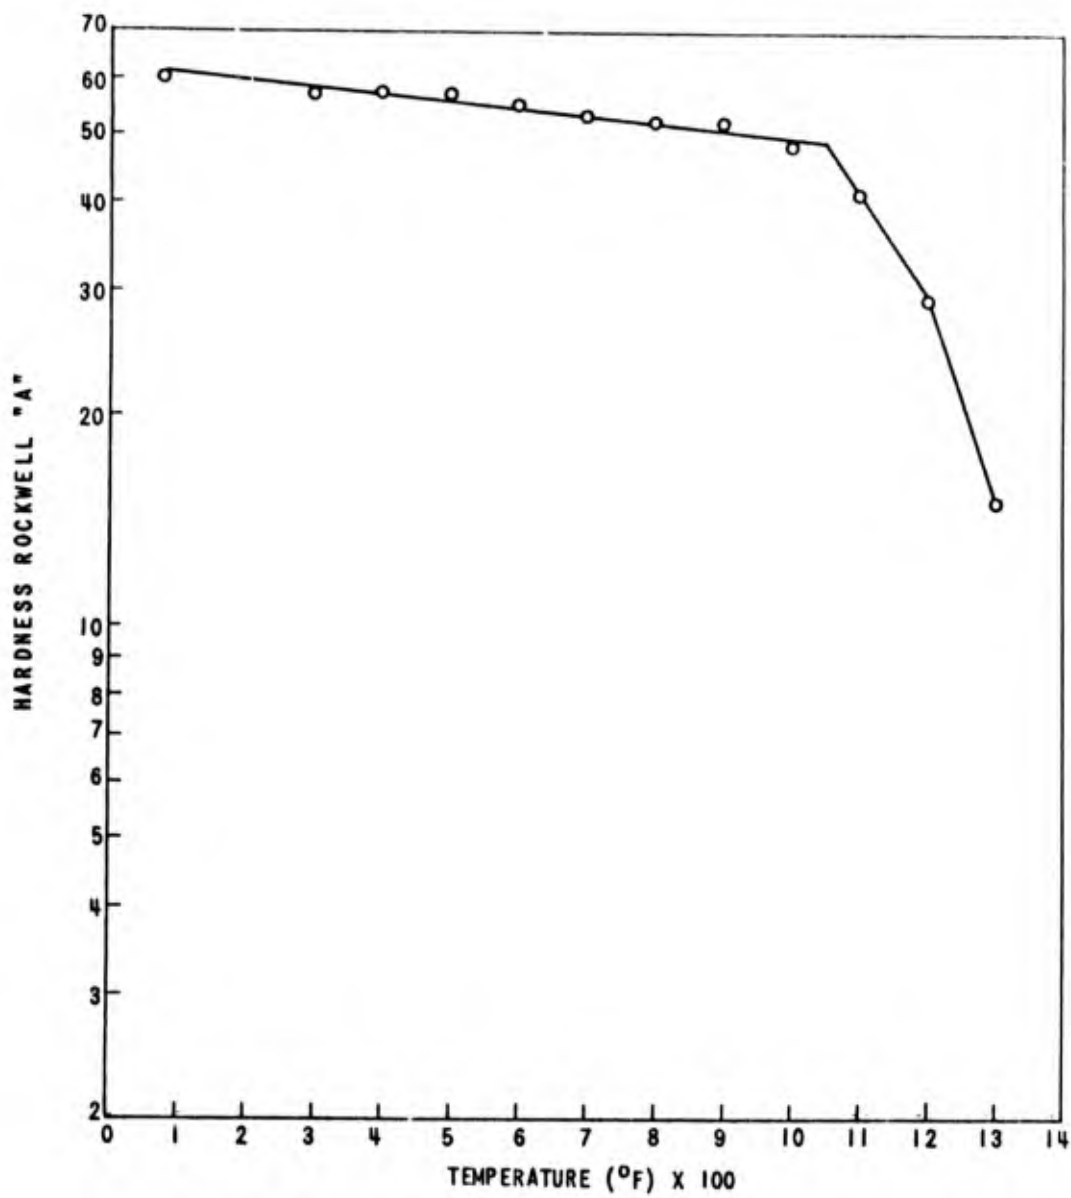


EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-26.3Zr (TZ6)

FIGURE 28

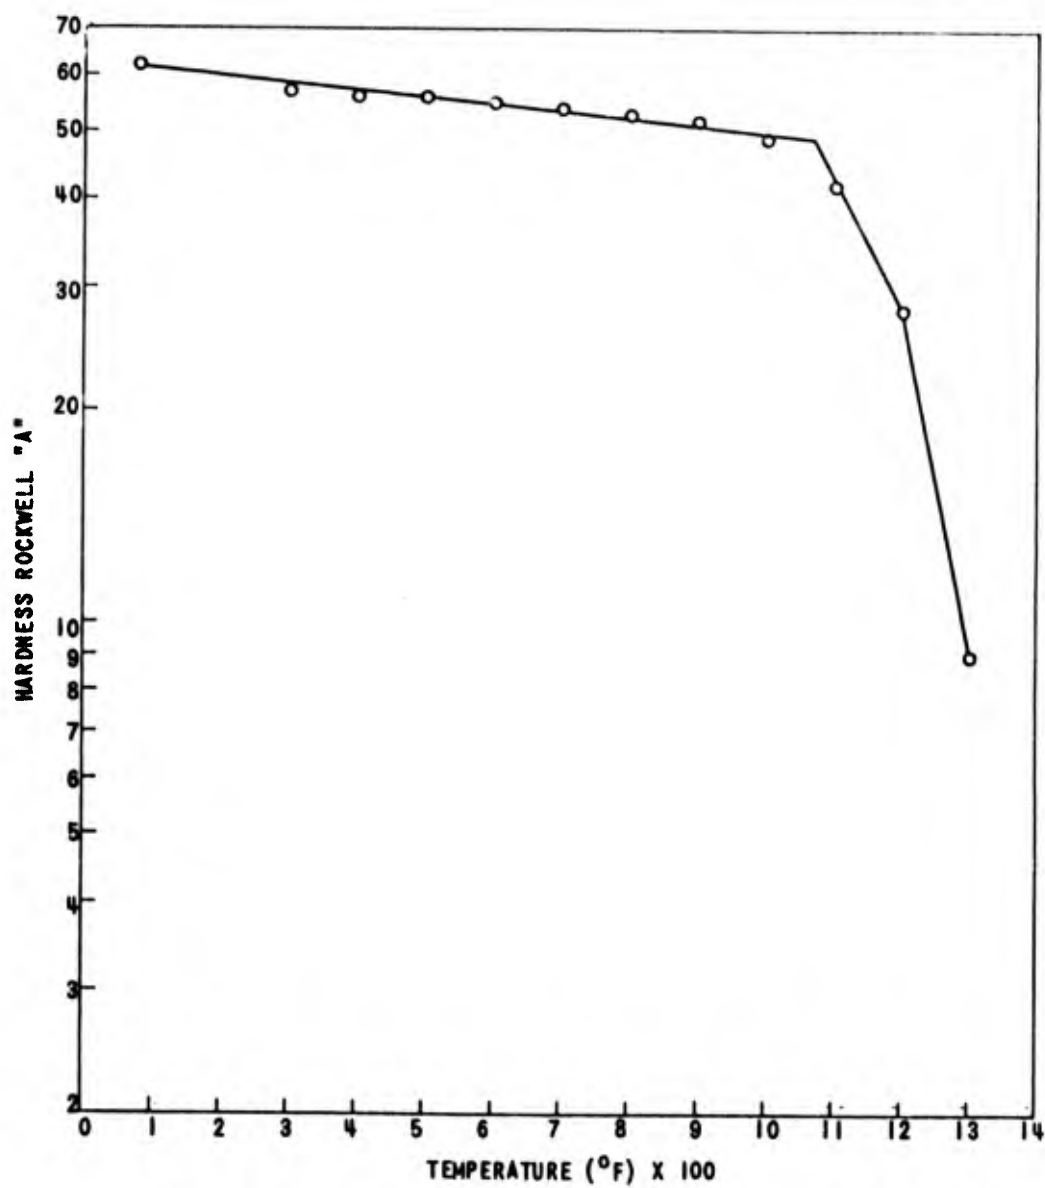

EFFECT OF TEMPERATURE ON THE HARDNESS OF Ti-31.5Zr (TZ7)

FIGURE 29

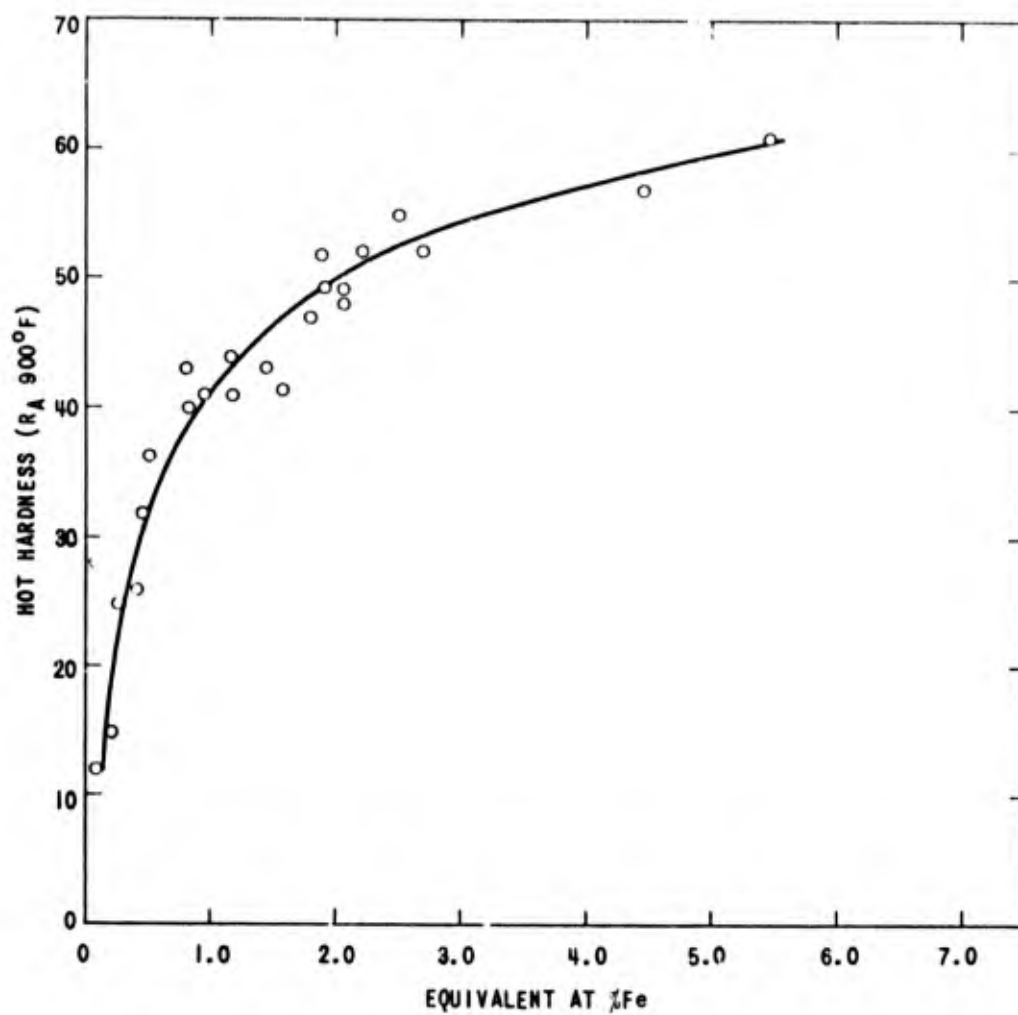

EFFECT OF CHEMICAL COMPOSITION ON THE HOT HARDNESS OF TITANIUM
AT 900°F

FIGURE 30

WATERTOWN ARSENAL
TECHNICAL REPORT DISTRIBUTION

Report No.: WAL TR 401/300

Title: "The Hot Hardness of Titanium
and Titanium Alloys"

To:	No. of Copies
Commanding Officer Watertown Arsenal Watertown 72, Mass. Attn: ORDBE-L	5
Rodman Lab.	1
OMRO, PS&C Division	1
Office, Chief of Ordnance Department of the Army Washington 25, D. C. Attn: ORDTB-Res. & Materials	1
Commanding General Frankford Arsenal Philadelphia 37, Pa. Attn: Pitman-Dunn Labs.	2
Commanding General Picatinny Arsenal Dover, New Jersey Attn: SFAL	1
Commanding Officer Rock Island Arsenal Rock Island, Illinois Attn: Laboratory	1
Commanding Officer Springfield Armory Springfield 1, Mass. Attn: ORDBD-TX	1
Commanding Officer Watervliet Arsenal Watervliet, New York Attn: ORDBF-RT	1
Commanding General Aberdeen Proving Ground Aberdeen, Maryland Attn: Ballistic Research Lab.	1

To:	No. of Copies
Commanding General Detroit Arsenal Center Line, Michigan Attn: ORDMX-BMW ORDMX-AL	1 1
Commanding General Ordnance Weapons Command Rock Island, Illinois Attn: ORDOW-TX	2
Commanding General U. S. Army Rocket & Guided Missile Agency Redstone Arsenal, Alabama Attn: ORDDW-MR	1
Commanding General Army Ballistic Missile Agency Redstone Arsenal, Alabama Attn: ORDAB-DV	1
Commanding General Ordnance Ammunition Center Joliet, Illinois Attn: ORDLY-AR	1
Commanding General Ordnance Tank-Automotive Command 1501 Beard Street Detroit 9, Michigan Attn: ORDMC-RM.1	1
Commanding Officer Diamond Ordnance Fuze Labs. Washington 25, D. C. Attn: Tech. Reference Section ORDTL 06.33	1
Commanding Officer Office of Ordnance Research Box CM, Duke Station Durham, North Carolina Attn: ORDOR-ED	1
Chief, Bureau of Aeronautics Department of the Navy Washington 25, D. C. Attn: TD Division	1

To:	No. of Copies
Chief, Bureau of Ordnance Department of the Navy Washington 25, D. C. Attn: RE-8a	1
Chief, Bureau of Ships Department of the Navy Washington 25, D. C. Attn: Code 592	1
Director Naval Research Lab. Anacostia Station Washington 25, D. C. Attn: Tech. Info. Officer	1
Chief, Office of Naval Research Department of the Navy Washington 25, D. C. Attn: Code 423	1
Commander Naval Proving Ground Dahlgren, Virginia Attn: A&P Lab.	1
Chief, Naval Eng. Exp. Station Department of the Navy Annapolis, Maryland	1
Armed Services Tech. Info. Agency Arlington Hall Station Arlington 12, Virginia	5
Commanding General Wright-Patterson Air Force Base Dayton 2, Ohio Attn: WCRT0	1
WCRR1	1
National Advisory Committee for Aeronautics 1724 F Street, N. W. Washington 25, D. C.	1
Jet Propulsion Laboratory California Institute of Technology 4800 Oak Grove Drive Pasadena, California Attn: Dr. Leonard Jaffe	1

To:	No. of Copies
British Joint Services Mission 1800 K Street, N. W. Washington, D. C. Attn: Technical Services Dept.	4
Canadian Joint Staff 2450 Mass. Ave. Washington 8, D. C. Attn: GSO-I, A&R Sec.	3
Chief, Bureau of Mines Eastern Research Station College Park, Maryland	1
Commanding General Corps of Engineers Fort Belvoir, Virginia Attn: Eng. R&D Labs.	1
Atomic Energy Commission P. O. Box 62 Oak Ridge, Tennessee Attn: Library	1

TOTAL REPORTS DISTRIBUTED 51

AD _____ Accession No. _____ Watertown Arsenal Laboratories, Watertown 72, Mass. THE HOT HARDNESS OF TITANIUM AND TITANIUM ALLOYS - F. R. Larson Report No. WAL TR 401/300, July 1958, 6 pp - tables - illus, DA Proj 593-32-003, 00 Proj TB4-003, Unclassified Report The hot hardness of 27 different heats of titanium and titanium alloys was studied. Tests were conducted on a modified Rockwell machine in an argon atmosphere. Results indicate that low alloy heats lose their hardnesses at a fairly high even rate. On the other hand, high alloy heats hold their hardnesses well up to about 1100°F, and then the hardness drops off very sharply with increasing temperature. The influence of alloying elements in promoting resistance to softening was evaluated at 900°F. Iron was found to be the most effective with the other elements being arranged in order of decreasing effect, as follows: manganese, molybdenum, aluminum, zirconium, and chromium.	UNCLASSIFIED 1. Titanium	AD _____ Accession No. _____ Watertown Arsenal Laboratories, Watertown 72, Mass. THE HOT HARDNESS OF TITANIUM AND TITANIUM ALLOYS - F. R. Larson Report No. WAL TR 401/300, July 1958, 6 pp - tables - illus, DA Proj 593-32-003, 00 Proj TB4-003, Unclassified Report The hot hardness of 27 different heats of titanium and titanium alloys was studied. Tests were conducted on a modified Rockwell machine in an argon atmosphere. Results indicate that low alloy heats lose their hardnesses at a fairly high even rate. On the other hand, high alloy heats hold their hardnesses well up to about 1100°F, and then the hardness drops off very sharply with increasing temperature. The influence of alloying elements in promoting resistance to softening was evaluated at 900°F. Iron was found to be the most effective with the other elements being arranged in order of decreasing effect, as follows: manganese, molybdenum, aluminum, zirconium, and chromium.	UNCLASSIFIED 1. Titanium
AD _____ Accession No. _____ Watertown Arsenal Laboratories, Watertown 72, Mass. THE HOT HARDNESS OF TITANIUM AND TITANIUM ALLOYS - F. R. Larson Report No. WAL TR 401/300, July 1958, 6 pp - tables - illus, DA Proj 593-32-003, 00 Proj TB4-003, Unclassified Report The hot hardness of 27 different heats of titanium and titanium alloys was studied. Tests were conducted on a modified Rockwell machine in an argon atmosphere. Results indicate that low alloy heats lose their hardnesses at a fairly high even rate. On the other hand, high alloy heats hold their hardnesses well up to about 1100°F, and then the hardness drops off very sharply with increasing temperature. The influence of alloying elements in promoting resistance to softening was evaluated at 900°F. Iron was found to be the most effective with the other elements being arranged in order of decreasing effect, as follows: manganese, molybdenum, aluminum, zirconium, and chromium.	UNCLASSIFIED 1. Titanium	AD _____ Accession No. _____ Watertown Arsenal Laboratories, Watertown 72, Mass. THE HOT HARDNESS OF TITANIUM AND TITANIUM ALLOYS - F. R. Larson Report No. WAL TR 401/300, July 1958, 6 pp - tables - illus, DA Proj 593-32-003, 00 Proj TB4-003, Unclassified Report The hot hardness of 27 different heats of titanium and titanium alloys was studied. Tests were conducted on a modified Rockwell machine in an argon atmosphere. Results indicate that low alloy heats lose their hardnesses at a fairly high even rate. On the other hand, high alloy heats hold their hardnesses well up to about 1100°F, and then the hardness drops off very sharply with increasing temperature. The influence of alloying elements in promoting resistance to softening was evaluated at 900°F. Iron was found to be the most effective with the other elements being arranged in order of decreasing effect, as follows: manganese, molybdenum, aluminum, zirconium, and chromium.	UNCLASSIFIED 1. Titanium