

UNCLASSIFIED

AD NUMBER
ADB255677
NEW LIMITATION CHANGE
TO Approved for public release, distribution unlimited
FROM Distribution: Further dissemination only as directed by National Aeronautics and Space Administration, Washington, DC 20546, NOV 1967, or higher DoD authority.
AUTHORITY
NASA TR Server Website

THIS PAGE IS UNCLASSIFIED

73910

X 68 19 039  
NASA CR 96639

CONTRACT NAS 7-436 - INTERIM REPORT 06641-6014-R000 - NOVEMBER 1967

**AMPTIAC**

**ADVANCED  
VALVE  
TECHNOLOGY**

20000519 094

**VOLUME II MATERIALS COMPATIBILITY  
AND LIQUID PROPELLANT STUDY**

PREPARED FOR  
CHIEF, LIQUID-PROPULSION TECHNOLOGY, CODE RPL  
NATIONAL AERONAUTICS AND SPACE ADMINISTRATION  
WASHINGTON, D. C.

Reproduced From  
Best Available Copy

**TRW** SYSTEMS  
ONE SPACE PARK • REDONDO BEACH • CALIFORNIA

**DQC** QUALITY INSPECTED 4

73910

# ADVANCED VALVE TECHNOLOGY

VOLUME II

MATERIALS COMPATIBILITY AND LIQUID PROPELLANT STUDY

CONTRACT NAS 7-436

INTERIM REPORT

06641-6014-R000

NOVEMBER 1967

PREPARED FOR

CHIEF, LIQUID PROPULSION TECHNOLOGY, CODE RPL  
NATIONAL AERONAUTICS AND SPACE ADMINISTRATION

### DISTRIBUTION STATEMENT F:


Further dissemination only as directed by

NATIONAL AERONAUTICS AND SPACE


or higher DoD authority.

ADMINISTRATION, WASHINGTON, DC

20546-0001



R. J. Salvinski, Program Manager

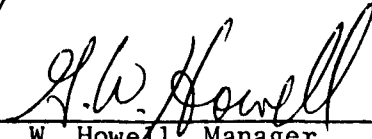

G. W. Howell, Manager  
Propulsion Auxiliaries and  
Component Technology Department



D. H. Lee, Assistant Manager  
Technology Laboratory

TRW SYSTEMS GROUP  
ONE SPACE PARK • REDONDO BEACH, CALIFORNIA

## FOREWARD

This report was prepared by TRW Systems Group, Redondo Beach, California, and contains the results of work accomplished between January 1967 to November 1967. The report is published in two volumes. This volume reports the results of the work accomplished on the Liquid Propellant Study. The work was performed for the Chief, Liquid Propulsion Technology, Code RPL; Headquarters, National Aeronautics and Space Administration. The Headquarters Project Manager is Mr. Frank E. Compitello. The program was administered under the technical direction of Mr. Louis R. Toth of the Jet Propulsion Laboratory, Pasadena, California.

The work performed on the program was accomplished by TRW Systems Group, Power Systems Division, Technology Laboratory. Mr. R. J. Salvinski of the Auxiliaries and Component Technology Department is the Program Manager. Technical efforts provided for the work reported in Volume II of this program by the several TRW Systems Group personnel are acknowledged.

Mr. L. Berman	Materials Engineering Department, Power Systems Division
Mr. A. Grunt	Chemistry and Chemical Engineering Department, Power Systems Division
Mr. J. Reger	Materials Science Department, Systems Laboratories
Dr. R. Sayano	Biosciences and Electrochemistry Department, Systems Laboratories
Dr. V. Srinivasan	Biosciences and Electrochemistry Department, Systems Laboratories

## ABSTRACT

This report describes the work performed by TRW Systems Group during a 12-month period with the objective of advancing the state of the art of valves used on spacecraft liquid propulsion systems. Current problems and future requirements relating to valve design, operation and test were determined. Interviews were held with personnel of NASA, Air Force, and prime manufacturers of propulsion systems to identify valve problems. New technology was utilized where necessary, to solve problems. Areas of study included propellant valves, valve actuators, and fluidic controls, instrumentation and measurements, liquid propellants and thin polymeric films. The results of the effort are reported in two volumes.

### Volume I - Spacecraft Valve Technology

The valve technology study included problem analysis and problem identification; a review of reliability techniques in the specific area of valve redundant systems; seal leakage; and conceptual studies. A bipropellant valve concept requiring no-moving parts is described. Surface tension of liquids to provide valve sealing was studied and test data presented. A no-moving parts valve based on the principle of electroplating to effect a zero leak shutoff and throttling function was fabricated and tested. Conceptual tests were performed in a simple shutoff valve utilizing the interaction of magnetic fields on liquids to shift the liquid from off or on flow positions.

The applications and limitations of valve actuators were determined and new technology reported included a high speed actuator study. Reported are a monopropellant and bipropellant actuator, and a thermal actuator concept. The monopropellant actuator was fabricated and tested to determine feasibility. An investigation of thin film beryllium for use as an electrical conductor at low temperatures showed constant electrical resistance within 1 percent over a temperature range from ambient to liquid  $N_2$ . Actuation techniques studied include electromechanical, hydraulic, pneumatic, chemical and thermal.

The advantages of applying fluidics to liquid propulsion systems are reduced size, and weight, with increased reliability. The most common fluidic devices were studied relative to configuration, performance, fabrication and materials, specific functional parameters, propellant compatibility, and the space environment. The technical problems and standard application criteria were reviewed, and the analytical techniques used to synthesize and design fluidic systems from the components level were outlined. Conceptual studies were initiated in the areas of pressure references and fluid flow regulation. An extensive bibliography is included.

In-flight leakage and valve positioning measurements criteria were established. The application of thin polymeric films as compatible coatings and valve seals were considered. In support of the work, an investigation was made of the formation kinetics of the films applied by electron bombardment techniques.

*Start*  
Volume II - Materials Compatibility and Liquid Propellant Study

This volume includes the results of surveys pertaining to the materials compatibility, shock sensitivity, lubricity, viscosity, radiation tolerances, and effects of leakage for 21 liquid propellants in present use or anticipated use within the next ten years. The information contained herein results from review of the literature listed in the Bibliography at the conclusion of this section. A new test method was studied pertaining to the evaluation of materials compatibility with propellants for long term storage.

Also included in this volume is a report on clogging of filters and orifices during flow with  $N_2O_4$ .

*P. 1-6*  
→

## CONTENTS

	<u>Page</u>
I. MATERIALS COMPATIBILITY	1-1
INTRODUCTION	1-1
DISCUSSION	1-2
MATERIALS COMPATIBILITY TEST METHODS	1-6
RECOMMENDATIONS	1-9
PROPELLANT RATING CHART (TABLE 1-1)	1-11
EARTH STORABLE PROPELLANTS	1-12
FUELS	1-12
HYDRAZINE ( $N_2H_4$ )	1-12
MONOMETHYLHYDRAZINE ( $CH_3NHNH_2$ )	1-20
UNSYMMETRICAL DIMETHYLHYDRAZINE ( $(CH_3)_2NNH_2$ )	1-23
AEROZINE-50 (50% HYDRAZINE/50% UDMH)	1-28
PENTABORANE ( $B_2H_9$ )	1-34
OXIDIZERS	1-39
NITROGEN TETROXIDE (NTO) ( $N_2O_4$ )	1-39
CORROSION OF MATERIALS WITH IMPURE $N_2O_4$	1-51
SPACE STORABLE PROPELLANTS	1-61
FUELS	1-61
DIBORANE ( $B_2H_6$ )	1-61
HYBALINE A-5	1-64
LIQUID PETROLEUM GASES (LPG) PROPELLANTS	1-66
OXIDIZERS	1-68
CHLORINE TRIFLUORIDE (CTF) ( $ClF_3$ )	1-68
CHLORINE PENTAFLUORIDE	1-72
OXYGEN DIFLUORIDE ( $OF_2$ )	1-74
PERCHLORYL FLUORIDE (PF) ( $FClO_3$ or $ClO_3F$ )	1-79
NITROGEN-FLUORINE COMPOUNDS	1-83
Nitrogen Trifluoride ( $NF_3$ )	1-83
Nitryl Fluoride ( $NO_2F$ )	1-83
Tetrafluorohydrazine ( $N_2F_4$ )	1-83

	<u>Page</u>
HARD CRYOGENICS	
LIQUID FLUORINE (LF <sub>2</sub> )	1-84
LIQUID OXYGEN (LOX)	1-90
LIQUID HYDROGEN (H <sub>2</sub> )	1-95
LIQUID OXYGEN-LIQUID FLUORINE MIXTURES (FLOX)	1-98
GELLED PROPELLANTS	1-99
LIQUID GELLED PROPELLANTS	1-99
METALLIZED GELLED PROPELLANTS	1-103
REFERENCES - MATERIALS COMPATIBILITY	1-106
II. CLOGGING OF FILTERS AND ORIFICES	2-1

## MATERIALS COMPATIBILITY AND LIQUID PROPELLANT STUDY

### I. MATERIALS COMPATIBILITY

#### INTRODUCTION

The information contained in this section has been extracted from the best technical sources available; these sources are referenced in the bibliography at the end of the compatibility section. Materials compatibility data derived from these sources are generally the result of laboratory scale bottle tests involving immersion of materials in propellants under static conditions. For the most part, these data are fairly consistent, but many instances exist where data are contradictory or differing in degree of compatibility. Also, in most cases the data report only the effects of propellant exposure, and do not reflect the functionality of the material after exposure.

Where differences were noted, acceptance of information was based on multiple sources, appropriate procedures, availability of service data, and recentness of evaluation. Unless specifically noted, data not meeting these criteria have not been included.

Propellant compatibility data contained in the following reference is included:

"Advanced Valve Technology," Interim Report, September 1, 1965 to November 1, 1966, TRW Systems Report No. 06641-6004-R000.

The work presented in this report represents a continuation of the referenced study, however, where possible the data was updated to include more recent information.

## DISCUSSION

In the course of the literature search performed, several areas requiring early additional effort became apparent. Basically, it was noted that the testing performed to obtain the desired data shared a common failing: there was no conformity of method, no procedural approach to the problem of the compatibility test, and little assessment of the effects of impurities in the propellants. For example, some long term compatibility data were generated based on actual immersion for one year periods, while others were conducted for shorter periods of time, and data extrapolated to one year. Short term compatibility, in some cases, denotes ability to survive propellant exposure for two to four weeks. In other cases, it is defined as the ability to withstand propellant splash or fumes for designated periods of time. In very few cases, has the effect of the material on the propellants been determined, and the initial processing of the test specimen is seldom recorded. The variations do not reflect on the multitude of investigators, but rather on the void which exists with respect to test standards to which work has been performed.

The compatibility of materials to the liquid propellants primarily takes on three aspects:

- Slow to rapid chemical or electrochemical reaction between metals and the propellants leading to corrosion and loss of strength of the metals and/or degradation of the propellants.
- Slow to rapid chemical reaction between non-metals and the propellants leading to degradation and loss of strength.
- Rapid chemical reaction between all types of materials and the propellants leading to explosion or fire within the system.

Each of these undesirable aspects of materials compatibility have been investigated by various organizations, and the data reported. However, there are quite often differing and sometimes conflicting points of view concerning the compatibility and use of a specific material. This conflict of opinion frequently arises not from incorrect data or interpretation, but rather from a lack of a common reference point. In particular,

Failure to delineate all of the testing parameters and procedures, and of not characterizing the test fluid sufficiently, can lead to widely different results, each of which, however, are valid within the context of the experiment performed. Two illustrations are presented as cases in point:

#### 1. Corrosion

Most of the data on corrosion of metals are given in terms of depth of material removed per unit time. Usually the data are presented as penetration in mils per year (MPY). Not so frequently, however, is a description given of the type of corrosion, or of the localized severity. Inasmuch as a MPY removal figure implies a general, overall corrosion of the metal, failure of the investigator to remark that the greatest amount of corrosion occurred as pitting or intergranular attack could lead a designer, using the compatibility data, to arrive at an erroneous conclusion regarding the service life of the metal with respect to the propellant in question. It is suggested that a common corrosion description, such as that proposed by Champion\*, should be employed when reporting data of this nature.

#### 2. Propellant and Test Specimen Characterization

It is well known that relatively minor impurities can cause gross changes in the characteristics of liquid propellants. Failure to properly analyze and report the chemical makeup of the test fluid utilized in the experiments can lead to unwarranted conclusions. As an example, several metals are compatible with  $OF_2$ . If, however, the  $OF_2$  is contaminated with water, hydrogen fluoride is formed which is particularly reactive toward metals which cannot form adherent, passive protective films against the fluoride ion. Thus, failure to analyze the HF content of the  $OF_2$  can lead to erroneous conclusions regarding its compatibility.

\* General Reference, No. 1, Page 1-105.

This same type of problem has occurred in the testing of the impact sensitivity of LOX with various metals. Lack of close control in insuring contamination free metal samples and the testing apparatus has led to some conflict of data in this area.

Since contamination can occur during transport and handling of samples and test equipment, it is suggested that the test fluids be analyzed as used, and any possible contamination path be noted.

From the standpoint of the valve designer involved in the process of material selection as one portion of the component design, the available data do not provide the necessary information from which to make rapid and automatic selections. In order for such information to be intelligently used, it must be supplemented in areas which are currently lacking.

For example, the data presently available do not normally distinguish between static and dynamic compatibility, either in respect to the test methods employed, or where a material's use is approved, in respect to that material's potential application. In many instances it may be assumed that the mechanism for potential failure of a particular material is augmented by the mechanical action of adjoining component materials and/or the erosive effects of the flowing propellant itself. Specifically, a material appropriate for use as a static parking within a given valve assembly may be completely incompatible, in the identical propellant service, when used as a sliding seal or an impact seal. For example, butyl rubber seals and O-rings have proven to be excellent static seals for containment of nitrogen tetroxide, even though the material itself is completely incompatible with the propellant. The sealing ability of the material is enhanced by the fact that it swells and becomes gummy in contact with  $N_2O_4$ . On the other hand, once the material has been exposed to  $N_2O_4$ , it could never survive a sliding motion. Data regarding these conditional aspects of compatibility are not presently documented. Similarly, the effects of temperature, pressure and propellant phase variations have seldom been treated in establishing compatibility.

A second distinct information void, with respect to material compatibility, exists in the area of historical data accumulation. The primary source of the data presented is the laboratory test. This is seldom supplemented by field information which should be extensive.

A search of the actual materials employed in varying configurations, environments, and propellant service would greatly aid in establishing a realistic confidence level for new valve designs. A detailed search, though beyond the scope of the present program, would not only serve as an early source of dynamic use-data, but would provide confirmation of, and give direction to, successive laboratory test effort. An attempt was, therefore, made in the course of the Advanced Valve Technology Program, to survey briefly the available experience through direct interview of cognizant personnel.

The data presently contained in this survey report attempt to correct some of these shortcomings by including what supplementary information could be readily obtained. It is felt that a more extensive program will permit sounder initial component designs with a minimum expenditure of development time and cost and is, therefore, warranted.

## MATERIALS COMPATIBILITY TEST METHODS

There is a serious lack of precise compatibility data for both short term and long term storage of the more energetic propellants in the accepted materials of construction. The shortcomings of present compatibility data and the lack of standard, unified test methods, reporting and compilation has been discussed in the introduction. The more serious problem is that of obtaining reliable data for long term requirements necessary for upcoming spacecraft missions, which have operating lifetimes of up to ten years. It is generally accepted that short term, accelerated storage and testing do not give data which can be reliably extrapolated to longer mission lives. Compatibility testing in real time is prohibitively expensive, and may be outmoded by state of the art advances from the initiation of testing, which may render the evaluation obsolete.

Under this program a <sup>A</sup> laser technique was studied which may prove to circumvent the traditional shortcomings of conventional compatibility testing. This technique is holographic interferometry. This test method records the fringe pattern of the propellant adjacent to the sample. <sup>Ti, Co, R, S, Al, Mg</sup> The distortion of the fringe pattern with time represents corrosion mapping. The theory of holographic processes have been extensively discussed in the literature\* and will not be detailed.

However, it is significant to note that a hologram is able to record a complex optical wave so that when the hologram is reilluminated later, another optical wave is created identical to the original in both phase and amplitude. It is this property which makes it possible to use a hologram to generate either the test beam, or a comparison beam, or both as an interferometric analytical technique.

Holographic interferometry may be considered as a form of common path interferometry (normally not used with conventional light sources due to cell size, configurations, optical inhomogeneities, etc.), except that the

\*E.N. Leith and J. Upatnieks, J. Opt. Soc. Amer., 52, 1123 (1962); 53, 377 (1963); 54, 1295 (1964).

[test and comparison beams are separated in time. It is the use of this feature, either double exposure or "stored beam" interferometry, that is of interest in their application to compatibility and corrosion investigation.]

Thus far, the techniques have been utilized in applications to electro-mechanical processes\*. In the case of double exposure interferometry, the holographic record represents only one instant of time, and it is not possible to view changes as they occur in the subject without making new holograms. However, if only the comparison beam is holographically recorded and "stored", and the reconstructed comparison beam is compared with the actual subject and test beam, then the real time behavior of the subject can be seen interferometrically. Thus, "stored beam" holographic interferometry offers not only real time information, but provides a means for acquiring time-lapse or moving picture records during the course of the reaction.]

There are several advantages of the "stored beam" holographic interferometric method over the classical methods: alignment and preparatory procedures are far less critical, the common path nature provides significant flexibility and irregular shaped and imperfect optic elements and cells may be used. Furthermore, by the use of diffusers, three-dimensional information may be obtained. Thus, investigation of localization of corrosion and non-rotational symmetrical activities can be observed, as well as the use of assymmetric samples. p. 1-10

These advantages then, enable one to observe changes which occur in a subject as a function of time, and since the aspects of the subject do not change the interference pattern as a function of time, a technique is

---

\* L. O. Heflinger, R. F. Wuerker and R. E. Brooks, Appl. Phys., 37, 642 (1966).

R. W. Brooks, L. O. Heflinger and R. F. Wuerker, Appl. Phys., Letters, 7, 248, (1965).

available which is able to measure subtle changes in very complex samples incapable of being explored with any of the classical methods of interferometry.

While it is true that this method has thus far been utilized only for electromechanical changes with an external driving force, there is no reason that subtle interactions between materials and their potentially corrosive environment cannot be observed also. Thus, elucidation of the onset and nature of corrosion should be observable. The rating of the suitability of a material can be evaluated with far more precision than with any other available method.

## RECOMMENDATIONS

In order to provide greater utility for the valve component designer, it is recommended that a study be authorized and implemented which will achieve the following results:

1. Establishment of realistic criteria for valve component materials and definition of parameters which can affect performance under those conditions.
2. Establishment of test methodology (see section on test methods), the test fluid and test specimen, and which will provide more meaningful information to the designer relative to the performance of materials under specified conditions.
3. Establishment of a procedure for documenting and reporting compatibility data such that extraneous data will be minimized, and pertinent data will be presented in their most useable form.

The proposed program would not only take advantage of all existing data, but would identify the effects of material processing variables as well as propellant impurities. It would also introduce advanced concepts of testing to more accurately determine the functionality of materials during and after propellant exposure, and under static and dynamic conditions.

The recommended program will also consider the long duration mission such as the ten year space flight to the outer planets. Past applications have usually involved storage and operation times on the order of days, weeks or months. This has generally enabled design personnel to instigate full duration tests of new materials during the design phase. Full duration tests of materials for a ten year space flight might well become obsolete during the test phase due to rapid technological advances in material developments. Consequently, the proposed program will attempt to generate accelerated test methods that will provide valid data applicable to long term materials and component compatibility with propellants.

It is felt that the outlined program will provide a significant advance in an area of vitally needed data where the approach taken to date has been seriously inadequate.

PROPELLANT RATING CHART (TABLE 1-1.)

In this chart the severity of the problems associated with each propellant were assessed and values assigned to the various combinations of propellants and parameters according to the following definitions:

<u>RATING</u>	<u>DEFINITION</u>
1	A value of 1 was assigned to those combinations with which a serious problem exists; i.e., one for which there is no satisfactory solution.
2	A value of 2 was assigned to those combinations with which a problem exists, but for which a remedy may be available. This is, the combination of component and parameter is deemed to be acceptable, <u>with qualifications</u> .
3	A value of 3 was assigned to those combinations which were deemed to be satisfactory; i.e., within the present state of the art.
U	A designation of U was made where the necessary information upon which to base a judgement was unavailable.
NA	Where a parameter was not applicable, the letters NA were used.

Following the Propellant Rating Chart is a discussion of the more serious problem areas (with ratings of 1 or 2) for each propellant type.




TABLE 1-1. PROPELLANT RATING CHART

LEGEND 1 POOR 2 FAIR 3 GOOD NA - NOT APPLICABLE U - UNAVAILABLE INFORMATION (NO TEST DATA)	COMPATIBILITY					VALVE TYPES										OVERALL PROBABLE RATING IN 10 YEARS				
	METALS	CERAMICS	POLYMERS	WET LUBES	DRY LUBES	SHOCK SENSITIVITY	LUBRICITY	VISCOSITY	RADIATION TOLERANCE	EFFECTS OF LEAKAGE	CONTROL OF FLOW	SOFT SEATS	HARD SEATS	COMPONENT STABILIZATION	REGULATORS		SHUTOFF	FLOW METERING	VENT (ZERO-G)	DISCONNECT
EARTH STORAGE																				
FUELS																				
HYDRAZINE	3	3	3	2 <sup>c</sup>	2	3	1	2	2	1-2	3	3	3	2-3	3	3	3	NA	3	3
MONOMETHYLHYDRAZINE	3	3	2	2 <sup>c</sup>	1	3	U	3	2	1	3	U	U	2-3	3	3	3	NA	3	3
U-DIMETHYLHYDRAZINE	3	3	2	2 <sup>c</sup>	1-2	3	1	3	2	1-2	3	3 <sup>a</sup>	3	1-2	3	3	3	NA	3	3
AEROSOLINE-50	3	3	2	2 <sup>c</sup>	1-2	3	1	2	2	1-2	3	3 <sup>a</sup>	3	2-3	3	3	3	NA	3	3
PENTABORANE	3	2	2-3	2	3	3	U	3	3	1	3	2-3	2	U	3	2-3	2-3	2-3	3	2-3
OXIDIZERS																				
NITROGEN TETROXIDE	3	3	2	2	2	3	3	3	3	1-2	3	1-2	3	2-3	3	3	3	NA	3	3
SPACE STORAGE																				
FUELS																				
DIBORANE	3	2	2-3	2	3	3	U	3	3	1	3	2-3	2	U	2-3	2-3	2-3	2-3	3	2-3
HYDRAZINE AS	3	3	3	2-3	2-3	3	2	3	2	2	3	3	3	U	3	1-2 <sup>b</sup>	3	2	3	3
LP <sup>d</sup>																				
OXIDIZERS																				
CHLORINE TRIFLUORIDE	3	2	1-2	1	1	3	U	3	3	1	3	1-2	3	U	3	2 <sup>b</sup>	3	NA	3	2-3
CHLORINE PENTAFLUORIDE	2-3	2	1-2	1	1	3	U	3	3	1	3	1-2	3	U	3	2 <sup>b</sup>	3	NA	3	2-3
OXYGEN DIFLUORIDE	3	2	2	1	1	3	U	3	U	1-2	3	1	3	U	3	2 <sup>b</sup>	3	2-3	3	2
PERCHLORYL FLUORIDE	3	2	2	1-2	1	3	U	2-3	U	1-2	3	2	3	U	3	2 <sup>b</sup>	3	NA	3	2-3
NITROGEN TRIFLUORIDE	3	2	1-2	1	1	3	1-2	2-3	U	1	3	1-2	2-3	U	3	1 <sup>b</sup>	1-2	1-2	2	2-3
NITRYL FLUORIDE	2-3	1-2	1	1	1	3	2	U	U	1	3	1-2	2-3	U	3	1 <sup>b</sup>	1-2	1-2	2	2
TETRAFLUOROETHYLENE	3	2	1-2	1	1	3	2	3	U	1	3	1-2	2-3	U	3	1 <sup>b</sup>	1-2	1-2	2	2
HARD CRYOGENICS																				
LIQUID FLUORINE	3	2	1-2	1	1	3	1-2	3	3	1	3	1-2	2-3	U	3	1 <sup>b</sup>	1-2	1-2	2	2
LIQUID OXYGEN	3	3	2	1	1	3	2	3	3	2	3	2-3 <sup>a</sup>	3	U	3	2 <sup>b</sup>	3	2-3	2	3
LIQUID HYDROGEN	3	3	1-2	1	1	3	2	3	3	2	3	2-3 <sup>a</sup>	3	U	3	1-2 <sup>b</sup>	3	2-3	2	2-3
FLOX (80% LF <sub>2</sub> , 20% O <sub>2</sub> )	3	2	1-2	1	1	3	1-2	3	3	1	3	1-2	2-3	U	3	1 <sup>b</sup>	1-2	1-2	2	2
GELS																				
LIQUID GELS	3	2	2	2	2	3	2	2	2	2	2	3 <sup>a</sup>	3	1	U	1	2	NA	U	2
METALLIZED GELS	2	2	2	1-2	1-2	3	1	2-3	2	1	1	2	2	1	U	1	1	NA	U	2

a. THESE RATINGS, UNLIKE THOSE UNDER ORGANIC POLYMERS, WERE BASED ON THE USE OF A SPECIFIC POLYMERIC MATERIAL, IN MOST CASES TEFLON, FOR SOFT SEATS.  
 b. RATINGS BASED ON LEAKAGE CONTROL.  
 c. THESE RATINGS ARE BASED ON THE USE OF DUPONT FLUORINATED GREASE KRYTOX 240.  
 d. LIQUIDIFIED PETROLEUM GASES; METHANE, PROPANE, BUTENE.  
 e. 300°F, 60 HRS., 6 CYCLES.

## EARTH STORABLE PROPELLANTS

### FUELS

#### HYDRAZINE ( $N_2H_4$ )

Hydrazine is a clear liquid used as a high-energy propellant that is insensitive to mechanical shock or friction and exhibits excellent thermal stability at ambient temperatures. It is considered a hazardous propellant, however, due to its toxicity, reactivity, and flammability. Since it is thermodynamically unstable (i.e., a monopropellant), hydrazine will decompose under elevated temperatures when catalyzed by graphite or a metal oxide such as iron oxide or copper oxide, and will release considerable energy resulting in a possible explosion or fire. In addition, liquid hydrazine exerts sufficient vapor pressure above 100°F to form flammable air mixtures. Its freezing point is 35°F. Hydrazine is hygroscopic and readily forms flammable mixtures in air; therefore, a nitrogen blanket is required.

In assessing the compatibility of a material with hydrazine, the specific application for its use must be considered. Materials satisfactorily used with hydrazine where air oxidation of the surface can be prevented may not be satisfactory for service where prolonged exposure to air cannot be avoided. Factors to consider when selecting materials to use with hydrazine for any given exposure condition are: 1) corrosiveness of the material in contact with hydrazine and 2) the effect of the material and/or its corrosion products formed on the rate of decomposition of hydrazine.

These factors to be considered are particularly true for carbon steel, low-alloy steels, copper alloys, and molybdenum. From the corrosion standpoint, these metals are satisfactory for use in hydrazine; however, these metals and/or their oxides may catalyze hydrazine decomposition at elevated temperatures. At one time it was thought that 316 stainless (containing molybdenum) caused excessive hydrazine decomposition rates at elevated temperatures. However, it is now generally agreed that the

hazard at typical operating (<200°F) temperatures is no greater with 316 stainless than with any of the other 300 series stainless steels.

Table 1-2 lists those materials considered to be compatible with hydrazine for long-term application.

#### PHYSICAL PROPERTIES

Specific Gravity	1.00 (60°F)
Molecular Weight	32.048
Freezing Temperature °F	35.1
Normal Boiling Point °F	236.3
Critical Temperature °F	716
Critical Pressure psia	2131
Heat of Vaporization Btu/lb <sub>m</sub>	540

Discussion of Problem Areas -

Hydrazine (N<sub>2</sub>H<sub>4</sub>)

Wet Lubes (2)\* - Most wet lubes either wash off or are attacked by hydrazine. For limited use, some silicone lubricants and "Q-Seal," Quigley Company, have been used with fair results. A new fluorinated grease by DuPont, Krytox 240, appears to be compatible.

Dry Lubes (2) - Most dry film lubricants are attacked or removed by hydrazine. Electrofilm 1000G and Lubeco 2029-3 are partially compatible and can be used, although wear life after propellant exposure is somewhat reduced.

Lubricity (1) - Unsatisfactory lubricating performance was found for hydrazine in a series of low-load short duration ball bearing and gear tests at 24,600 rpm. The poor lubricity, resulting in degradation of the component metals surveyed, was attributed to its active solvent and reducing properties.

Viscosity (2) - The viscosity of hydrazine presents a problem only at low temperatures. The freezing point of commercial hydrazine is approximately 30°F, which is relatively high for operation under cold climatic conditions. Three methods of preventing N<sub>2</sub>H<sub>4</sub> from freezing have been employed: 1) the addition of freezing point depressant, 2) insulation of container and components, and 3) insulation plus tracing with heat elements, steam, or hot water.

Radiation Tolerance (2) - Hydrazine, UDMH, and Aerozine 50, subjected to an irradiation dose of  $1 \times 10^9$  erg/g, which is the maximum space radiation dose likely to be incurred in two years of operation in the Van Allen belts, showed that the composition of the propellants was not significantly affected. However, a pressure increase resulted, accompanied by the evolution of insoluble gases, due to slight decomposition. It is therefore recommended that tanks be designed to minimize this problem.

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Effects of Leakage (1-2)\* - Anhydrous hydrazine is a flammable liquid, hence leakage may initiate a fire; it is hypergolic with most oxidizing agents and decomposes on contact with catalytic materials including iron rust. Vapors of hydrazine can be detonated by an electric spark or an open flame.

Since this propellant is a strong chemical reducing agent, leakage may result in malfunction of other elements in the system or injury to man. Prolonged exposure to this toxic material produces damage to the liver and kidneys and, to a lesser extent, anemia and lowering of blood sugar concentrations. The threshold value which has been adopted by the American Conference of Governmental Industrial Hygienists is 1 ppm.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

TABLE 1-2. HYDRAZINE (N<sub>2</sub>H<sub>4</sub>)  
 COMPATIBILITY OF MATERIALS FOR  
 LONG TERM APPLICATION (NOTE 1)

MATERIAL	TEST TEMP °F
<u>ALUMINUM ALLOYS</u>	
1100	140
2014	80
2017	160
2024	70
3003	80
4043	160
5052	80
5456	140
6061	160
6061-T6	110
6066	80
716	140
356	160
*356-T6	110
40E	75
Tens 50	-
<u>STAINLESS STEEL</u>	
410	80
416	200 (pits)
430	68
440C	80
302	80
304	140
316	200
317	80
321	140
347	200
17-4 PH	140
17-7 PH	75
AM 350	160
AM 355	160

\*Reported noncompatible for period > 1 year based on limits of decomposition of hydrazine, see specific Reference 128.

HYDRAZINE (N<sub>2</sub>H<sub>4</sub>) (Continued)

MATERIALS	TEST TEMP °F
<u>MISCELLANEOUS METALS</u>	
Chromel A	80
Chromium Plating	70
Gold	75
Hastelloy C	125
Inconel	200
Inconel X	80
K-Monel	140
Monel	80
Nichrome Braze	80
Platinum	110
Silver	80
Silver Solder	75
Stellite 21	75
Tantalum	80
Tin	80
Titanium, A110AT	140
*Titanium, 6Al-4V	160
Zirconium	75
<u>NON-METALS</u>	
Butyl Rubber Compound 805-70	140
Butyl Rubber Compound 823-70 (Parco)	-
Butyl Rubber Compound B480 (Parker)	-
Butyl Rubber Compound 9257 (Precision)	-
Ethylene Propylene Co-polymer	110
Kel-F	80
Polyethylene	80
Teflon	140
Teflon Coatings	-

\*Has been reported noncompatible for period >1 year at 110°F based on limits of decomposition of hydrazine, see specific Reference 128.

HYDRAZINE (N<sub>2</sub>H<sub>4</sub>) (Continued)

<u>MATERIAL</u>	<u>TEST TEMP °F</u>
<u>NON-METALS</u>	
Asbestos	80
Delanium	140
Glass	80
Polypropylene	-
SBR	75
Silicone Grease DC-11	-

Note 1. Metals listed above are rated compatible on a corrosion rate of less than 1 mil per year and the material does not cause decomposition, and is free from impact sensitivity. Non-metals are rated for satisfactory service for general use.

HYDRAZINE (N<sub>2</sub>H<sub>4</sub>) (Continued)

INCOMPATIBLE MATERIALS

INCOMPATIBLE MISCELLANEOUS METALS	INCOMPATIBLE NON-METALS
Cadmium	Buna-N Rubber
Cobalt	Cellulose Acetate
Lead	Diallyl Phthalate
Magnesium	Epons
Zinc	Kel-F 300 @140°F
Brass*	Kel-F @160°F
Bronze*	Kel-F Grease @212°F
Copper*	Natural Rubber
Iron*	Neoprene Rubber
Molybdenum*	Nylon
Mild Steel*	Mylar
6A-4V Ti (110°F, <1 year)**	Polyester
	Polyvinyl Alcohol
	Polyvinyl Chloride
	Saran
	Silastic LS-53
	Tygon

\*The oxide of these metals act as catalysts for decomposition of hydrazine at elevated temperatures.

\*\*Outside limit for decomposition rate of hydrazine, see specific Reference 128.

## MONOMETHYLHYDRAZINE (CH<sub>3</sub>NHNH<sub>2</sub>)

Monomethylhydrazine (MMH) is a clear, water white liquid with a strong amine odor detectable in concentrations of 1 to 3 ppm. It is a fairly volatile liquid; the vapor pressure, 0.96 psia at 77°F, is higher than that of hydrazine and hence creates a more hazardous health problem than hydrazine. The maximum allowable concentration of MMH vapor in air has not been established, but it has been suggested that it be set within 0.1 and 0.5 ppm.

Liquid MMH is not sensitive to impact or friction and is more stable than hydrazine under conditions of mild heating. The flammability characteristics of MMH with air are close to those of hydrazine and UDMH; consequently it should be maintained under a nitrogen blanket at all times. MMH must be stored away from any oxidizers and from possible sources of ignition. All metallic equipment employed for storage and handling of MMH requires grounding to prevent an accumulation of static charge.

An extensive compilation of compatibility data for metals and non-metals is not available. Due to the similarity in catalytic oxidation and chemical activity for MMH and hydrazine, those metals found satisfactory for hydrazine should suffice for MMH. In general, monomethylhydrazine attacks organic materials more readily than does hydrazine. Only short-term studies on a selected few plastics have been reported; no long-term compatibility tests have been done. Table 1-3 lists the materials which have been found to be satisfactory for use in the storage and handling of MMH.

### PHYSICAL PROPERTIES

Molecular Weight	46.075
Freezing Temperature °F	-63
Normal Boiling Point °F	189
Critical Temperature °F	609
Critical Pressure psia	1195
Heat of Vaporization Btu/lb <sub>m</sub>	377

Discussion of Problem Areas -

Monomethylhydrazine

Organic Polymers (2)\* - In general, monomethylhydrazine attacks organic materials more readily than does hydrazine. Materials satisfactory for limited use include Teflon, some silicone rubbers and high density polyethylene.

Wet and Dry Lubes (2) - Because monomethylhydrazine is a better solvent than UDMH and  $N_2H_4$ , it also has attendant undesirable lubricant and "wash-out" effects. DuPont's Krytox 240 grease is compatible. Electrofilm 2406 and 1000G dry film lubricants have shown an ability to withstand attack. However, lubricity after exposure is undetermined. Cico 200-029-3 dry film lubricant has shown an increase in wear life after 72 hours exposure to monomethylhydrazine.

Radiation Tolerance (2) - This rating was made by analogy to hydrazine and UDMH, which have very similar chemical structure and physical and chemical properties.

Effects of Leakage (1) - Monomethylhydrazine is somewhat more toxic than UDMH or hydrazine; its flammability characteristics are similar. MMH vapors detonate on ignition by static sparking. Iron rust promotes the catalytic decomposition, resulting in spontaneous ignition. For effects of space vacuum, see the discussed effects of leakage for hydrazine.

---

\*Parenthetical enclosures refer to the Propellant Rating Chart, Page 1-11.

TABLE 1-3. MONOMETHYLHYDRAZINE

COMPATIBILITY OF MATERIALS  
FOR SHORT TERM USE<sup>a</sup>

<u>MATERIAL</u>	<u>TEMPERATURE</u>
<u>ALUMINUM ALLOYS</u>	
3003	
5052	
5154	
6061-S	Satisfactory below 160°F
<u>MISCELLANEOUS ALLOYS</u>	
Titanium 6Al-4V	
Columbium C 103	
<u>STEELS</u>	
303 Stainless Steels	
304 Stainless Steels	
321 Stainless Steels	
347 Stainless Steels	
17-7 PH Stainless Steels	
4130 <sup>b</sup>	Satisfactory below 160°F
<u>BRAZES</u>	
Aerobrazo-T	
82 Au-18 Ni Braze Alloy	
<u>PLASTICS AND ELASTOMERS</u>	
Natural Rubber	Intermediate <sup>d</sup> below 160°F, 1 wk
Neoprene	Intermediate <sup>d</sup> below 160°F, 1 wk
Polyethylene (high density)	Good <sup>c</sup> below 160°F, 1 wk
Silicone Rubber	Intermediate <sup>d</sup> below 160°F, 1 wk
Teflon	Intermediate <sup>d</sup> below 160°F, 1 wk
Some unplasticized trichlorofluoroethylenes	
Butyl Rubber	Below 95°F

a Two to four weeks.

b Very susceptible to rusting.

c Negligible weight change (0.5%); no change in elasticity.

d Moderate weight change (0.5 - 2.5%); change in elasticity of 25-40%.

## UNSYMMETRICAL DIMETHYLHYDRAZINE $(\text{CH}_3)_2\text{NNH}_2$

UDMH is a derivative of hydrazine and is a moderately toxic, shock insensitive, storable liquid propellant. It exhibits excellent thermal stability and resistance to catalytic breakdown. It has a lower freezing point and higher boiling point than hydrazine.

Due to an extremely wide flammable range in air and the possibility that explosive vapor-air mixtures may be found above the liquid, UDMH should not be exposed to open air. Instead, it should be stored in a closed container under a nitrogen blanket.

At the present time test results imply that lubricants which are compatible for use with UDMH are still in the development stage. Lubricants such as APS C-407, Parkerlube 6PB, Molykote, and Peraline 12-4 may cause decomposition, while petroleum and silicone greases which do not react but are dissolved by the UDMH.

Table 1-4 lists those materials which are considered to be compatible with UDMH for long-term application.

### PHYSICAL PROPERTIES

Specific Gravity	0.785 (60°F)
Molecular Weight	60.078
Freezing Temperature °F	-72
Normal Boiling Point °F	146
Critical Temperature °F	480
Critical Pressure psia	880
Heat of Vaporization Btu/lb <sub>m</sub>	250.7

## Discussion of Problem Areas -

### Unsymmetrical Dimethylhydrazine (UDMH)

Organic Polymers (2)\* - In view of the variable nature of the service in which organic polymeric materials might be employed, it is difficult to be specific regarding their performance. Because of the excellent solvent properties of UDMH, most polymeric materials prove unsatisfactory. Numerous plastics and rubbers are rated "good" (suitable for repeated short-term exposure). Of the references cited, all indicated that Teflon was not attacked by UDMH and rated it as suitable for long-term storage or exposure.

Wet and Dry Lubes (2) - Because of the excellent solvent properties of UDMH, most lubricants are incompatible. Several lubricants, litharge, glycerine paste, X-Pando, and Q-Seal, are compatible and have been employed for pipe threads and other similar applications involving minimum contact with UDMH. Petroleum and silicone greases do not react, however, they tend to "wash-out" under dynamic conditions. DuPont's fluorinated grease, Krytox 240 is compatible.

Lubricity (1) - UDMH was found to have unsatisfactory lubricating properties when subjected to bearing and gear tests. The performance was thought to be related to the excellent solvent and reducing properties of UDMH.

Radiation Tolerance (2) - See hydrazine.

Effects of Leakage (2) - Being chemically similar to hydrazine, the same hazards are encountered as with that material. The maximum allowable concentration is somewhat less (0.5 ppm) than hydrazine. It is flammable in air, hypergolic in the presence of oxidizers; its excellent solvent properties may cause malfunction of components constructed of incompatible organic plastics with which it may come in contact. For space conditions, see the discussion on effects of leakage for hydrazine.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

TABLE 1-4. UNSYMMETRICAL DIMETHYLHYDRAZINE (UDMH)

COMPATIBILITY OF MATERIALS FOR  
LONG TERM APPLICATIONS (NOTE 1)

<u>MATERIALS</u>	<u>TEST TEMP °F</u>
<u>ALUMINUM ALLOYS<sup>a</sup></u>	
1100	160
1100-H14	145
1260-H14	145
2014	140
2017	75
2024	75
2024-T3	145
3003	86
3003-H14	145
3004-H34	145
5052	160
5052-H34	145
5086	85
5086-H34	145
5154-H34	145
5456	140
6061	160
6061-T6	145
6063-T6	145
7075	160
7075-T6	145
356	160
356-T6	85
43	145

a Aluminum is attacked by UDMH if water is present, with the attack being directly proportional to the amount of water present.

UNSYMMETRICAL DIMETHYLHYDRAZINE (UDMH) (Continued)

<u>MATERIALS</u>	<u>TEST TEMP °F</u>
<u>STAINLESS STEEL</u>	
302	160
303	160
304	160
316	140
321	160
347	160
410	160
416	250
422	145
17-7 PH	160
Carpenter 20	140
PH15-7 Mo	85
A286	85
AM350	
AM355 CRT	100
17-4 PH Cond H925	
17-4 PH Cond H1151	
<u>MISCELLANEOUS METALS</u>	
Copper	145
Hastelloy (B, C, X, F)	145
Haynes Alloy 25	140
Inconel	140
Magnesium Alloy AZ-31B-O	85
Magnesium Alloy AZ-31B, AZ-61A	130
Magnesium Alloy AZ-92-F	85
Mild Steel	140
4130 Steel	85
Monel	140
Nickel	140

UNSYMMETRICAL DIMETHYLHYDRAZINE (UDMH) (Continued)

<u>MATERIALS</u>	<u>TEST TEMP °F</u>
<u>MISCELLANEOUS METALS (Cont.)</u>	
Tantalum	140
Titanium Alloy 6Al-4V	
Titanium A-55 (Commercially Pure)	145
Titanium Alloy B-120VCA	145
Titanium Alloy C-120AV	160
Columbium C 103	
<u>PLASTICS AND ELASTOMERS</u>	
Butyl Rubber	140
Kel-F (Unplasticized)	140
Nylon	130
Polyethylene	80
Teflon (FEP)	160
Teflon (TFE)	160
<u>MISCELLANEOUS MATERIALS</u>	
Delanium	75
Glass Pyrex	160
Graphitar No. 2	140
Graphite	75

Note 1: Materials listed above are rated compatible based on a corrosion rate of less than 1 mil per year and the material does not cause decomposition, and is free from impact sensitivity. Non-metals are rated for satisfactory service for general use.

## AEROZINE-50 (50% HYDRAZINE/50% UDMH)

The storable fuel blend of a nominal 50 percent by weight of hydrazine ( $N_2H_4$ ) and 50 percent by weight of unsymmetrical dimethylhydrazine (UDMH) is a hygroscopic (readily capable of absorbing moisture) liquid which is insensitive to mechanical shock but flammable in both liquid and vapor states. When combined, there is a definite tendency for each to dissolve in the other. Since the vapor above the fuel blend at 72°F is predominantly UDMH, the flammability hazards of the mixture are the same as for UDMH. Explosion hazards can be minimized, however, by maintaining the fuel in closed systems.

Most common metals which might be used for valve construction, with the exception of the magnesium and copper alloys, are compatible with the 50/50 fuel blend providing they are clean. Care should be exercised when using ferrous alloys because of the possible catalytic decomposition of the fuel blend due to rust. Titanium alloy 6AL-4V has been reported non-compatible based on hydrazine decomposition rate limits (see specific Reference 128).

Table 1-5 lists those materials which are considered to be compatible with the 50/50 fuel blend for long term application.

### PHYSICAL PROPERTIES

Molecular Weight	41.797
Freezing Temperature °F	18
Normal Boiling Point °F	170
Critical Temperature °F	634
Critical Pressure psia	1696
Heat of Vaporization Btu/lb <sub>m</sub>	425.8

Discussion of Problem Areas -  
Aerozine-50 (N<sub>2</sub>H<sub>4</sub> and UDMH)

Organic Polymers (2)\* - Most organic polymers either dissolve or deteriorate in the presence of Aerozine-50. Teflon has proved most successful for some uses; butyl rubbers are being used for most dynamic seals.

Wet Lubes (2) - Certain silicone-base greases, polyglycol oils, and powdered Teflon have been used for limited service. The fluorolubes react; many dissolve. DuPont's fluorinated grease, Krytox 240 is compatible.

Dry Lubes (1-2) - Graphite has been used, but found susceptible to washing out under dynamic conditions. Electrofilm 2406 and 1000 have shown resistance to propellant attack. However, lubricity after exposure is unknown.

Lubricity (1) - Being a mixture of hydrazine and UDMH, Aerozine-50 would have properties similar to the two components.

Viscosity (2) - Because of the high freezing temperature (18°F) of the Aerozine-50 mixture and the rapid increase in viscosity as this temperature is approached, it is desirable to maintain fuel temperature well above this point to insure proper flow characteristics.

Radiation Tolerance (2) - See hydrazine.

Effects of Leakage (1-2) - The leakage effects will be similar to those discussed for the components of the fuel blend.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

TABLE 1-5. AEROZINE-50 (50% HYDRAZINE/50% UDMH)

COMPATIBILITY OF MATERIALS FOR  
LONG TERM APPLICATION

<u>MATERIAL</u>	<u>TEST TEMP °F</u>
<u>ALUMINUM ALLOYS</u>	
1100	55-60
2014-T4	55-60
*2014-T6	160
*2024-T6	160
2219-T81	55-60
3003-H14	150
5086-H36	160
5254-F	160
5456-H24	55-60
5456-H321	160
6061-T6	160
6066	160
*7075-T6	160
356	160
Tens 50	160
<u>STAINLESS STEEL</u>	
303	160
304L	
*316	160
321	160
347	160
PH15-7 Mo (Cond. A)	160
*17-4 PH	160
17-4 PH (Cond. A)	160
*AM355 (Cond. H)	160
*AM350 SCT	160
*410H and T	160
440C	160

\*Disagreement exists among authorities as to acceptability.

AEROZINE-50 (Continued)

<u>MATERIALS</u>	<u>TEST TEMP °F</u>
<u>OTHER METALS</u>	
*Anodize Coatings on Aluminum	160
Berlyco 25	160
Cadmium Plate	60
Columbium C 103	
Non-porous Chromium Plating	55-60
Gold Plate	160
Monel	80
Nickel	160
Non-porous Electrolytic Nickel Plating	55-60
*Electroless Nickel Plating	160
Silver	55-60
Silver Solder	60
Stellite 6K	160
*Stellite 21	160
Stellite 25	160
A286 Steel (rust free)	55-60
*1020 Steel (rust free)	55-60
4130 Steel (rust free)	55-60
Ti Alloy A110-AT	160
Ti Alloy C 120AV	160
Ti Alloy B 120VCA	55-60
**Titanium 6Al-4V	110
Tin	55-60
Titanium Carbide (Ni Binder)	160
Tungsten Carbide	160
<u>PLASTICS AND ELASTOMERS</u>	
Enjay 035	80
Fluorobestos filled with Asbestos	55-60
Fluorogreen	55-60

\*Disagreement exists between authorities as to acceptability.

\*\*Reported noncompatible based on limits of decomposition rate of hydrazine, see specific Reference 128.

AEROZINE-50 (Continued)

<u>MATERIALS</u>	<u>TEST TEMP °F</u>
<u>PLASTICS AND ELASTOMERS (Cont.)</u>	
Hadbar SB800-71 Rubber	160
Kel-F 300 (15% Glass Filled)	75
Kel-F 300 (Unfilled)	75
Parker B496-7 Rubber	160
Low-density Polyethylene	60
Polypropylene	160
Precision Rubber 9257, 940, X559	80
Teflon (FEP)	70-80
Teflon (TFE)	70-80
Teflon filled with Graphite	55-60
Teflon filled with Molydisulfide	55-60
Teflon filled with Asbestos	55-60
Zytel 31 Nylon	70-80
Zytel 101 Nylon	60
<u>LUBRICANTS AND GRAPHITE</u>	
Flake Graphite	80
Graphitar 39	70-80
Graphitar 84	70-80
Graphitar 86	160
Microseal 100-1 (dry lube)	80
National Carbon CCP-72	160
Purebon P3N	160
Reddy Lube 100	80
Reddy Lube 200	80
Silicone DC 11	80
Water Glass Graphite	80
Krytox 240	80

AEROZINE-50 (Continued)

MATERIALS TEST TEMP °F

---

CERAMICS

Rockflux	75
Sauereisen P-1	60
Sauereisen 31	60
Temporall 1500	60

ADHESIVES

Epon 422	80
----------	----

## PENTABORANE ( $B_2H_9$ )

Pentaborane is a high energy fuel which is an extremely hazardous pyrophoric compound which is insensitive to mechanical shock and in an inert atmosphere, exhibits satisfactory (to 77°F) thermal stability. It exhibits hypergolicity with the high-energy oxidizers, and behaves as a strong reducing agent in oxidation-reduction reactions.

The boranes have a pungent, sickeningly sweet odor, and are toxic to a high degree. Toxic concentrations are reached before any odor can be detected and special detectors must be used. Any substance which will function as a potential oxidizer will react with the boranes. Materials such as water, air, metal oxides, and reducible organic compounds are in this category. For this reason, considerable care should be exercised in the selection of materials to be used with pentaborane, so as to avoid use of any organic compounds containing a reducible functional group. Teflon, Viton, Kel-F, and Fluorosilica rubber are among the compatible polymers.

Organic materials such as gaskets, lubricants, and seals must be chemically inert if they are to be used. High-porosity castings and gaskets should be avoided. Because of the ability of the boranes to reduce some metal oxides, welded joints should be avoided in pipe constructions. To date, no metals are known to be incompatible with pentaborane at ordinary room temperatures and atmospheric pressures. Pentaborane forms shock-sensitive mixtures with many highly chlorinated organic compounds such as carbon tetrachloride or trichloroethylene and with organic compounds containing reactive carbonyl groups such as acetone, other ketones and aldehydes. Thus, strict house-keeping rules and thorough solvent removal procedures must be employed when cleaning components such as valves, etc., in propellant systems using pentaborane.

Table 1-6 lists those materials which are considered to be compatible with the pentaborane for long-term application.

## PHYSICAL PROPERTIES

Molecular Weight	63.17
Freezing Temperature °F	-52
Normal Boiling Point °F	136
Critical Temperature °F	435
Critical Pressure psia	557
Heat of Vaporization Btu/lb <sub>m</sub>	219
Density, gm/cc	0.643 (32)

### Discussion of Problem Areas - Pentaborane (B<sub>5</sub>H<sub>9</sub>)

Ceramics (2)\* - Because of their strong reducing properties, pentaboranes will reduce some metal oxides and also precipitate some heavy metals from solutions of their salts.

Wet Lubes (2) - A number of lubricants are satisfactory for short-term service; however, pentaborane, being soluble in these lubricants, presents problems of cleaning, disposal, and "wash-out" of lubricant from components. Generally, non-lubricated valve designs acceptable for use with other toxic and corrosive liquids may be used successfully with the boranes.

Effects of Leakage (1) - The toxicity of the boranes, with a tentative threshold limit of 0.005 ppm, would constitute a severe hazard to humans in the event of leakage. The pyrophoricity of pentaborane in air has been a controversial subject; however, it is generally agreed pentaborane must be treated as if it were spontaneously flammable in air under most conditions. For leakage in space, see the discussion on effects of leakage for hydrazine.

Hard Seats (2) - Because of the necessity of eliminating all leakage, soft seat materials compatible with the boranes are recommended. Particle

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

migration occurring where valve parts rub on plastic seals may cause problems of seal life, plugging or opening and fouling up close tolerance fits.

TABLE 1-6. PENTABORANE  
 COMPATIBILITY OF MATERIALS FOR  
 LONG TERM APPLICATIONS

<u>MATERIAL</u>	<u>TEMPERATURE °F</u>
<u>ALUMINUM ALLOYS</u>	
2024-T3	75
3003-H14	75
5052-S	75
6061-T6	75
7075-T6	75
356-T6	75
Cadmium Coated Aluminum	75
Chromated Aluminum	75
<u>STAINLESS STEELS</u>	
302	75
304	75
321	75
347	75
<u>OTHER METALS</u>	
Brass	75
Cadmium Plated Steel	75
Copper	75
Hastelloy No. X-1258	75
Iron	75
K-Monel	75
Magnesium Alloy, AZ63A	
Magnesium Alloy, AZ318	

PENTABORANE (Continued)

<u>MATERIAL</u>	<u>TEMPERATURE °F</u>
<u>OTHER METALS (Cont.)</u>	
Monel, Soft, M-8330-B	
Nichrome "V"	75
Steel	75
Titanium Alloy C-110M	75
Titanium Alloy C-130AM	75
<u>NON-METALS</u>	
Fluoroflex T	75
Fluorosilicone Rubber	75
Graphitar No. 39	75
Graphite Impregnated Asbestos	75
Kel-F No. 5500	75
Kel-F & Glass Cloth	75
Kel-F & Glass Yarn	75
Molybdenum Disulfide	75
Pure Carbons	75
Rockwell Nordstrom Lube No. 921	75
Teflon	75
Viton	75
Viton A	75

Note 1: Materials listed above are rated compatible based on corrosion rate of less than 1 mil per year and the material does not cause decomposition, and is free from impact sensitivity. Non-metals are rated for satisfactory service for general use.

- PENTABORANE

INCOMPATIBLE MATERIALS

INCOMPATIBLE NON-METALS

INCOMPATIBLE LUBRICANTS

Foamglass

Rockwell Nordstrom Lube 356

Dow Corning R7002 Foam

Rockwell Nordstrom Lube 833

Dow Corning R7003 Foam

Rockwell Nordstrom Lube 860

Napco F10 Foam

Rockwell Nordstrom Lube 852-S

Napco B49

Rockwell Nordstrom Lube P-21

Natural Rubber

Rockwell Nordstrom Lube P-55

Nitrile Rubber on Nylon

Rockwell Nordstrom Lube 942-S

Dow Corning 9283 Rubber

Saran

Nylon

Mylar

Tygon

Rubatex G-2027 N

Rubatex R-103 J

Fiberfrax No. XSW

Fiberfrax No. SIF

Dow Corning Silastic 80-24-480

Garlock Silastic 250

## EARTH STORABLE PROPELLANTS (Continued)

### OXIDIZERS

#### NITROGEN TETROXIDE (NTO) ( $N_2O_4$ )

Nitrogen tetroxide is a highly reactive, toxic oxidizer, insensitive to all types of mechanical shock and impact. It is a dense brown or green liquid, depending on the NO content, and although it is nonflammable itself, it will support combustion and will react hypergolically upon contact with certain high-energy fuels such as the hydrazines.  $N_2O_4$  can cause spontaneous ignition with common materials such as leather and wood. The fumes are extremely toxic. Nitrogen tetroxide is used as a storable propellant oxidizer and is used in the Titan II missile and many spacecraft propulsion systems.

Dry nitrogen tetroxide is compatible with many metals and alloys used in space vehicle construction. However, water contamination present in the nitrogen tetroxide causes the formation of nitric acid, which is corrosive to many metals; therefore, materials selected for use in  $N_2O_4$  should be compatible with nitric acid as well. Gold and a few types of stainless steel have been satisfactory as materials in nitric acid storage containers and so should be best for long-term  $N_2O_4$  containment.

In general, aluminum alloys and stainless steels are most suitable for use as materials in contact with dry nitrogen tetroxide. The resistance to corrosion exhibited by the various aluminum alloys is a function of water content in the nitrogen tetroxide and the aluminum content of the alloy in question. As the water content in the nitrogen tetroxide exceeds 0.3 percent, highly alloyed aluminum (e.g., 7075 Aluminum Alloy) shows a sharp increase in corrosion rates as contrasted by the purer aluminum alloys (e.g., 1100 Aluminum Alloy), whose increase in corrosion rate is much less pronounced. For stainless steel, however, the corrosion rate in nitrogen tetroxide varies directly with water content.

Stress corrosion of titanium tanks has been experienced with the use of Mil Spec grade  $N_2O_4$  (MIL-P-26539A). Addition of small amounts of NO (>1.0%)

in order to scavenge the dissolved oxygen has given dramatic evidence of reducing the incidence of stress corrosion in titanium tanks containing NTO. Shot peening the inside of titanium tanks in order to produce a surface under compression also has been effective in reducing corrosion by brown NTO. Thus, the true nature of the factors producing stress corrosion in titanium by NTO are still incompletely resolved. Copper, magnesium and nickel alloys are not recommended for use because of their poor corrosive resistance to nitric acid.

The chloride content of NTO may also give rise to pitting corrosion, which is a particularly serious matter with respect to very thin walled containers and/or bellows which must have long-term service life. This, coupled with the demonstrated problems of nitric acid production from moisture present and the uncertain role of  $O_2$  in NTO, clearly dictate that the aerospace designer should consider his choice of materials carefully in order to minimize failure due to materials incompatibility.

Most nonmetallic materials show poor resistance to nitrogen tetroxide and are considered unsatisfactory for use. Reaction of nitrogen tetroxide with non-metals can result in decomposition of the materials, causing degradation or complete destruction, or it can alter the physical properties such as volume and/or hardness of the material. In certain cases, this reaction can be advantageous as in the case of butyl rubber seals. Reaction of the butyl rubber with NTO results in tackiness and swelling which seems to augment the sealing characteristics of the material. This type of seal has been reported successful in field service for over one year. The propellant may also be affected in its physical characteristics. Of all the plastics available for use, Teflon and Teflon products exhibit the best resistance to nitrogen tetroxide; however, nitrogen tetroxide permeates and is absorbed by Teflon. Results from permeability tests conducted show that the permeability rate for Teflon TFE is three times greater than Teflon FEP. Under certain conditions, Teflon in conjunction with NTO has caused increased corrosion rates. This may be due to the water content of NTO; however,

no long-term storage data are available. Recently, the cyclized polybutadienes (HYSTL) and some of the nitroso copolymers ( $\text{CF}_3\text{NO}/\text{C}_2\text{F}_4$ ), and terpolymers ( $\text{CF}_3\text{NO}/\text{C}_6\text{F}_5\text{NO}/\text{C}_2\text{F}_4$ ) have shown promise as organic materials for use with NTO.

Another method of circumventing seal problems with NTO has been to design the O-ring groove such that less than 2% seal exposure is allowed. The swelling of the polymer then closes the gap and does not allow further interaction of the seal with the NTO. It has been claimed that over ten months storage life without leaks has been accomplished by this procedure.

Most lubricants in contact with nitrogen tetroxide are either dissolved and washed off or undergo a substantial change in hardness. DuPont's fluorinated grease, Krytox 240 and several dry lubricants such as Molykote Z, Drilube 703, and Electrofilm 66-C have been rated as compatible with nitrogen tetroxide. Microseal 100-1 is rated as compatible with nitrogen tetroxide and does not undergo any physical changes.

The formation of a gelatinous material has been reported and occurs during high velocity flow on  $\text{N}_2\text{O}_4$  through small clearances. Investigation of this phenomena is being carried out at several agencies and companies. The formation of the clogging material seems to be correlatable to various impurities in  $\text{N}_2\text{O}_4$  introduced either during the manufacture, storage, or conditioning of the oxidizer. The materials that appear to be responsible are metal- $\text{N}_2\text{O}_4$  reaction products and, possibly, organic species formed subsequent to the actual usage of the  $\text{N}_2\text{O}_4$ . A more comprehensive discussion of the problem is found on page 2-1 and Reference 1 of that section.

Table 1-7 lists those materials which are considered to be compatible with nitrogen tetroxide for long-term application. It should be noted that temperatures, temperature ranges and percent of water contamination are

parameters of conducted tests and are not necessarily temperature limits or moisture content limits.

#### PHYSICAL PROPERTIES

Specific Gravity	1.49 (60°F)
Molecular Weight	92.016
Freezing Temperature °F	11.8
Normal Boiling Point °F	70
Critical Temperature °F	316
Critical Pressure psia	1470
Heat of Vaporization Btu/lb <sub>m</sub>	178.2

Discussion of Problem Areas -

Nitrogen Tetroxide ( $N_2O_4$ )

Organic Polymers (2)\* - No completely satisfactory non-metallic material has yet been found for use as valve seats. Most organic polymers have some disadvantages, principally that of swelling when exposed to  $N_2O_4$ . Polymers of promise have not been fully characterized as yet in NTO service.

Wet Lubes (2) - Most lubricants absorb  $N_2O_4$ , rendering them useless. Certain silicone greases have limited use because they tend to absorb  $N_2O_4$  slowly. DuPont's fluorinated grease, Krytox 240 has been rated compatible.

Dry Lubes (2) - A number of dry lubricants, including graphite and molybdenum disulfide, show good compatibility, but tend to wash out under flow conditions.

Effects of Leakage (1) -  $N_2O_4$  is a highly toxic substance and thus is classified as a poison on ICC regulations. The maximum allowable concentration of 5 ppm in air is accepted by the American Conference of Government Hygienists. Because of its corrosive nature and reaction with, or absorption in organic materials, adjacent components may easily be affected by  $N_2O_4$  leakage. The hypergolic nature of  $N_2O_4$  with many fuels constitutes a potential fire problem if leakage allows the two propellants to mix. Effects of leakage in space are discussed under the propellant hydrazine.

Soft Seats (1-2) - A limited number of non-metallic materials are satisfactory for short-term use, but it is recommended that polymeric seals be avoided whenever possible. Teflon and Kel-F are the more resistant plastic materials. Teflon, while compatible with  $N_2O_4$ , absorbs  $N_2O_4$  vapors slowly. The resultant swelling may result in component malfunction.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11

TABLE 1-7. NITROGEN TETROXIDE  
 COMPATIBILITY OF MATERIALS FOR  
 LONG TERM APPLICATION

MATERIAL	TEST TEMP °F	% MOISTURE CONTENT
<u>ALUMINUM ALLOYS</u>		
1060	80	0.2 to 1.0
1100	60	0.3
1100-0	60	0.2 to 1.0
2014-T6	60	0.2 to 1.0
2014-T6 (Hardas Anodize)	60	
2014-T6 (H <sub>2</sub> SO <sub>4</sub> Anodize)	65	
2014-T6 (Iridite)	60	
2014-T6 (Welded)		
2024	140	0.2 to 1.0
2024-0	150	
2219-T6	60	
2219-T81	60	0.2 to 1.0
3003-H14	150	0.6
4043	80	
5052	130	0.2 to 1.0
5086-H34	165	
5086-H36	65	
5254-F	65	
5456	60	
5456 H-24	60	0.2 to 1.0
5456 H-24 (Iridite)	60	
5456 H 321	65	0.2 to 1.0
6061	130	
6061-T6	130	0.2 to 1.0
6061-T6 (Welded)	65	
6066	65	
7075	60	
7075-0	150	
7075-T6	150	

NITROGEN TETROXIDE (Continued)

MATERIAL	TEST TEMP °F	% MOISTURE CONTENT
<u>ALUMINUM ALLOYS (Cont.)</u>		
7075-T6	60	0.2 to 1.0
356	80	
356-T6 (See Incompatible Listing)	80	0.2 to 1.0
Tens 50	65	
<u>STAINLESS STEELS</u>		
410	110	
416	110	
430	110	
440C	110	
302	100	
303	80	0.2 to 1.0
304	140	0.2 to 1.0
304L	165	3.2
316	65	
321 (Incl. Welded)	60	3.0
347 (Incl. Welded)	100	10.0
17-4PH (Cond. A)	65	
17-4PH (H1000)	100	0.3
17-4PH	65	3.0
17-7PH (TH950)	100	
17-7PH (RH950)	100	
AM-350 (Annealed)	100	10.0
AM-355 (Cond. H)	100	
<u>MISCELLANEOUS METALS</u>		
Chromium Plate	60	
Haynes Stellite 1	100	
Haynes Stellite 12	100	
Haynes Stellite 6K	65	
Haynes Stellite 21	65	
Haynes Stellite 25		

NITROGEN TETROXIDE (Continued)

MATERIAL	TEST TEMP °F	% MOISTURE CONTENT
<u>MISCELLANEOUS METALS (Cont.)</u>		
Haynes Stellite 93	100	
Gold	75	
Gold Plate	60	
Cast Iron	80	
Carbon Steel	80	
Mild Steel	140	
1020 Steel	130	
A-285 (Grade C)	165	3.2
8630 Steel	140	
A286 (Annealed) Steel	100	
A286 (Aged)	60	
PH15-7 Mo (Cond. A)	165	3.2
Magnesium, 100A	60	
Magnesium, HM21A-T8	60	
Nickel Electroplate	60	
Electroless Nickel Plate	100	
Inconel	65	
Monel	65	
Ni-Span-C	60	
Inconel X	75	
Platinum	75	
718 Braze 6061-T6A1	65	
Pure Tin Solder on 303SS	65	
Easy Flo Braze on 347SS	65	
Tantalum	75	
Tin	80	
Columbium	75	

NITROGEN TETROXIDE (Continued)

MATERIAL	TEST TEMP °F	% MOISTURE CONTENT
<u>NON-METALS</u>		
Microseal 100-1 on 2014-T6A1	100	
Teflon TFE	75	
Teflon FEP	160	0.2 to 1.0
Teflon Graphite	75	
Teflon MoS <sub>2</sub>	75	
Teflon Asbestos	75	
Teflon Glass Filled	80	
Alcar 191	67	
Armalon 7700	75	
Armalon 7700B	75	
Fluorobestos	60	
Fluogreen	60	
Genetron GCX-3B	80	
Genetron XE-2B	65	
Kynar	80	
Raythene N. (Irradiated)	65	
Tedlar	67	
<u>LUBRICANTS</u>		
		0.2
XC 150	65	
Molykote Z	60	
Microseal 100-1	67	
Lox Safe	80	
Flake Graphite	80	
Graphitar 2, 14, 39, 50, 86	67	
CCP-72		
Fluorolube MG6DO	80	
Fluoroethane G	80	
Krytox 240	80	

NITROGEN TETROXIDE (Continued)

MATERIAL	TEST TEMP °F	% MOISTURE CONTENT
<u>SEALANTS AND POTTING COMPOUNDS</u>		0.2
Reddy Lube 100	160	
Reddy Lube 200	160	
Waterglass-Graphite	67	
Oxylube Sealant	80	
Teflon Tape (Unsintered)	80	
Crystal M&CF	60	
4-3	60	
Sauereisen P-1	60	
Proseal 333	60	

NITROGEN TETROXIDE

INCOMPATIBLE MATERIALS - Note 1

INCOMPATIBLE METALS

Cadmium  
Lead  
356-T6 Aluminum Alloy (110°F, 1.9 yr)  
Copper  
K-Monel  
Silver  
Sintered Molybdenum  
Zinc  
Zirconium  
Cobalt  
Hastelloy B (110°F)  
Magnesium A231C (110°F)

INCOMPATIBLE NON-METALS

ELASTOMERS

Natural Rubber  
Butyl Rubber  
Buna-N  
Neoprene  
Viton  
Chloroprene  
Ethylene Propylene  
Silicones  
Kel-F  
Hypalon  
Polyurethane

INCOMPATIBLE NON-METALS

PLASTICS

Kel-F  
Polyethylene  
Nylon  
Mylar  
Polyvinylidene Chloride  
Acrylics  
H-Film  
Polypropylene  
Silicone Laminates  
Epoxy Laminates  
Phenolic Laminates  
Polyester Laminates  
Polyvinyl Chloride  
Epon Resins  
Acetal Resins  
Vinyl

NITROGEN TETROXIDE

INCOMPATIBLE MATERIALS Note 1

INCOMPATIBLE NON-METALS

LUBRICANTS

DC 11  
DC 33  
DC 510  
DC 550  
Molykote M-8800  
Molykote X-106  
Drilube 7  
Drilube 1  
Surfkote N-1284  
Rayco 30  
Electrofilm 66C  
Johns Manville No. 60

INCOMPATIBLE SEALANTS  
AND POTTING COMPOUNDS

Polysulfides  
RTV Silicones  
Epon Resins  
Polyesters  
Polyurethanes

Note 1 - Plastics, elastomers and sealants are generally listed by chemical family. While not all commercial products have been tested, it has generally been determined that these chemical families are incompatible. Lubricants included are rated on basis of wash-out tendencies or failure to maintain lubricity after propellant exposure.

## CORROSION OF MATERIALS WITH IMPURE N<sub>2</sub>O<sub>4</sub>

TRW Systems performed corrosion testing using engineering materials at elevated temperatures with impure N<sub>2</sub>O<sub>4</sub> for NASA (General Reference No. 18). It was the intent of the NASA program to enhance corrosion, not suppress it, for purposes of determining the effect of corrosion products on contaminating the N<sub>2</sub>O<sub>4</sub>. However, this information and test data generated is valuable, since it represents the only known matrix testing done showing the effects of impurities in the propellant on corrosion. The work also included a different rating analysis on reporting corrosion not generally used by investigators. The test specimens were unstressed samples of 6061-T6 Aluminum, 347 Stainless Steel and Ti-6Al-4V Alloy subjected to one and four month durations at 165°F. The specimens measured nominal 0.025" thickness x 3/4" x 4" long and were placed in glass capsules containing the N<sub>2</sub>O<sub>4</sub> and sealed. The impurities individually added to the N<sub>2</sub>O<sub>4</sub> are listed as follows:

<u>ADDED IMPURITY</u>	<u>PRE-STORAGE CONCENTRATION, % w/w</u>
Chlorine (Cl <sub>2</sub> )	0.10
Water (H <sub>2</sub> O)	0.91
Oxygen (O <sub>2</sub> )	0.04
Nitrosyl Chloride (NOCl)	0.025
Nitrosyl Chloride + O <sub>2</sub> (NOCl + O <sub>2</sub> )	0.054 NOCl + 0.050 O <sub>2</sub>

The effects of the selected impurities in the corrosivity of N<sub>2</sub>O<sub>4</sub> showed no significant increase in dissolved metal content with time. Of all the impurities, water resulted in the greatest increase in corrosivity. Tables 1-8, 1-9, and 1-10, present a visual description of the appearance of the one and four month specimens. Tables 1-12 through 1-14 lists the results of the corrosion testing for all three metals. Table 1-11 gives the definitions of the rating analysis used in the corrosion results of Tables 1-12 through 1-14. The rating analysis is taken from Champion, General Reference 1.

### 6061-T6 Aluminum

The water contaminated  $N_2O_4$  caused the greatest weight change in the aluminum and also caused the greatest structural damage to the metal. A significant decrease in water content after the four month storage period is noted. The samples were covered with a very thick, white coating which was easily removed by washing. Greatest damage appeared to be concentrated in the rolling marks left in the metal during sheet fabrication. Oxygen and  $O_2/NOCl$  impurities caused general dark discoloration and pitting, with no deposit buildup. In the case of the oxygenated  $N_2O_4$ , no change in oxygen content occurred after one month storage whereas four month storage apparently resulted in  $O_2$  depletion. An unexpectedly large negative oxygen value was obtained for the one month  $O_2/NOCl$  fluid, reported as a positive nitric oxide (NO) content. Apparently either an impurity was present or spurious reaction occurred to cause consumption of oxygen. It is not possible that the oxygenation apparatus leaked, however, it is conceivable that an error in weighing caused the anomalous value. No change in  $NOCl$  content was detectable in the  $O_2/NOCl$  fluid after one or four months.

Of interest is the very small degree of corrosion caused by the  $Cl_2$  and  $NOCl$  contaminated  $N_2O_4$ , because it has been postulated that the chloride ion and/or molecular chlorine may be one of the principle species responsible for metal degradation in  $N_2O_4$ . The slight decrease in chlorine content is not considered significant in view of the fact that the specimens were not corroded significantly. Furthermore, they were extremely similar to the specimens exposed to uncontaminated  $N_2O_4$ . The larger values for  $NOCl$  content after storage are not particularly surprising as many instances of chloride buildup are reported in the literature.

### 347 Stainless Steel

The most severe attack was obtained in the  $O_2$ ,  $H_2O$ , and  $O_2/NOCl$  contaminated  $N_2O_4$  test fluids. Crystals formed on the specimen surface in the  $H_2O$  contaminated  $N_2O_4$  were of a green color when viewed by reflected light, but were red when viewed by transmitted light. The crystals formed in the

$O_2/NOCl$  contaminated  $N_2O_4$  were red when viewed by either light mode, and in addition, reacted vigorously (effervesced) when exposed to either atmospheric oxygen or water vapor. A significant water decrease and complete consumption of oxygen in the stainless steel tests were the most notable changes in contaminant additive. Once again an anomalous positive NO content results for the one month fluid contaminated with  $O_2/NOCl$ . The chlorine and  $NOCl$  contents changed moderately and insignificantly, respectively.

The general mode of corrosion for the stainless steel specimens was primarily minute pitting. Some surface roughening was also evident, however, since the objective of this task was to enhance, not suppress corrosion, none of the specimens were passivated prior to storage. The stainless steel specimens, however, did passivate to an extent, as can be noted from the thickness changes in the one and four month storage samples.

#### Ti-6Al-4V Alloy

The titanium alloy specimens were the least affected of any of the alloy systems by the corrosive fluids. The specimens appear somewhat darker than normal due to their high reflectivity. Some surface discoloration was evident on the specimens but they did not appear to be affected otherwise. No evidence of pitting or general attack was found in any of the specimens, and the only effect of the corrosive fluids noted was to slightly roughen the surface. In general, slight to moderate changes in contaminant level occurred with the exception of the four month  $O_2$  and water concentrations which decreased markedly, though no corresponding increase in corrosion was found.

TABLE 1-8. Physical Appearance of One and Four Month Aluminum Specimens Prior To and After Removal of Propellant ( $N_2O_4$ )

Added Contaminant	Appearance of One Month Capsules		Appearance of Four Month Capsules	
	Before Propellant Removal	After Propellant Removal	Before Propellant Removal	After Propellant Removal
None	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	Some oily substances on bottoms of tubes.
$H_2O$	Specimens covered with white salts.	Specimens covered with white salts.	White crystals on bottom of tubes. Specimens covered with white salts.	Specimens covered with white salts. Some crystals on walls and bottoms of tubes.
$O_2$	Slight spotted discoloration of specimens.	Slight spotted discoloration of specimens.	Slight discoloration.	Slight spotted discoloration of specimens. Yellow crystals at tops of the tubes. White powdery coating on the walls of the tubes.
$NOCl$	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.
$NOCl + O_2$	Specimens slightly tarnished. One tube contained yellow gelatinous material.	Specimens appeared corroded. One tube had a yellow powdery coating at the top of the tube and a yellowish-brown gelatinous material adhering to the walls.	Slight corrosion of specimens. One tube had yellow-green spots at the top of the liquid.	Specimens were slightly corroded. One tube had yellow particles at the top and a few on the bottom.
$Cl_2$	No noticeable corrosion.	No noticeable corrosion of specimens. One tube had a yellow ring at the $N_2O_4$ liquid-vapor interface.	No noticeable corrosion.	No noticeable corrosion.

TABLE 1-9. Physical Appearance of One and Four Month Stainless Steel Specimens Prior To and After Removal of Propellant (N<sub>2</sub>O<sub>4</sub>)

Added Contaminant	Appearance of One Month Capsules		Appearance of Four Month Capsules	
	Before Propellant Removal	After Propellant Removal	Before Propellant Removal	After Propellant Removal
None	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	Some gelatinous material on the bottoms of the tubes. One tube had yellow coating on wall.
H <sub>2</sub> O	Specimens were black with few black crystals on them. Greenish colored immiscible droplets on sides of tubes.	Specimens were black with few black crystals on them. Greenish colored immiscible droplets on sides of tubes.	Specimens were black with black crystals on them. Greenish colored immiscible droplets on sides of tubes.	Black salt crystals on specimens. Green oily substance on walls and bottom of tubes.
O <sub>2</sub>	Specimens were black. Some yellow crystals on specimens and walls of the tubes. One tube had a few immiscible droplets.	Specimens were black and had some yellow crystals on them and on the tube walls. One tube had green immiscible droplets on it.	Specimens were black. Reddish-brown crystals on walls of tubes above the liquid N <sub>2</sub> O <sub>4</sub> .	Specimens were black. Reddish-brown crystals on the walls of the tubes.
NOCl	No noticeable corrosion.	No noticeable corrosion.	Gelatinous material on the walls of the tubes. No noticeable corrosion of specimens.	Specimens are slightly discolored. Coating on the walls. No sign of gelatinous material.
NOCl + O <sub>2</sub>	Specimens were black. Yellow crystals at the top of the liquid. Clear crystals on the bottoms of the tubes.	Specimens were black. Some yellow crystals and coating on the tops of the tubes.	Specimens were black. One tube had reddish-brown gelatinous material above and 1/2" below the liquid. Some gelatinous material on the tube wall.	Specimens were black and tube walls were coated. One tube had yellow crystals on the wall and the other tube had black spots.
Cl <sub>2</sub>	Clear crystals on the tube walls. No noticeable corrosion of the specimens.	Slight discoloration of specimens.	No noticeable corrosion.	Slight discoloration of specimens. Reddish-brown crystals on bottoms of tubes.

TABLE 1-10. Physical Appearance of One and Four Month Titanium Specimens Prior To and After Removal of Propellant (N<sub>2</sub>O<sub>4</sub>)

Added Contaminant	Appearance of One Month Capsules			Appearance of Four Month Capsules	
	Before Propellant Removal	After Propellant Removal	After Propellant Removal	Before Propellant Removal	After Propellant Removal
	None	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.
H <sub>2</sub> O	Specimens slightly spotted.	Specimens slightly spotted.	Specimens slightly spotted.	No noticeable corrosion.	Small amount of oily substance on bottoms of tubes. Clear crystals on walls of tubes.
O <sub>2</sub>	No noticeable corrosion of the specimens. Tube walls covered with a yellowish-white material.	No noticeable corrosion of specimens. Tube walls coated with a yellowish-white substance.	No noticeable corrosion of specimens. Tube had reddish-yellow crystals on the wall above the liquid.	No noticeable corrosion.	No noticeable corrosion. One tube had reddish-brown crystals above the liquid level.
NOCl	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.
NOCl + O <sub>2</sub>	A few clear crystals on the walls of the tubes.	No noticeable corrosion.	Clear colorless gelatinous material at the top of the liquid on the tube walls.	No noticeable corrosion.	No noticeable corrosion. Yellowish-green immiscible droplets at the tops of the tubes and a few crystals on the bottoms.
Cl <sub>2</sub>	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.	No noticeable corrosion.

TABLE 1-11. Rating Chart for Macroscopic and Microscopic Examination of Corrosion Behavior of Metals (After Champion)

NO.	Number of Pits		Size of Pits		Intensity of Corrosion			Factors Affecting Corrosion (% Influence)
	Chart A		Chart B		Chart C			
	Standard Term	No. Per Sq. cm	Standard Term	Area (Sq. cm)	Standard Term	Depth of General Attack (cm)	Depth of Pitting or Cracking (cm)	
1	Very few	33	Minute	0.0006	Minute trace	0.0001	0.004	9
2	Few	100	Very small	0.003	Very small	0.0004	0.01	13
3	Small number	330	Small	0.016	Slight	0.0016	0.025	20
4	Moderate number	1,000	Moderate	0.08	Moderate	0.006	0.06	30
5	Considerable number	3,300	Considerable	0.4	Considerable	0.024	0.15	45
6	Numerous	10,000	Large	2.0	Severe	0.10	0.4	70
7	Very numerous	33,000	Very large	10.0	Very severe	0.40	1.0	100

TABLE 1-12 Results of One and Four Month Storage of 6061 T6 Aluminum Specimens With Neat and Contaminated N<sub>2</sub>O<sub>4</sub> at 165°F.

FLUID CHARACTERIZATION				POST TEST METAL CHARACTERIZATION						
Added Impurities	Pretest Concentration % w/w	Storage Period, Months	Post Test Concentration % w/w	Weight Change mg	Thickness Change mil	Rating (b)			Remarks	
						A	B	C		D
None	--	One	--	-0.3	-0.2	0	0	2	0	Little Discoloration.
		Four	--	-0.4	-0.1	1	1	0	0	Slight Discoloration.
Cl <sub>2</sub>	0.101	One	0.060	+0.4	+0.4	0	0	(c)	0	Little or No Discoloration.
		Four	0.094	-0.2	-0.2	0	0	2	0	Slight Discoloration.
H <sub>2</sub> O	0.91	One	0.82	-102.4	-0.6	3	2	3	2	Thick white coating on metal surface. General light discoloration after washing.
		Four	0.29	-111.1	-0.5	5	3	3	3	As Above.
O <sub>2</sub>	0.04	One	0.04	-0.5	-0.3	4	2	2	3	General Dark Discoloration.
		Four	0	+1.4	-0.1	4	3	0	3	As Above.
NOCl	0.024	One	0.035	+0.2	-0.3	0	0	2	0	Little Discoloration.
		Four	0.030	-0.1	0.0	1	1	0	1	Slight Discoloration
NOCl + O <sub>2</sub>	0.054 0.05	One	0.056 NOCl + 0.43 NO (a)	+1.0	-0.3	4	2	2	2	General Dark Discoloration.
		Four	0.054 NOCl + 0.07	+1.4	0.0	5	3	0	3	General Dark Discoloration.

(a) Oxygen apparently depleted and species formed which react with O<sub>2</sub>.  
 (b) Rating of zero indicates negligible corrosion. See Table 1-11 for rating definitions.  
 (c) Corrosion rating not applicable because of deposit build-up.

TABLE 1-13. Results of One and Four Month Storage of 347 Stainless Steel Specimens With Neat and Contaminated N<sub>2</sub>O<sub>4</sub> at 165°F.

FLUID CHARACTERIZATION				POST TEST METAL CHARACTERIZATION						
Added Impurities	Pretest Concentration % w/w	Storage Period, Months	Post Test Concentration % w/w	Weight Change mg	Thickness Change mil	Rating (b)				Remarks
						A	B	C	D	
None	--	One	--	-2.3	-0.1	0	0	0	0	No Discoloration.
		Four	--	-2.2	+0.1	0	0	(c)	0	No Discoloration.
Cl <sub>2</sub>	0.101	One	0.075	-1.6	-0.1	0	0	0	0	No Discoloration.
		Four	0.068	-2.5	+0.2	0	0	(c)	0	Slight Discoloration.
H <sub>2</sub> O	0.91	One	1.1	5.6	-0.4	1	1	3	1	Small crystals on metal surface. General dark discoloration.
		Four	0.48	-54.1	-0.1	4	1	0	2	As Above.
O <sub>2</sub>	0.04	One	0.07 NO(a)	-24.0	-0.2	4	2	2	3	Small crystals on metal surface. General dark discoloration.
		Four	0.01 NO(a)	-28.8	0.0	4	2	0	3	As Above.
NOCl	0.024	One	0.020	-0.8	-0.2	0	0	2	0	No Discoloration.
		Four	0.020	-1.5	+0.1	0	0	(c)	0	No Discoloration.
NOCl +	0.054	One	0.072 NOCl 0.33 <sup>+</sup> NO(a)	-37.2	-0.2	2	2	2	2	Small crystals on metal surface. General dark discoloration.
		Four	0.053 NOCl 0.03 <sup>+</sup>	-33.5	+0.1	4	2	(c)	2	As Above.

(a) Oxygen apparently depleted and species formed which react with O<sub>2</sub>.  
 (b) Rating of zero indicates negligible corrosion. See table 1-11 for rating definitions.  
 (c) Corrosion rating not applicable because of deposit build-up.

TABLE 1-14. Results of One and Four Month Storage of Ti-6Al-4V Alloy Specimens With Neat and Contaminated N<sub>2</sub>O<sub>4</sub> at 165°F.

FLUID CHARACTERIZATION				POST TEST METAL CHARACTERIZATION						
Added Impurities	Pretest Concentration % w/w	Storage Period, Months	Post Test Concentration % w/w	Weight Change mg	Thickness Change mil	Rating (b)				Remarks
						A	B	C	D	
None	--	One	--	-0.2	-0.1	0	0	0	0	Minute Discoloration.
		Four	--	-0.1	+0.2	0	0	(c)	0	Slight Discoloration.
Cl <sub>2</sub>	0.101	One	0.084	-0.3	+0.4	0	0	(c)	0	Minute Discoloration.
		Four	0.058	-0.0	+0.2	0	0	6	0	Slight Discoloration.
H <sub>2</sub> O	0.91	One	1.37	0.0	0.0	0	0	0	0	General Medium Discoloration.
		Four	0.52	+0.2	+0.2	0	0	(c)	0	As Above.
O <sub>2</sub>	0.04	One	0.12	-3.6	-0.1	0	0	0	0	No Discoloration.
		Four	0.04 NO <sup>(a)</sup>	-0.6	+0.2	0	0	(c)	0	Slight Discoloration.
NOCl	0.024	One	0.018	-0.2	0.0	0	0	0	0	No Discoloration.
		Four	0.017	-0.1	+0.1	0	0	(c)	0	Slight Discoloration.
NOCl +	0.054	One	0.060 NOCl 0.09 +	-6.0	-0.1	0	0	0	0	Minute Discoloration.
		Four	0.043 NOCl 0.09 +	-4.1	0.0	0	0	0	0	Slight Discoloration.

(a) Oxygen apparently depleted - oxygen reactive species present.  
 (b) Rating of zero indicates negligible corrosion. See table 1-11 for rating definitions.  
 (c) Corrosion rating not applicable because of deposit build-up.

## SPACE STORABLE PROPELLANTS

### FUELS

#### DIBORANE (B<sub>2</sub>H<sub>6</sub>)

Diborane is used as a high energy fuel. It is extremely toxic. Diborane is insensitive to mechanical shock and exhibits satisfactory (77°F) thermal stability in an inert atmosphere. It exhibits hypergolicity with the high energy oxidizers and behaves as a strong reducing agent in oxidation reduction reactions.

Diborane has a distinctive odor described as rotten eggs, sickly sweet and musty or foul. The recommended threshold limit is 0.1 ppm for an 8 hour exposure. Toxic concentrations are reached before any odor is detected. The ability to detect the odor decreases with exposure, therefore, special detectors must be used. Any substance which will function as a potential oxidizer will react with diborane including such materials as water, air, some metal oxides and reducible organic compounds. Diborane decomposes slowly at room temperature to hydrogen and high-molecular weight boron hydrides. Diborane is completely hydrolyzed by water:



The compatibility of diborane with other materials is similar to those listed under pentaborane except that diborane is somewhat more reactive than pentaborane at normal storage temperatures. In comparing chemical compatibility of pentaborane with diborane consideration should be given to problems associated with the lower temperature of the gaseous state of diborane.

Table 1-15 lists the materials considered to be most recommended for diborane. In all cases, these materials are suitable only if strict control of surface contamination and careful attention to minimize thermal

fluctuations above  $-20^{\circ}\text{C}$  are maintained. In regard to cleanliness, selection and complete removal of cleaning solvents requires special consideration since diborane may react explosively with certain halogenated solvents, e.g., carbon tetrachloride.

#### PHYSICAL PROPERTIES

Molecular Weight	27.69
Freezing Temperature $^{\circ}\text{F}$	-265
Normal Boiling Point $^{\circ}\text{F}$	-134
Critical Temperature $^{\circ}\text{F}$	62
Critical Pressure psia	581
Heat of Vaporization Btu/lb <sub>m</sub>	414
Density, gm/cc	0.47(-250)

TABLE 1-15. DIBORANE

COMPATIBILITY OF MATERIALS FOR LONG TERM APPLICATION

COMPATIBLE MATERIALS

Metals

Stainless Steel 18-8 Series  
Low Carbon Steels  
Nickel  
Monel  
Brass

Non-Metals

50-50 Polyethylene Polyisobutalene  
Kel-F  
Glyptal  
Vaseline-Paraffin-Graphite  
Asbestos-Graphite-Copper Packings

INCOMPATIBLE MATERIALS

Non-Metals

Most Natural and Synthetic  
Elastomers  
Silicone Grease <sup>a</sup>/<sub>—</sub>  
Fluorolube FS <sup>a</sup>/<sub>—</sub>

<sup>a</sup> These materials absorb small quantities of diborane and thus are suitable for limited service only.

## HYBALINE A-5

Hybaline A-5 is a pyrophoric, high energy fuel blend, of low volatility and reacts violently with water. Its composition is classified.

Cursory tests have been performed on some materials, although no definitive evaluation has as yet been conducted. Two separate investigations have been performed on the compatibility and corrosion rates of structural materials in Hybaline A-5 liquid and vapor at 50°C (122°F). Some discrepancy is noted on the compatibility of copper and brass toward the decomposition of Hybaline A-5, thus, caution is recommended until extensive investigation resolves these differences. The primary corrosion agents in the mixture are chlorides, utilized in the synthesis, which are not completely removed from the product.

The results of the two investigations are listed in Table 1-16. Materials listed as compatible have low ( 0.1 MPY avg.) corrosion rates and/or do not catalyze the decomposition of Hybaline A-5.

### Discussion of Problem Areas -

#### Hybaline A-5

Metals, Ceramics, Organic Polymers, Wet and Dry Lubes (2)\* - There is not sufficient data available on Hybaline A-5 to enable a reliable assessment of materials compatibility, but it would appear that no serious problems exist with these materials.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

TABLE 1-16. HYBALINE A-5  
 COMPATIBILITY OF MATERIALS AT 122°F

<u>COMPATIBLE METALS</u>	<u>NON-COMPATIBLE METALS</u>
<u>ALUMINUM</u>	Copper <sup>a</sup>
1100 <sup>a</sup>	Brass <sup>a</sup>
2104-T6	
2024-T3	
6061-T6	
7075-T6	
7075-T73	
356-T6	
Titanium Alloy A-110 AT <sup>a</sup>	
<u>STAINLESS STEELS</u>	
17-7 PH <sup>a</sup>	
17-4 PH	
302	
304L <sup>a</sup>	
316	
321	
347	
410	
<u>NON-METALS</u>	<u>NON-METALS</u>
Mylar <sup>a</sup>	Neoprene
Teflon (TFE and FEP) <sup>a</sup>	Viton-A
Kynar <sup>a</sup>	Tygon
Polyethylene <sup>a</sup>	Ke-F 90
Buna-N <sup>a</sup>	Fluorolube 362
Halocarbon Grease <sup>a</sup>	Dow Corning Valve
Dow Corning Hi-Vac Oil <sup>a</sup>	Seal Aerochlor 1254

a - exposure for 2 months. Other data is for a static, twenty-one day test.

## LIQUID PETROLEUM GASES (LPG) PROPELLANTS

The LPG propellants are colorless, flammable hydrocarbons, which are normally gaseous at room temperature and atmospheric pressure. The primary pure materials of interest are methane, propane, and butene. A pentane blend has also been proposed for use. The LPG propellants are not considered toxic gases. Methane acts physiologically as a simple asphyxiant. Butene and propane, in higher concentrations, also have an anesthetic action. Self-contained breathing apparatus, therefore, should be used if there is a suspected high concentration of these gases present, as in the case of a spill, etc. The LPG propellants should be stored away from any oxidizer and from possible sources of ignitions. All metallic equipment required for storage and handling should be grounded in order to prevent an accumulation of static charge.

Since the LPG propellants are non-corrosive, any common or commercially available metal may be used in the LPG is in the gaseous state. Metals having acceptable low temperature physical properties must be utilized in storing liquid methane, however, since it boils at  $-259^{\circ}\text{F}$  (1 atm).

Inasmuch as the propellants are hydrocarbons, they exert a solvent action on many greases, plastics and rubbers. Thus, consideration must be given to the types of organic materials which may come in contact with the propellants. Teflon, nylon, and the alkylene polysulfides are all resistant to attack, with the neoprene and butadiene-acrylonitrile rubbers being slightly less resistant.

### PHYSICAL PROPERTIES

	Methane	Propane	1-Butene
Molecular weight	16.04	44.10	56.10
Freezing point $^{\circ}\text{F}$ at 1 atm	-296	-306	-303
Normal boiling point $^{\circ}\text{F}$ at 1 atm	-259	-44	20.7
Critical pressure, psia	693	617	583
Latent heat of vaporization, cal/g	121.9	101.8	93.4

Discussion of Problem Areas -

Liquified Petroleum Gases (LPG) Propellants

Radiation Tolerance (2)\* - Since butene is an unsaturated hydrocarbon, reactions such as polymerization or molecular rearrangement can occur. Polymerization by free radical extension is normally carried out using catalysts, but can be induced by ionizing radiation. If the polymerization initiation is widespread throughout the storage tank, a violent and uncontrollable reaction may take place. Slow polymerization may result in the formation of sludge or varnish, leading to system malfunction.

Wet and Dry Lubes (2-3) - Because of the solvent properties of the propellants, there tend to be undesirable "wash-out" effects on lubricants. These problems can be minimized by the use of glands and seals. Experience in the petroleum industry with such lubricants as Plastilube #1 (Lubrication Company of America), John Crane Insoluble Gasoline Lubricant (Crane Packing Company), and Dow Corning Valve Seal (Dow Corning), indicated that these materials may be satisfactory for use.

Effects of Leakage (2) - Because of the extensive flammability of the propellants, the main hazard lies in the accumulation of vapors in confined areas, where the possibility of accidental ignition can occur. However, inasmuch as the gases are non-toxic, possess low flammability limits and since reliable vapor detectors are available, proper ventilation and elimination of sources of ignition reduce the danger of fire or explosion.

---

\*Parenthetical enclosures refer to the Propellant Rating Chart, Page 1-11.

## SPACE STORABLE PROPELLANTS (Continued)

### OXIDIZERS

#### CHLORINE TRIFLUORIDE (CTF) ( $\text{ClF}_3$ )

Chloride trifluoride, like fluorine, is among the most active chemicals known. Being a very strong oxidizing agent, it reacts vigorously with most oxidizable substances at room temperature and with most common metals at elevated temperatures. Under ordinary conditions, chlorine trifluoride reacts violently with water or ice. It is, however, insensitive to mechanical shock, nonflammable in dry air, and shows good thermal stability at ambient temperatures. Although some surface staining has occurred in tests employing impact, there has been no evidence of ignition utilizing aluminum, copper, magnesium or titanium in either gaseous or liquid CTF. Since CTF is probably the most corrosive and toxic of the interhalogens, the materials and precautions given for it are sufficient for use with the other halogen fluorides.

The corrosion resistance of all materials of construction used with chlorine trifluoride depends on the formation of a passive metal fluoride film which protects the metal from further attack. It is important that this film exhibit a tenacious bond with the parent material and not be easily removed or soluble in the CTF. Successive wearing operations can destroy the film and result in a "pseudo-corrosion rate" which is due to the inability of the film to withstand the operation and not due to a basic incompatibility of the material. The ability of some metals such as Monel, copper, nickel, stainless steel, etc., to form this tenacious, passive, metal-fluoride film makes them resistant to attack by chlorine trifluoride. Among the metals mentioned, Monel and nickel are preferred because of their resistance to hydrogen fluoride and hydrogen chloride, which are formed by the reaction of chlorine trifluoride with water. Aluminum alloys, 18-8 stainless steels and K Monel have been used for bellow materials. Gaskets have been made from sterling silver and lead-indium alloys, copper braid backed in Teflon, and calcium fluoride filled Teflon. Tin, indium carbon and boron carbide have been used for rotating seals.

Table 1-17 lists those materials which are considered to be compatible with chlorine trifluoride under most conditions for long-term application. However, materials that are listed in the table must be thoroughly cleaned and passivated (in the case of metal) to insure a contamination-free surface. All chlorine trifluoride systems must also be dry and leak-proof.

#### PHYSICAL PROPERTIES

Specific Gravity	1.83 (60°F)
Molecular Weight	92.46
Freezing Temperature °F	-105
Normal Boiling Point °F	53
Critical Temperature °F	345
Critical Pressure psia	838
Heat of Vaporization Btu/lb <sub>m</sub>	128

Discussion of Problem Areas -

#### Chlorine Trifluoride (ClF<sub>3</sub>)

Organic Polymers (1-2)\* - most organic polymers undergo spontaneous ignition and/or absorption of ClF<sub>3</sub> to form detonable mixtures, hence use of components incorporating plastic materials is not recommended. Teflon and Kel-F have been found acceptable under static propellant (nonflow) conditions; however, they may ignite when heated.

Wet and Dry Lubes (1) - No completely satisfactory lubricant is known. Most lubricants ignite spontaneously and/or form detonable mixtures with chlorine trifluoride. However, see remarks under fluorine.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Effects of Leakage (1) - Leakage cannot be tolerated in valves used for chlorine trifluoride. Although  $\text{ClF}_3$  is nonflammable in air and exhibits excellent thermal stability at ambient temperatures, it does represent an extremely hazardous propellant due to its toxicity and extreme reactivity with the vast majority of organic and inorganic compounds. At elevated temperatures it will react vigorously with most common metals; the propellant readily ignites organic materials such as solvents and lubricants. Space leakage is discussed under hydrazine.

Soft Seats (1-2) - Soft seats made of plastic materials generally are unsuitable for service with chlorine trifluoride. Some success has been found using Teflon impregnated with 40% calcium fluoride.

Hard Seats (2) - A very limited number of soft metals (principally aluminum 1100 and copper) have been found satisfactory for valve seat use. The seats should be thoroughly cleaned and propellant passivated prior to installation.

TABLE 1-17. CHLORINE TRIFLUORIDE (ClF<sub>3</sub>)

<u>MATERIAL</u>	<u>TEMP °F</u>	<u>MATERIAL</u>	<u>TEMP °F</u>
<u>ALUMINUM ALLOYS</u>		<u>OTHER METALS</u>	
1060	85	A-Nickel	85
1100	85	Copper	85
2014	85	Incoloy	85
2024	85	Inconel	85
3003	85	Indium	
5052	85	Lead Indium Alloy	
6061 (Welded)	85	Tin Indium Alloy	
6063		Magnesium AZ-31B	85
6066		Magnesium HM-21A	85
356		Magnesium HK-31A	85
Tens 50		Monel	85
		K. Monel	
		Nitralloy	
		Silver Solder	
		Sterling Silver	
		Tin	
<u>STAINLESS STEEL</u>		<u>NON-METALS</u>	
301		Boron Carbide	
302		Carbon	
303	85	Kel-F (Under Static Cond. Only)	
304	85	Teflon (Under Static Cond. Only)	
316	85	Teflon-40% CaF <sub>2</sub>	
321			
347	85		
403	85		
PH 15-7 Mo	85		
410	85		

Note 1: Materials listed above are rated compatible based on a corrosion rate of less than 1 mil per year and the material does not cause decomposition, and is free from impact sensitivity. Non-metals are rated for satisfactory service for general use.

## CHLORINE PENTAFLUORIDE

Chlorine Pentafluoride is among one of the most energetic oxidizers in use as a rocket propellant.

Immersion of TFE Teflon and Kel-F in liquid Chlorine Pentafluoride up to 86°F resulted in moderate weight gains, particularly for Kel-F. Complete and rapid reaction of columbium and molybdenum and degradation of blocks of carbon and graphite to powders resulted from immersion in this propellant. There was no change in titanium from immersion in Chlorine Pentafluoride however. Ignition could not be initiated by impassing aluminum 2014-T6, magnesium AZ 31B, nickel 200, or 347 stainless at 65 ft-lbs in the liquid at 86°F. Teflon TFE violently reacted when impacted under similar circumstances with 410 stainless. Table 1-18 lists those materials which showed minimal corrosion rates at 86°F or 150°F.

### Discussion of Problem Areas -

#### Chlorine Pentafluoride

Organic Polymers (1-2)\* - Most organic polymers undergo spontaneous ignition and/or absorption to form detonable mixtures, hence use of components incorporating plastic materials is recommended. Teflon TFE and FEP have been found satisfactory under static propellant conditions; however, they may ignite when heated or impacted.

Wet and Dry Lubes (1) - No completely satisfactory lubricant is known. Most lubricants ignite spontaneously and/or form detonable mixtures.

Effects of Leakage (1) - Leakage through valves presents a serious hazard, due to its toxicity and reactivity with most known materials. In addition, the effect of leakage is usually to increase the size of the leakage passage and thus present an increasing exposure threat to its surrounding environment. Space leakage is discussed under Hydrazine.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Soft Seats (1-2) - Soft seats made of plastic are unsuitable for service. CaF<sub>2</sub> - filled Teflon might be applicable under special conditions.

Hard Seats (2) - No data is available, but probably valve seats found suitable for use in the more energetic oxidizers would prove satisfactory.

TABLE 1-18. CHLORINE PENTAFLUORIDE

MATERIAL	CORROSION RATE	
	MPY	(21 day storage)
Aluminum 2014-T6	86°F	150°F
Aluminum 6061-T6	0.03	0.00
Yellow Brass, 1/2 Hard	0.13	0.66
Copper ETP, Soft Temper	0.07	0.17
Magnesium AZ 31B-0	0.06	0.07
Monel 400, Annealed	0.00	0.00
Nickel 200, Annealed	0.00	0.01
347 SS, Hot-rolled	0.00	0.00
410 SS, 180-200 ksi T.S.	0.00	0.67

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

## OXYGEN DIFLUORIDE (OF<sub>2</sub>)

Oxygen difluoride is a colorless gas at room temperature and atmospheric pressure, condensing to a yellow liquid at -229°F. It has a foul odor. The limit of detectability appears to be in the range of 0.1 ppm; 0.5 ppm in air is easily detected. Based on present knowledge, oxygen difluoride must be regarded as a highly toxic gas, possessing the same lethal characteristics as phosgene.

Oxygen difluoride is a powerful oxidizing agent similar to fluorine and the halogen fluorides, but is generally considered to be much less reactive than fluorine. It is capable of reacting with a majority of inorganic and organic compounds provided sufficient activation energy is available.

When reaction with OF<sub>2</sub> occurs, high heats of reaction are common, many sufficiently energetic to cause ignition. Reports on hypergolicity of fuels such as hydrazine, ammonia and monomethylhydrazine give varying conclusions; hence, the materials should be treated as potentially hypergolic at all times. Oxygen difluoride and diborane are unquestionably hypergolic. Oxygen difluoride is a relatively stable compound in that it does not detonate by sparking and was found to be insensitive to shock at -320°F. It does, however, begin to decompose thermally at approximately 480°F.

The data for materials compatibility are limited, but they do show that no major problems are to be expected with the majority of metals. A few metals including Titanium 110 AT, tantalum, magnesium and lead, exhibit moderate-to-violent reactions when subjected to shock loading in the presence of OF<sub>2</sub>. In like manner, Teflon, Kel-F and graphite indicate shock sensitivity. Parts made of these materials are not suitable for OF<sub>2</sub> applications if shock or impact loading is a requirement. On the other hand, there exists some service experience with valves containing fluorinated polymers such as Teflon, Alcar and Halon in contact with the liquid phase.\* These data are insufficient, but results are reported to be encouraging. Oxygen difluoride can be handled readily in most common metals and glass, with the choice dependent

---

\* Although most data indicate that these materials are recommended for gas phase service only.

upon the service requirement. Metals such as stainless steel, copper, aluminum, Monel, and nickel may be used for gas and liquid service from cryogenic temperatures to approximately 400°F.

Table 1-19 lists the materials considered to be compatible with oxygen difluoride. Tests were conducted with liquid OF<sub>2</sub> at -109°F.

#### PHYSICAL PROPERTIES

Specific Gravity	1.496 (-288.8°F)
Molecular Weight	54.00
Freezing Temperature °F	-370.8
Normal Boiling Point °F	-288.6
Critical Temperature °F	-72.8
Critical Pressure psia	719

#### Discussion of Problem Areas -

##### Oxygen Difluoride (OF<sub>2</sub>)

Ceramics (2)\* - Oxygen difluoride exhibits a strong oxidizing power similar to that of fluorine, and thus reacts with the vast majority of inorganic and organic materials. Extreme care should be taken to select materials compatible with the propellant under the temperature extremes of its environment.

Organic Polymers (2) - Polymers such as Teflon (TFE and FEP), Kel-F-81, the fluorosilicones, and the vinyl silicone elastomers have been utilized for limited service at moderate temperatures.

Wet and Dry Lubes (1) - There is no known lubricant for use in contact with liquid or gaseous oxygen difluoride. Because of the high reactivity of OF<sub>2</sub> with organic materials, conventional lubricants should definitely be avoided. Even the most likely candidates, the normally unreactive perfluorinated hydrocarbon lubricants, are degraded in the presence of liquid or gaseous OF<sub>2</sub>. It is therefore recommended that all valves be designed so as to eliminate the use of a lubricant in intimate contact with this oxidizer.

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Soft Seats (1)\* - Soft seat materials are often used at cryogenic temperatures, however this use is normally limited to polymers rather than elastomers. Extreme care must be used with polymers in  $OF_2$  service due to possible reaction with the propellant. The use of polymers should be limited to static seals not exposed to the flow stream. All metal valves with metal to metal seats are preferred.

Effects of Leakage (1) - Oxygen difluoride displays properties similar to those of liquid fluorine, but is generally considered to be less reactive and easier to handle. It is a relatively stable material in that it does not detonate by sparking, but it does begin to decompose thermally at elevated temperatures (about 480°F). Tests of reactivity to fuels such as hydrazine, ammonia, and monomethylhydrazine have given varied results as to its hypergolic nature. However, it should be assumed that the oxidizer is hypergolic with all fuels because of its very strong oxidizing power. The data on toxicity are quite limited, but  $OF_2$  must be regarded as a highly toxic material, similar to phosgene. Space leakage problems are similar to those discussed for Hydrazine.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

TABLE 1-19. OXYGEN DIFLUORIDE  
 COMPATIBILITY OF MATERIALS AT -109°F<sup>(a)</sup>

<u>MATERIAL</u>	<u>MATERIAL</u>
<u>METALS</u>	<u>OTHER METALS</u>
<u>ALUMINUM</u>	PH 15-7 Mo
1100-0	AM-350
2014-T6	Nickel 200
2219-T6	Inconel X
6061-T6	Rene 41
7079-T6	Cufenloy 40
	Cufenloy with electroless Ni plate
<u>STAINLESS</u>	Copper
301	Brass 7030
316	Columbium
347	
410	

(a) Metals listed above are rated compatible based on a corrosion rate of less than 1 mil per year, and the material does not cause decomposition and is free of impact sensitivity.

COMPATIBILITY OF MATERIALS FOR SHORT TERM USE

<u>MATERIAL</u>	<u>REMARKS</u>
<u>ALUMINUM ALLOYS</u>	
2024-T3	*
2024-T3 (Alclad)	*
<u>STAINLESS STEEL</u>	
301	*
304	
Maraging AM 355	*(No change for gas at ambient temperature)
Maraging AM 367	*

\*Fluoride coatings formed, but weight gain was considered insignificant.

OXYGEN DIFLUORIDE

COMPATIBILITY OF MATERIALS FOR SHORT TERM USE  
(Continued)

<u>MATERIAL</u>	<u>REMARKS</u>
<u>OTHER METALS</u>	
Beryllium Copper (2%)	*
Inconel X750	
Magnesium AZ 31B, H24	*
Monel 400	*
Monel K500	*
Titanium Alloy 5A1-2.5 Sn	
<u>NON-METALS</u>	
Glass	Above 390°F, glass is attacked by OF <sub>2</sub>

\*Fluoride coatings formed, but weight gain was considered insignificant.

INCOMPATIBLE MATERIALS\*

<u>INCOMPATIBLE METALS</u>	<u>INCOMPATIBLE NON-METALS</u>
Titanium A110-AT	Graphite
Titanium 6Al-4V	Teflon TFE
Lead	Teflon FEP
	Kel-F 5909
Tantalum	Kel-F Resin
	Oxylube 701
Magnesium HM21A-T8	

\*Incompatibility with OF<sub>2</sub> is based on impact sensitivity.

PERCHLORYL FLUORIDE (PF) ( $\text{FClO}_3$  or  $\text{ClO}_3\text{F}$ )

Perchloryl fluoride is a colorless gas at ambient conditions with a characteristic sweetish odor. Under pressure or low temperature it is storable in liquid form. The toxic action of perchloryl fluoride is derived from its pronounced oxidizing properties and results in respiratory irritation, oxidation of hemoglobin and absorption of fluoride into the body. The toxicity threshold limit for perchloryl fluoride in air is 3 ppm.

Perchloryl fluoride is thermally stable up to  $849^\circ\text{F}$  in absence of air. It is nonflammable but, being a strong oxidizing agent, readily supports combustion of many organic materials. Although not shock sensitive itself, in combination with porous organic or inorganic materials it can produce a potentially shock-sensitive mixture. Combinations of perchloryl fluoride and most rocket fuels constitute explosion hazards.

Reactions of perchloryl fluoride with water is very slow up to about  $575^\circ\text{F}$ . However, in the presence of water, perchloryl fluoride becomes more corrosive. The corrosion resistance of metals of construction therefore depends largely on the quantity of moisture present, hence selection must be governed by the moisture content. Under moisture conditions, types 304, 310, and 314 stainless steels have shown good resistance at room temperature.

Teflon and Kel-F are very resistant to attack by perchloryl fluoride. Other plastics which are suitable are unmodified phenolic resins and epoxy resins. Under mild conditions of heat shock, Teflon, Kel-F and Kaynar can be used, but may undergo structural changes when moderate amounts of perchloryl fluoride are absorbed. These plastics should not be used under dynamic flow conditions such as would result in their use with valves, since the resultant swelling of seal materials so constituted presents problems of physical interference.

Table 1-20 lists materials suitable for use with perchloryl fluoride.

#### PHYSICAL PROPERTIES

Specific Gravity	1.69 (-52.2°F)
Molecular Weight	102.457
Freezing Temperature °F	-231
Normal Boiling Point °F	-52.2
Critical Temperature °F	202
Critical Pressure psia	779
Heat of Vaporization Btu/lb <sub>m</sub>	84.0

#### Discussion of Problem Areas - Perchloryl Fluoride (FClO<sub>3</sub>)

Metals (2-3)\* - Although anhydrous perchloryl fluoride (less reactive and corrosive than other halogen-containing oxidants) at ordinary temperatures is not reactive to most common metals, selection of a metal for use with this propellant should be governed by the moisture content. In the presence of water, perchloryl fluoride is corrosive to most metals. The readily oxidized metals will burn in perchloryl fluoride under severe conditions; therefore, extreme care must be taken in selecting metals with thorough knowledge of propellant purity, compatibility, and potential environmental extremes.

Organic Polymers (2) - Many organic materials do not react with perchloryl fluoride at ambient temperature, but if ignited, will burn violently; some are hypergolic. Hence, materials compatibility is extremely important in the selection of a polymeric material. Teflon and Kel-F appear to be resistant to attack, but tend to absorb the fuel. Some phenolic and epoxy resins have found limited use.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page

Wet and Dry Lubes (1-2) - Fluorocarbons are the only suitable lubricants. Perchloryl fluoride must not be brought into contact with any other conventional valve grease or oil.

Effects of Leakage (1-2) - Perchloryl fluoride leakage represents an acute toxic hazard. Because of its strong oxidizing effect, it readily supports combustion with oxidizable materials such as organic compounds; it is hypergolic with some fuels such as hydrazine, and in combination with most other fuels may detonate. Space effects of leakage are discussed under hydrazine.

Soft Seats (2) - Teflon and Kel-F seats are recommended for limited use; however, consideration must be given to their ability to absorb perchloryl fluoride.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

TABLE 1-20. PERCHLORYL CHLORIDE  
 COMPATIBILITY OF MATERIALS FOR  
 LONG TERM APPLICATION (NOTE 1)

<u>MATERIALS</u>	<u>TEST TEMP °F</u>	<u>MATERIALS</u>	<u>TEST TEMP °F</u>
<u>ALUMINUM ALLOYS</u>		<u>MAGNESIUM ALLOYS</u>	
1060	85	AZ-31B	85
1100	85	HK-31A	85
2014	85	HM-21A	85
2024	85		
3003	85	<u>NICKEL ALLOYS</u>	
5052	85	"A" Nickel	85
6061	85	Nickel 200	85
7079	85	Inconel	85*
		Incoloy	85*
		Monel	85
		Ni-o-Nel	85*
<u>STAINLESS STEELS</u>		<u>LOW CARBON STEELS</u>	
304	85*	1010	85
316	85*	1010 (Coated w/Fosbond 40)	85
347	85	1010 (Coated w/Fosbond 27)	85
403	85		
410	85		
Carpenter No. 20-Cb	85*		
PH 15-7 Mo (Cond. RH 950)	85		
PH 15-7 Mo (Cond. TH 1050)	85		
AM 350 (Welded)	85	<u>MISCELLANEOUS METALS</u>	
		Gold	85*
		Platinum	85*
		Silver	85*
<u>COPPER ALLOYS</u>		<u>PLASTICS AND ELASTOMERS</u>	
Aluminum Bronze, 8% Ampco 8	85	Teflon	
Beryllium Copper, 2%	85	Kel-F	
Nickel Silver, 18% Alloy A	85	Polyethylene	
Phosphor Bronze, 5% Grade A	85		
Rule Brass	85		
Yellow Brass	85		
Copper, ETP	85		
Copper, DHP	85		

\*Moisture content to 1%.

NOTE 1: Metals listed above are rated compatible based on a corrosion rate of less than 1 mil per year and the material does not cause decomposition, and is free from impact sensitivity. Non-metals are rated for satisfactory service for general use.

## NITROGEN-FLUORINE COMPOUNDS

This family of chemical compounds includes three oxidizers which have limited usage as storable propellants. Included are nitrogen trifluoride ( $\text{NF}_3$ ), tetrafluorohydrazine ( $\text{N}_2\text{F}_4$ ) and nitryl fluoride ( $\text{NO}_2\text{F}$ ). Usage is limited because these oxidizers present most of the normal problems associated with corrosive cryogenic propellants but do not yield as high a specific impulse as other oxidizers such as liquid fluorine and oxygen difluoride. The main interest in these oxidizers stems from the fact that they have become building blocks toward the production of other N-F compounds that have higher boiling points, hence, are more easily storable. Inasmuch as compatibility data is limited, separate compatibility tables are not included, but discussed under each propellant.

### Nitrogen Trifluoride ( $\text{NF}_3$ )

Nitrogen trifluoride is a colorless gas at room temperature and atmospheric pressure which condenses to a liquid at  $-200^\circ\text{F}$ . It is relatively easy to prepare, thus potentially inexpensive. As a gas it is fairly stable and non-corrosive. As a liquid it is similar to liquid fluorine in that it is highly reactive with certain fuels. Materials compatibility data is very limited. Glass, stainless steel, nickel, copper and monel are suitable for use with this oxidizer.

### Nitryl Fluoride ( $\text{NO}_2\text{F}$ )

Nitryl fluoride is a gas at room temperature and atmospheric pressure which condenses to a liquid at  $-82^\circ\text{F}$ . It is highly reactive, even attacking glass. Reaction with metals and non-metals differs from the above two oxidizers because of the oxygen present. Most metals, including aluminum, steel, and titanium react to form both an oxide and a fluoride. Most non-metals react to form nitronium salts. Beryllium, magnesium, and gold do not react with nitryl fluoride below  $300^\circ\text{F}$ .

### Tetrafluorohydrazine ( $\text{N}_2\text{F}_4$ )

This oxidizer is similar to nitrogen trifluoride but is slightly heavier. At room temperature and atmospheric pressure, it is a gas, and condenses to a liquid at  $-100^\circ\text{F}$ . Compatibility data is scarce, but will be similar to that supplied for  $\text{NF}_3$ .

## HARD CRYOGENICS

### LIQUID FLUORINE (LF<sub>2</sub>)

Fluorine is the most powerful chemical oxidizing agent known. It reacts with practically all organic and inorganic substances, with a few exceptions being the inert gases, some metal fluorides and a few uncontaminated fluorinated organic compounds. It exhibits excellent thermal stability and resistance to catalytic breakdown, thereby presenting little or no problem in these areas. Compatibility ratings are, therefore, based primarily on the reaction of the fluorine with the various materials used.

Although fluorine is the most chemically active of all elements, many of the common metals can be considered for use in liquid fluorine systems.

Fluorine is a liquid at atmospheric pressure only in the short temperature range of -306°F to -363°F, therefore requiring insulation of all valves. At these low temperatures chemical reactions in general tend to take place rather slowly, thus corrosive attack by the liquid fluorine is generated at a slower rate. Another factor responsible for low rate of attack by liquid fluorine on the common metals is that protective films of fluoride compounds tend to form on metal surfaces and act as a barrier to further reaction. These films, however, must be tenaciously held by the parent material in order to retain their effectiveness.

The effectiveness of the protective film formed on the metals by the liquid fluorine also is based on the solubility of the various metal fluorides that form in the film in fluorine. It is believed that, as a protective film builds up and the rate of reaction slows down, an equilibrium between reactive rate and solubility of the film will be reached and a relatively steady corrosion rate will result. Lack of solubility data for fluorine compounds and corrosion rates for long periods of exposure can only be supplemented by actual service data and extrapolation of existing data. Service data indicate that the fluorides of nickel,

copper, chromium and iron are relatively insoluble in liquid fluorine. Also, metals such as Monel, nickel and stainless steels exhibit satisfactory performance in liquid fluorine and indications are that much lower rates of corrosion can be expected for long-term exposure where equilibrium rates are reached, than for short-term laboratory exposure. Some experiments, however, have shown that there is no increased corrosion of specimens immersed in liquid fluorine and wirebrushed to remove any films. This suggests that either not all the passivating effect is from formation of a metal fluoride film, or that the thickness of the film necessary for protection can be extremely thin.

Several lightweight metals such as the alloys of aluminum, titanium and magnesium are also known to produce protective films in liquid fluorine. Of these, titanium probably exhibits the lowest rate of corrosion; however, tests have shown it to be impact sensitive in fluorine.

Other factors to consider in selecting materials for use in a liquid fluorine system are: 1) flow rates, 2) water contamination in the system, and 3) mechanical properties of the material at the low temperatures experienced with liquid fluorine. The rate of flow of the liquid fluorine in a valve and through an orifice is considered to be an important factor in maintaining the protective film on the materials being attacked. Fluoride coatings on some metals that are less resistant to fluorine, such as low-alloy steels, are sometimes very brittle or porous and powdery. High flow rates tend to remove these coatings and thus increase corrosive action. In restricted flow applications "flaking" of the coating may result in contamination of the propellant, thus creating leakage problems at the valve seat.

Teflon has withstood exposure to liquid fluorine in a static condition. However, Teflon tends to react with fluorine to break down the polymers and form unsaturated low molecular weight fluorocarbons which do not adhere to the surface. Any flow of the propellant or movement of material over the surface of Teflon will remove these fluorocarbons, thus leaving them valueless as a protective film. Impurities introduced in the

manufacturing process appear to be responsible for accelerated decomposition of Teflon in liquid fluorine service.

Fluorine will react with any water present in the system to form hydrofluoric acid. This acid tends to attack some materials that are normally resistant to uncontaminated fluorine. Of all the metals showing resistivity to fluorine attack, Monel is generally preferred for use because of its inherent resistivity to the hydrofluoric acid.

In selecting materials for use in fluorine systems, consideration should also be given to the effects of low temperature environment on the mechanical properties of the materials. Some metals, such as the martensitic stainless steels, become brittle at these low temperatures.

Table 1-21 lists those materials which are considered to be compatible for service with liquid fluorine. However, as previously stated, insufficient information on prolonged usage of these materials in liquid fluorine restricts any rating for long-term application. Also, before using any material with fluorine, extreme care should be exercised in cleaning the material thoroughly to remove all possible contamination that may be present. Pre-treatment or conditioning treatment is also recommended. After thoroughly cleaning the material, a conditioning treatment exposes the material at room temperature to pure fluorine gas or a mixture of fluorine diluted with an inert gas. This, it is believed, initiates the formation of a relatively inert fluoride film. With the use of a diluted gas, the reaction that may take place with any traces of contamination remaining after cleaning would be less violent in nature. This treatment will then permit the material to withstand attack by full strength fluorine with much less reaction.

## PHYSICAL PROPERTIES

Specific Gravity	1.69 (-52.2°F)
Molecular Weight	102.457
Freezing Temperature °F	-231
Normal Boiling Point °F	-52.2
Critical Temperature °F	202
Critical Pressure psia	779
Heat of Vaporization Btu/lb <sub>m</sub>	84.0

Discussion of Problem Areas -

### Liquid Fluorine (F<sub>2</sub>)

Ceramics (2-3)\* - There are few ceramic materials which are completely satisfactory for use with liquid fluorine, although some have found limited use. Ceramic materials such as calcium fluoride and alumina are resistant to attack by gaseous fluorine even at high temperatures, but these lack mechanical strength. Both materials exhibited corrosion rates lower than metals tested at the same temperature and can be used where physical properties of ceramic materials can be tolerated. Recent work using TiC cermet and fused coatings of CaF<sub>2</sub> + LiF + NiF<sub>2</sub> on alumina has been encouraging.

Organic Polymers (1-2) - Organic polymeric materials are generally not suitable for service in liquid fluorine. Some fluorinated polymers have found limited service at moderate pressures with gaseous fluorine. Impurities introduced in the manufacturing process appear to be responsible for accelerated decomposition of Teflon in liquid fluorine service.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Lubricity (1-2)\* - Recent work at NASA Lewis on pumping of liquid fluorine has shown excellent results using liquid fluorine as the lubricant and alumina and titanium carbide as the rotating shaft seals. These materials showed no reaction with liquid fluorine and adequately performed their functions as seal materials.

Effects of Leakage (1) - Leakage of fluorine represents potential toxic, fire, and explosion hazards. The threshold limit value of fluorine is 0.1 ppm; it reacts vigorously with most substances at ambient temperatures, frequently with immediate ignition. Space leakage of propellants is discussed under the section for hydrazine.

Soft Seats (1-2) - Under static conditions, fluorocarbon plastics are satisfactory for liquid fluorine service. Limited applications of some fluorinated soft seat materials (Teflon) have been found for dynamic flow conditions; however, it is recommended that the material be shielded and a minimum of surface area exposed to liquid fluorine.

Hard Seats (2) - Valves having metal-to-metal seats have been used quite extensively in handling fluorine. It is desirable to use dissimilar materials to obtain a good seal and to prevent galling or binding when the valve is operated. Because metal valve seats are not as leak tight as those which utilize a resilient material, the use of double valving is recommended for critical applications.

Disconnect (2) - Further availability tests and evaluations are required before a more realistic prediction of performance can be made. Icing due to water vapor in the atmosphere can cause problems in disengagement of the separable units.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

TABLE 1-21. LIQUID FLUORINE (LF<sub>2</sub>)

COMPATIBILITY OF MATERIALS

<u>ALUMINUM ALLOYS</u>	<u>TEMP °F</u>	<u>CLASS</u>	<u>OTHER METALS</u>	<u>TEMP °F</u>	<u>CLASS</u>
1100	-320	1	A-Nickel	-320	1
2017	-320	11	Brass (Yellow)	-320	1
5052	-320	11	Brass (Cartridge)	-320	1
6061	-320	1	Brass (Casting)	-320	11
7079	-320	1	Copper	-320	1
			Copper-10% Nickel	-320	1
			Copper-30% Nickel	-320	1
<u>STAINLESS STEELS</u>			Everdur 1010	-320	1
304	-320	1	Magnesium Alloy		1
316	-320	1	AZ-31	-320	
347	-320	1	Magnesium Alloy		
410	-320	1	HK-31	-320	1
420	-320	1	Magnesium Alloy		
PH 15-7 Mo	-320	1	HM-31	-320	1
AM 350-C,CX,D,DX	-320	1	Monel	-320	1
Carpenter 20	-320	1			

NOTE: Materials listed above are rated compatible based on corrosion resistance and shock sensitivity; they do not include effects of cryogenic temperatures on the materials mechanical properties.

Class 1 Metals listed above are rated compatible based on a corrosion rate of less than 1 mil per year and the material does not cause decomposition, and is free from impact sensitivity. Non-metals are rated for satisfactory service for general use.

Class 11 Materials which exhibit corrosion rates as great as 5 mils per year.

## LIQUID OXYGEN (LOX)

Liquid oxygen is a non-toxic, nonflammable, and non-explosive oxidizing agent having a reactivity much lower than gaseous oxygen. Mixing of liquid oxygen with a hydrocarbon fuel will cause the latter to solidify. The resulting mixture is extremely shock sensitive.

Most metals are not corroded by liquid oxygen; however, the low temperature of liquid oxygen (-300°F) does cause embrittlement of some metals, especially the body-centered ferrous alloys. As a result, the alloys most commonly used in liquid oxygen handling equipment are nickel, Monel, copper, aluminum, the 300-series of stainless steels, brass, and silver solder.

Of all the metals studied to date, titanium exhibits the greatest sensitivity to impact when immersed in LOX. Battelle Memorial Institute studied the reactivity of metals with liquid and gaseous oxygen and found that only zirconium shows similar reactions to that of titanium. Aluminum and the stainless steels were found to exhibit almost no reactivity in oxygen, although aluminum will ignite under conditions of high explosive shock. Magnesium shows reactivity to explosive shock lying about midway between that of aluminum and titanium. Following is a partial summary of the results reported by Battelle for titanium.

The sensitivity of titanium approaches that of many organic materials, particularly when the surfaces are not completely cleaned or particles of dirt or grit are present. Reactivity is observed in liquid oxygen and mixtures of liquid oxygen and liquid nitrogen and mixtures of liquid oxygen and liquid nitrogen at impact forces of 20 ft-pounds until the LOX concentration is reduced to 30 percent. Titanium can be partially protected from reactivity in LOX under impact by certain protective coatings, provided these coatings are not broken. Electroless copper and nickel coatings are best, although protection also is provided by nitroding which adds a protective film, and by annealing which increases the oxide film thickness.

When a titanium vessel containing LOX or gaseous oxygen is ruptured by a bullet, a simulated micrometeoroid, or other mechanical puncture, violent burning begins at almost zero pressure (gauge). If the vessel is not fractured by application of external impact, vibration, acoustic or thermal energy, no reactivity is noted. Slowly propagated cracks, such as fatigue cracks, also do not cause reactivity.

The mechanism for the Ti-O<sub>2</sub> reaction is described as a reaction between a freshly formed titanium surface and gaseous oxygen. Titanium exhibits no great reactivity in LOX when deformed by compression, by exposure of a fresh surface by machining or rupture, or by exposure of bulk titanium to high-pressure or high-velocity LOX. In gaseous oxygen, however, titanium is highly reactive when a freshly formed surface is exposed at even moderate pressures. Under conditions of tensile rupture, a pressure of approximately 100 psig will initiate a violent burning reaction with titanium from about -250°F up to room temperature. When 2 percent HF is added as an inhibitor or 5 percent argon as a diluent, the pressure must be increased approximately twofold at room temperature before reaction occurs. Titanium could not be made to react even at very high pressure when the oxygen content was 35 percent or less.

All valves require insulation to avoid evaporation losses. Drainage of condensed water on valves should be provided to avoid water entrapment which may cause corrosion, or valve malfunction if the water refreezes.

Discussion of Problem Areas -

#### Liquid Oxygen (O<sub>2</sub>)

Organic Polymers (2)\* - Organic materials should be avoided whenever possible with both liquid and gaseous oxygen because of possibilities of explosion. Currently there are no tests which give a reliable compatibility rating for organic materials in liquid oxygen. Although there are several

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

lists of organic materials rated as suitable for use with liquid oxygen, specific conditions such as compatibility, impact sensitivity, and embrittlement at cryogenic temperatures should be thoroughly and carefully studied before any organic material is utilized. Sources of energy also may be from operation of mechanical parts, such as; 1) heat produced by friction of metal surfaces, 2) heat from shearing of liquids, 3) shock waves, and 4) heat generated by the catalytic breakdown of an organic material in contact with the metal surface, etc.

The most reliable organic materials for liquid oxygen applications are the fluorinated organic compounds (the more highly fluorinated the compound, the more stable\*\* to attack by liquid oxygen). In special applications many other organic compounds are used, even though these materials have shown to be sensitive to LOX. However, investigations with satisfactory testing procedures are needed before organic materials can be used with liquid oxygen with any great assurance of success.

Currently, there is no single test or group of tests which gives a reliable, uniform compatibility rating for materials suitable for use with liquid oxygen because of difficulty in determining impact sensitivity. Much of the data which are available were based on the ABMA 70 ft-lb acceptance level for impact sensitivity. This requirement was designed for application to materials used in missiles, based on the impact threshold level of a particular lubricant which, at the time, was considered to be the only safe available lubricant. Because of the lack of a technical basis for the establishment of the 70 ft-lb as an acceptance test parameter, and because the size, shape and cleanliness of the sample and test apparatus, as well as the design of the testing machine affect the detonation results, little can be assigned to published compatibility tables. Battelle has indicated that Teflon and Kel-F are the preferred plastics; with a combination of the two most desirable from the standpoint of ductility and strength. Picatinny reports that a polyurethane adhesive

---

\*\*The word stable here is more applicable than resistant because it deals with impact sensitivity and not resistance to corrosion.

has been found to be LOX compatible under ABMA procedure. A TFE-FEP hot melt adhesive was also reported to be the only insensitive adhesive when used in direct contact with LOX, but requires a 700°F bonding temperature. Because of the apparent need of individual use-tests for each design, no compatibility tables are included in this report.

Wet and Dry Lubes (1)\* - No completely compatible lubricants have been found. Selected perfluorinated hydrocarbon and dry lubricants have found limited use; however, the possibility of detonation still exists.

Lubricity (2) - Satisfactory low-load, short-life bearing and gear operation was possible where liquid oxygen was used as a lubricant. While some of the metals of construction proved satisfactory for use with liquid oxygen, others, under stress, tend to become brittle.

Effects of Leakage (2) - Liquid or gaseous oxygen does not display hazards similar to those encountered with most other oxidizers. Pure oxygen is incapable of burning or detonating, but mixed with a material that will burn, the resulting fire is intensified. Gaseous mixtures of oxygen and fuels form a potentially dangerous mixture which can be ignited by any form of spark. Liquid oxygen, when in contact or mixed with any form of combustible material, such as fuels, wood, plastics, oil, lubricants, or paper, forms an explosive mixture and even when frozen may be detonated by static electricity, mechanical shock, or similar energy source. Oxygen is non-toxic; however, contact with liquid or gaseous oxygen close to its boiling temperature will cause severe frostbite. Space conditions and leakage are discussed under this section for hydrazine.

Soft Seats (2) - Because of the composition of soft seat materials, they should be avoided in liquid oxygen service. Although some fluorinated plastics have been found reliable, until satisfactory testing procedures are available, there remains doubt about compatibility tests.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Disconnects (2) - Pneumatically operated disconnected valves used on missiles presented problems due to icing caused by condensed water vapor in the atmosphere, requiring extensive effort to disengage. In space transfer of the propellant, "freeze-up" should not be a problem due to the absence of water vapor in space atmospheres. Disconnects of the pull-away type during liftoff caused few problems, except for minor leakage.

## LIQUID HYDROGEN (H<sub>2</sub>)

Liquid hydrogen is a colorless, odorless liquid that normally does not present an explosive hazard when it evaporates and mixes with air in an unconfined space. However, an unconfined mixture of hydrogen gas and air will burn if exposed to an ignition source such as a spark. Liquid hydrogen is not in itself explosive, but reacts violently with strong oxidizers. If it is contaminated with oxygen, it becomes unstable and an explosion is likely to occur. Reaction with fluorine and chlorine trifluoride is spontaneous. Two species of liquid hydrogen exist: ortho-hydrogen and para-hydrogen.

At the low temperature (-423°F) at which hydrogen is a liquid, corrosive attack on materials is not considered to be an important factor in selecting materials to be used. A more important factor in selecting the materials for use with liquid hydrogen is the embrittlement of some materials by the low temperature of the liquid. Embrittlement of some materials by the low temperature of the liquid requires selection of materials on the basis of their structural properties, i.e., yield strength, tensile strength, ductility, impact strength, and notch sensitivity. The materials must also be metallurgically stable so that phase changes in the crystalline structure will not occur either with time-or temperature-cycling. It is known that body-centered metals (such as low-alloy steels) undergo a transition from a ductile to brittle behavior at low temperatures; therefore, such metals are generally not suitable for structural applications at cryogenic temperatures. Face-centered metals, such as the austenitic stainless steels, normally do not show a transition from a ductile to a brittle behavior at low temperatures. For this reason, these types of materials are desirable for use in cryogenic applications; however, care should be exercised in selection of face-centered metals. Low temperature toughness is not a characteristic of all face-centered metals, nor is it a characteristic of all conditions of a specific metal. For example, severely coldworked or sensitized (carbide precipitation at grain boundaries) austenitic stainless steels can become embrittled at low temperatures.

Table 1-22 lists those materials which are considered to be compatible with liquid hydrogen for long-term application.

Discussion of Problem Areas -  
Liquid Hydrogen (H<sub>2</sub>)

Organic Polymers (1-2)\* - The ability of polymeric materials to maintain satisfactory physical properties and to withstand thermal stress caused by large temperature changes is of prime importance. The use of a selected few organic plastics is thus limited to service where embrittling effect at the low temperatures of liquid hydrogen is minimized. Specifically, lip seals constructed of Teflon and Kel-F, static seals and some rubbers, and diaphragm seals from Mylar have proved serviceable. Studies at the National Bureau of Standards have shown that some elastomeric seals under compression retain their sealing capabilities effectively well below the normal brittle point of the polymer without compression.

Wet and Dry Lubes (1) - Lubricants are generally not practical in the presence of liquid hydrogen since they solidify and become brittle at the temperatures involved.

Lubricity (2) - Liquid hydrogen can be utilized as a lubricant under low-load, short-life conditions. Severe surface failure will occur, however, if the service conditions are such that local heating of the contact surface is allowed. The stainless steels are particularly susceptible to surface failure, as are other materials with low thermal conductivities. (Wear rates are reduced drastically by coating one of the surfaces with Teflon or Kel-F). Coldwelding has also been found to occur in gate valves having seats and wedges of 304 stainless in cryogenic service.

Effects of Leakage (2) - The leakage of hydrogen gas does not appear to present problems of an unusual nature, even though the composition limits for combustion are very wide. Hydrogen, being very light, tends to

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

dissipate rapidly. Proper ventilation and elimination of sources of ignition reduce danger of detonation. An explosion hazard exists when the hydrogen-air mixture is completely or partially confined. Effects of leakage in space are discussed under this section for Hydrazine.

Disconnects (2)\* - See comments under Liquid Oxygen.

TABLE 1-22. LIQUID HYDROGEN (H<sub>2</sub>)

COMPATIBILITY OF MATERIALS  
FOR LONG-TERM APPLICATION

<u>ALUMINUM ALLOYS</u>	<u>OTHER METALS</u>
1100	Molybdenum
1100T	Nickel
2024T	Monel
4043	Inconel
5052	Low Carbon Steel
	High Nickel Steel
	Titanium
<u>STAINLESS STEEL</u>	<u>NON-METALS</u>
301	Nitryl Rubber
302	Silicone Rubber
303	Teflon
304	Garlock Packing
304L	Bakelite
316	Micarta
321	Lucite
347	Graphite
410	
Haynes 21	

NOTE: The above listed materials were rated compatible primarily for their embrittlement properties at cryogenic temperatures. Non-metals shown as being compatible should be restricted for "warm" joint application or equivalent.

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

## LIQUID OXYGEN-LIQUID FLUORINE MIXTURES (FLOX)

Mixtures of liquid fluorine and liquid oxygen (FLOX) have received some consideration as oxidizers. A typical mixture contains 80 percent fluorine and 20 percent oxygen. There is limited compatibility data for these mixtures, but results of work done at various installations suggest that any material that performs well in liquid fluorine service will also work in FLOX. Evaluation of Atlas components showed no serious problems, except for the replacement of valves with constricted passageways.

The problem areas for FLOX are considered to be the same as those for fluorine, and the reader is referred to that section. Table 1-23 lists the limited compatibility data accumulated to date for FLOX.

TABLE 1-23. LIQUID FLUORINE-LIQUID OXYGEN (FLOX)  
COMPATIBILITY OF MATERIALS AT  $-320^{\circ}\text{F}$ (a)

<u>FLOX-40 (40%F<sub>2</sub> - 60% O<sub>2</sub>)</u>	<u>FLOX-20 (20% F<sub>2</sub> - 80% O<sub>2</sub>)</u>
<u>MATERIAL</u>	<u>MATERIAL</u>
Aluminum 2014-T6	Aluminum 2014
Aluminum 5052-H34	
Aluminum 6061-T6	Cadmium Plated 4037 Steel
4340 Steel	
301 Stainless	
304 Stainless	
347 Stainless	
Monel	
Inconel X	

(a) These materials exhibited less than 1 mil per year corrosion rate, do not cause decomposition, and are impact insensitive.

## GELLED PROPELLANTS

### LIQUID GELLED PROPELLANTS

A gelled propellant is any liquid propellant which has been conditioned so that it exhibits non-Newtonian properties. So many propellants have been gelled (e.g., hydrazine, RP-1, nitrogen tetroxide, etc.) that it is impossible to make any generalized statements about the compatibility of the gels, as such, with other materials. However, as a rule the additives needed to cause gelling (carbon black, silica, etc.) are not reactive and do not modify the chemical characteristics of the parent propellant, so that the compatibilities of gel can be considered to be the same as those of the parent propellant with respect to the action of the propellant on the system. Recently, studies on some gelled systems has indicated that the degradation of the propellant by system materials or impurities has been decreased by the gellation. Current work has been concentrated on finding more efficient gellation agents, in order to increase combustion efficiency and storage life.

One type of gelled propellant is characterized by thixotropic properties; that is, the viscosity of the propellant decreases with increasing shear and stress decreases with time at constant shear. These properties are of interest for several reasons. For example, when the propellant is locked in a tank, there is no shear being applied and the propellant is very viscous. When pressure is applied and the propellant valve is opened, shear stresses are induced, viscosity is reduced, and the propellant flows. As the propellant flows through the tank, valves, feed lines, and injector orifices, the shear becomes greater, the viscosity becomes less and the propellant behaves more like a low-viscosity liquid. From the standpoint of safety, the highly viscous state of the propellant when locked in a nonpressurized tank is advantageous.

The properties of gelled propellants also present some problems. For example, a relatively thick coating of propellant may adhere to tank and valve walls. Pressure drops through lines, valves and other components

are larger than those of comparable liquids. Valve maintenance and cleaning may be difficult if there are inaccessible cavities where gel may collect. Gels also may break down under the influence of radiation, temperature extremes, or inclusion of impurity electrolytes.

Excessive cold working (i.e., pumping into run tanks, over-mixing, etc.) can reduce the strength of the gel to an unacceptable value. Evaporation of the propellant can leave a fine powdery residue which could interfere with the normal action of moving parts such as valve stems.

Gelled propellant systems will probably be schematically similar to liquid propulsion systems which perform the same task. In general, it can be stated that the interaction between typical valve configurations and gelled propellants is not overly severe and that the associated problem areas can be circumvented through the use of proper design techniques.

Discussion of Problem Areas -

#### Liquid Gelled Propellants

Metals and Ceramics (3)\* - No real problem is envisioned with selecting metals suitable for use with liquid gels. It has been demonstrated that metals compatible with the liquid constituent will serve equally as well for gelled propellants.

Organic Polymers (2) - As with metals, it is necessary to select polymeric material based on the compatibility of the liquid constituent since the gelling agents are present in very small quantity and are normally inert materials.

Wet and Dry Lubes (2) - Compatibility of lubricants with gelled liquids depends on the compatibility of the liquid constituent.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Lubricity (2) - Experimental flow systems on both real and simulated systems has shown that it is reasonable to consider that the gelled liquid will have lubricating properties similar to those of the liquid constituent. These properties are the result of solvent characteristics and reducing properties of the liquid constituent under a frictional force.

Viscosity (2)\* - Viscosity varies with shear force (i.e., velocity, tube diameter). This presents a definite problem of retention in pockets and cavities of components, resulting in poor propellant utilization and difficulties in cleaning. As discussed previously, proper mechanical design should eliminate most of these difficulties.

Radiation Tolerance (2) - While no major problems have been envisioned for the liquid constituents under consideration for gels, some gelling agents appear to break down under various types of radiation and, in turn, cause the gel to be degraded.

Effects of Leakage (2) - The vapor pressure of the parent propellant is unaffected by gelling, hence toxic hazards of the liquid constituent must be considered. The rate of vapor evolution, however, is reduced, which in turn will reduce fire and explosion possibilities. Leakage, predominantly from volatilization of the high vapor pressure liquid constituent of the gel, will leave a residual powder, the gelling agent, creating problems such as sticking or malfunction of valves.

Control of Flow (2) - Difficulties in accurately measuring flow rate are anticipated; however, it may be expected that pressure drop will generally be higher than for the parent propellant and design allowances may be necessary.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

Shut-Off (1) - A very serious problem exists with the last valve in a system exposed to space environment. Rapid volatilization of the liquid component of a gelled liquid would leave a solid residue possibly of sufficient quantity to produce leakage or sticking of the valve on subsequent operations.

## METALIZED GELLED PROPELLANTS

In order to increase the thermochemical performance of rocket propellants, or to increase propellant bulk density for volume-limited propulsion system applications, powdered metals have been added to liquid propellants. The solid phase of these mixtures can be anywhere from 10 to 90 percent by weight. The metallic gel is generally prepared with metal having an average particle size range of 5 to 50 micron so that: 1) its effect on the flow characteristics of the propellant will be minimized, 2) burning in the combustion chamber will be less difficult, 3) suspension in the liquid will be easier. It has been necessary to gel the mixtures in order to suspend the metal powder in the propellant. Like gelled propellants, these metalized gelled propellants often exhibit thixotropic properties. Another similar class of gels employ metal containing compounds as gellants. These systems are more energetic than the straight metalized ones, but exhibit some storage instability.

Because of the solid particles, metalized gelled propellants present problems which are not encountered with standard propellants. For example, abrasive action of the particles could cause galling of the valve stems or scarring of valve seats and plugs. Particles may become trapped between a valve seat and plug, allowing the valve to leak. Evaporation of the liquid phase of the propellant will leave a solid matrix as a residue which can hinder valve operation and restrict propellant flow. The presence of solid particles in the propellant can result in the galvanic corrosion of certain standard materials of construction, particularly in the presence of impurities which allow electrolytic activity to occur. Any intimate contact of the propellant with lubricants could result in the transfer of particles to the lubricant, thereby reducing the effectiveness of the lubricant. In addition, the problems listed previously for non-metalized gels are applicable. Although it is not certain whether special components will be necessary to utilize metalized gels in propulsion systems, modified designs of standard components will be required to reduce the effects of the undesirable characteristics.

Discussion of Problem Areas -

Metalized Gelled Propellants

Metals and Ceramics (2)\* - Metalized gels subject certain metal components (i.e., aluminum, nickel, copper) to erosion and/or galling under dynamic conditions. Suitable metals for construction require compatibility with the liquid carrier and relatively high hardness for erosion resistance against the metal constituents of the gel.

Organic Polymers (2) - Considerably greater erosion and galling of plastic materials are anticipated under dynamic conditions. Generally, polymeric materials compatible with the liquid constituent are expected to serve as well under static conditions.

Wet and Dry Lubes (1-2) - Gels containing metal particles have considerably greater abrasive action under dynamic flow resulting in greater "wash-out" of lubricants. For static conditions, the restrictions placed upon the liquid constituent dictate selection of a compatible lubricant.

Lubricity (1) - The incorporation of metal particles in a gelled propellant tends to decrease the lubricating properties due to the added abrasive nature of such metals.

Viscosity (2-3) - As with gelled liquid propellants, viscosity varies with shear force and presents problems of propellant utilization, cleaning and greater pressure drop in components. Recent tests were performed by Edwards AFB on metallized propellant simulants in order to define the problem areas in pumping a metallized gelled propellant. Prior to testing, the pump start transient performance was considered to be the greatest potential problem area. Test results indicate, however, that pump start transients with a metallized gel compared favorable with those obtained with a Newtonian fluid. The pump cavitation performance was unaffected by

---

\*Parenthetical enclosure refers to Propellant Rating Chart, Page 1-11.

the presence of solid particles in the test fluid. Considerable erosion of the aluminum pump hardware was encountered during testing with the simulated propellant; however, they considered that there was a good indication that the use of steel hardware would solve the problem.

Radiation Tolerance (2)\* - Some gelling agents appear to deteriorate under radiation and in turn cause the gel to be degraded.

Effects of Leakage (1) - Loss of the liquid component of the gel by leakage will leave a solid matrix to interfere with proper operation of a component. The volatile liquid component will still present toxic, fire, and explosion hazards, but to a lesser extent due to the probable slower rate of evolution.

Control of Flow (1) - No satisfactory way has been found to measure flow rate accurately.

Soft Seats (1-2) - It is anticipated that the metal particles of gels will have detrimental effects on soft seats. Metal particles, trapped against the valve seat when the valve is closed, can cause the valve to leak initially or after several cycles. Selection of seat material should be based principally on compatibility with the liquid constituent of the gel.

Hard Seats (2) - Metal particles of the gel may prevent valves utilizing hard seats from complete sealing, and under dynamic flow the metal particles may result in considerable erosion of the seat by abrasive action.

Shut Off (1) - As with liquid gels, metalized gels present a serious problem for valves exposed to vacuum conditions because there would remain a greater quantity of residue on volatilization of the liquid constituent.

---

\*Parenthetical enclosures refer to Propellant Rating Chart, Page 1-11.

## REFERENCES - MATERIALS COMPATIBILITY

A number of the propellants of interest have similar compatibility behavior and degradation mechanisms. Because of this, it is felt that the references should be listed numerically and the number referred to for the propellant of interest. Some of the references were general enough in nature to warrant inclusion under a general heading. These references normally include either a general treatise on materials compatibility, or else deal with a large number of the listed propellants. As such, these references should be examined in conjunction with the references for the specific propellants of interest. A compilation of reference numbers for specific propellants given in Section B, unless otherwise noted, are listed as follows:

Reference numbers are for specific propellants, Section B, unless otherwise noted.

#### EARTH STORABLE PROPELLANTS

1. Hydrazine: 8, 13, 14, 15, 16, 17, 18, 19, 20, 21, 22, 23, 24, 25, 26, 128.
2. Monomethylhydrazine: 27, 28, 29, 30.
3. Unsymmetrical Dimethylhydrazine: 8, 31, 32, 33,
4. Aerozine - 50: 8, 20, 34, 35, 36, 37, 38, 39, 40, 128.
5. Pentaborane: 3, 4, 5, 6, 7, 8, 9, 10, 11, 12, 54.
6. Nitrogen Tetroxide: 8, 20, 23, 38, 59, 60, 61, 62, 63, 64, 65, 66, 67, 68, 69, 70, 71, 72, 73, 76, 127.

#### SPACE STORABLE PROPELLANTS

1. Diborane: 54
2. Hybaline A5: 1, 2, 12, 51.
3. Liquified Petroleum Gases: 126; General References Section A - 5, 10.
4. Chlorine Trifluoride: 8, 24, 44, 45, 46, 47, 48, 49, 50.
5. Chlorine Pentafluoride: 24, 51.
6. Oxygen Difluoride: 52, 53, 106, 108, 109, 110, 111, 112, 113.
7. Perchloryl Fluoride: 24, 48, 49, 55, 56, 57, 58.
8. Nitrogen Trifluoride: 21, 129, 130.
9. Nitryl Trifluoride: 21, 129, 130.
10. Tetrafluorohydrazine: 21, 129, 130.
11. Liquid Fluorine: 50, 96, 97, 98, 99, 100, 101, 102, 103, 104, 105, 106, 107, plus Section C: "Bibliography of Fluorine Reports."
12. Liquid Oxygen: 40, 83, 84, 85, 86, 87, 88, 89, 90, 91, 92, 93, 94, 95.
13. Liquid Hydrogen: 74, 75, 76, 77, 78, 79, 80, 81, 82.
14. Liquid Oxygen-Liquid Fluorine Mistures: 106, 113, 114, 115, 116, 117, 118, 119, 131
15. Liquid and Metallized Gelled Propellants: 120, 121, 122, 123, 124, 125.

#### A. GENERAL REFERENCES

1. F. Champion, "Corrosion Testing Procedures," John Wiley and Sons, Inc., 1965, 2nd Ed.
2. NASA, "Lubrication, Corrosion and Wear, A continuing Bibliography," Jan. 1962 - March 1965, NASA SP-7020, N65-29845
3. CPIA, "Chemical Propulsion Abstracts - 1965," (U) CPIA Publication No. 116, August 1966, (CONFIDENTIAL)
4. NASA, "Handling Hazardous Materials," NASA SP-5032, September 1965
5. NASA, "Advanced Valve Technology," NASA SP-5019, February 1965
6. NASA, "High Energy Propellants, A Continuing Bibliography," NASA SP-7002, 1964
7. NASA "High Energy Propellants, A continuing Bibliography," NASA SP-7002 (01), March 1965
8. NASA, "High Energy Propellants, A continuing Bibliography," NASA SP-7002 (03), April 1966
9. Defense Metals Information Center, "Combatibility of Materials with Rocket Propellants and Oxidizers," DMIC Memo: No. 201, Jan. 29, 1965
10. S. Sarner, "Propellant Chemistry," Reinhold Publishing Corp., New York, 1966
11. N. Tomashov, "Theory of Corrosion and Protection of Metals," The Macmillan Co., N.Y., 1966
12. R. M. McClintock and H. P. Gibbons, "Compilation of Mechanical Properties of Materials at Cryogenic Temperatures," NBS Report 6064
13. "Conference on Elastomers," Sixth Joint Army, Navy, Air Force, AD250916, Volume 2
14. Evans, George R., "Construction Materials for Containers of Liquid Propellants; Hydrogen, Fluorine, Hydrazine and Nitrogen Tetroxide: An Annotated Bibliography," AD 271034, April 1960, Lockheed Aircraft Company, Technical Information Center, Research Section.
15. Masteller, R. D. and others, "Design Criteria--Materials," 804-1001001, March 1960, The Martin Company, Denver Division

16. Howell, G. W. and Weathers, T. M., "Aerospace Fluid Component Designers' Handbook," Revision B, RPL-TDR-64-25, Vol. I (AD 809182), Vol. II (AD 809183), March 1967, TRW Systems
17. Beach, N. E., "Compatibility of Plastics with Liquid Propellants, Fuels and Oxidizers," Plastic Report 25, January 1966, Plastics Technical Evaluation Center, Picatinny Arsenal
18. "Investigation of the Formation and Behavior of Clogging Material In Earth and Space Storable Propellants," Interim Report No. 08113-6007-R000, Contract No. NAS 7-549, October 1967.

## B. SPECIFIC REFERENCES

1. Union Carbide Chemicals Co., "Research and Development of Metal Hydride Organic Nitrogen Complexes," (U), Rocket Propulsion Department Quarterly Progress No. 3, Sept. 1962, South Charleston, West Virginia, (CONFIDENTIAL)
2. Telecon, M. W. Wong, TRW and Capt. K. F. Illies, Edwards AFB, 16 Oct. 1963
3. S. S. Miller, "Pentaborane," Unit 4, Liquid Propellant Manual, Liquid Propellant Information Agency, March 1961
4. Rocketdyne, "Pentaborane Handling Manual," AF/SSD TR-61-110, R-3137, Sept. 1961
5. Rocketdyne, "Mechanical System Design-Criteria Manual for Penaborane," AF/SSD TR-61-3, R-3233, Sept. 1961
6. A. V. Jensen and B. B. Goshgarian, "A Study of Pentaborane," AFFTC-TR-61-3, R-3233, Sept. 1961
7. Gallery Chemical Company, "Pentaborane," Technical Bulletin CT-1300, October 1961
8. P. D. Gray, et al. "Rockets in Space Environment, Vol. I - The Experimental Program," Aerojet-General Corporation, RTD-TDR-63-1050, Contract AF04(611)-7441, Feb. 1963
9. F. Ward, "Pentaborane Jamming and Safety Procedures," American Rocket Society Missile and Spacecraft Testing Conference, Los Angeles, March 13-16, 1961, Paper No. 1638-61
10. B. Dawson and R. Schreib, "Investigation of Advanced High Energy Space Storable Propellant System -  $\text{OF}_2/\text{B}_2\text{H}_6$ ," AIAA Summer Meeting, Los Angeles June 17-20, 1963, Paper No. 63-238
11. CPIA, "Boron Hydrides and Derivatives. An Indexed Bibliography of Unclassified Titles for 1952-1959." CPIA (LPIA Publication LBH-1), June 1962; AD-468981
12. AFML, "Evaluation of Elastomers as O-Ring Seals for Liquid Rocket Fuel and Oxidizer Systems," Technical Documentary Report No. ASD-TDR-63-496, Part VI, August 1964; AD-607240
13. E. W. Cox, "Hydrazine," Unit 2, Liquid Propellant Manual, Liquid Propellant Information Agency, March 1961

14. Bell Aerosystems Company, "Titan II Storable Propellant Handbook," Bell Report No. 8182-933004 for AFBSD, Contract No. AF04(694)-72, March 1962
15. Bell Aerosystems Company, "Titan II Storable Propellant Handbook," Bell Report No. 8182-933004, AFBSD TR-62-2, Contract AF04(694)-72, March 1963
16. Arthur D. Little, Inc., "The Problems of Toxicity, Explosivity, and Corrosivity Associated with the WS 107A Mark II Operational Base Facility," Report to the Ralph M. Parsons Co., May 1960
17. Rocketdyne, "Hydrazine Handling Manual," AF/SSD-TR-61-7, R-3134, September 1961
18. Rocketdyne, "Mechanical System Design-Criteria Manual for Hydrazine," AF/SSD-TR-61-6, R-3130, September 1961
19. Department of the Air Force, "The Handling and Storage of Liquid Propellants," AFM 160-39, March 1961
20. Martin Company, "Propellant Compatibility Report," CR-64-88, November 1964.
21. D. J. Simkin, G. C. Szego and P. J. Valentine, Advances in Space Propulsion, U.C.L.A. Course Test, 1961.
22. JPL, "Supporting Research and Advanced Development," 31 Aug. 1965, Space Programs Summary No. 37-34, Vol. IV
23. C. Grelicki and S. Tannenbaum, "Survey of Current Storable Propellants," ARS Journal, 32, 1189 (1962)
24. S. N. Levine, W. Sheehan, and J. Green, "Elastomeric and Compliant Materials for Liquid Rocket Fuel and Oxidizer Application," Technical Report ML-TDR-64-107, Part II, Feb. 1965 (See Also Chemical Engineering Progress Symposium Series, No. 52, Vol. 60, p. 45)
25. K. Carroll, "Hydrazine - Chemical Properties, Decomposition," Report No. SB-59-63, 15 June 1959, AD-462732
26. Bell Aerosystems, "Handling and Storageability of Liquid Rocket Propellants - Tank Storage Tests," Report No. 02-989-020, Jan. 23, 1956, AD-455098
27. Olin Mathieson Chemical Corporation, "Mathieson Monomethylhydrazine - MMH," Product Bulletin, 1961
28. S. S. Miller, "Monomethylhydrazine," Unit II, Liquid Propellant Manual, Liquid Propellant Information Agency, December 1961

29. S. Sarner, "Monomethylhydrazine (MMH)," Astronautics, 5, 86 (July 1960)
30. O. Knight, "Monomethyl Hydrazine," Hydrocarbon Processing and Petroleum Refiner, 41, 179 (1962)
31. S. S. Miller, "Unsym. Dimethylhydr-zine," Unit 5, Liquid Propellant Manual, Liquid Propellant Information Agency, March 1961
32. Department of the Air Force, "The Handling and Storage of Liquid Propellants," AFM 160-39, March 1961
33. M. F. Butner, "Final Report - Proepllant Lubrication Properties Investigation," Rocketdyne, WADD-TR-61-77, June 1961
34. E. W. Cox, "Hydrazine/Unsym. Dimethylhydrazine (50:50)," Unit 7, Liquid Propellant Manual, Liquid Propellant Information Agency, July, 1961
35. Bell Aerosystems Company, "Titan II Storable Propellant Handbook," Bell Report No. 8182-933004, for AFBSD, Contract No. AF04(694)-72, March 1962
36. Bell Aerosystems Company, "Titan II Storable Propellant Handbook," AFFTC TR-61-32, Contract No. AF04(611)-6079, June 1961
37. E. M. Tomlinson, "Materials Selector for Propellant Systems," Aerospace Management, 4, 24 (February 1961)
38. S. Lewis and J. P. Cooper, "Materials Compatibility with Storable Propellants," Space/Aeronautics R&D Handbook, July 1962
39. Aerojet-General Corporation, "Storable Liquid Propellants - Nitrogen Tetroxide/Aerozine 50, LRP 198, June 1962
40. W. D. Smith and O. C. Bender, "Comparison of Storable and Cryogenic Propellants," AIAA Summer Meeting, Los Angeles, California, June 1963
41. J. Messina, "Greases Nonreactive with Missile Fuels and Oxidizers," Fourth National SAMPE Symposium, Los Angeles, Calif., Nov. 13-15, 1962
42. C. Wong, "Design for Material Compatibility and Corrosion Control Problems Associated with Typical Storage Propellants," SAE, Nat'l Aeronautic and Space Engineering and Manufacturing Meeting, Los Angeles Oct. 5-9, 1964, Paper No. 916C
43. K. Fisch, L. Peale, J. Messina, and H. Gisser, "Compatibility of Lubricants with Missile Fuels and Oxidizers," ASLE Trans. 5, 287 (1962); N63-13326
44. E. W. Cox, "Chlorine Trifluoride," Unit 3, Liquid Propellant Manual, Liquid Propellant Information Agency, March 1961

45. Rocketdyne, "Chlorine Trifluoride Handling Manual," AF/SSD TR-61-9, R-3136, Sept. 1961
46. Rocketdyne, Mechanical System Design-Criteria Manual for Chlorine Trifluoride," AF/SSD TR-61-4, R-3132, Sept. 1961
47. Rocketdyne, "Semiannual Program Progress Report for Product Engineering," (U), Report No. R-5652-2P, 31 July 1964 (CONFIDENTIAL)
48. J. Grigger and H. Miller, "The Compatibility of Materials with Chlorine Trifluoride, Perchloryl Fluoride, and Their Mixtures," Materials Protection 3, 53 (1964)
49. C. Grelecki and S. Tannenbaum, "Survey of Current Storable Propellants," ARS Journal 32, 1189 (1962)
50. W. English, S. Pohl, and N. Tines, "Corrosion Behavior of Structural Materials with Fluorine - Containing Liquid Oxidizers," SAMPE Nat'l Symp. on Mat'ls for Space Vehicle Use, 6th, Seattle, Wash., Nov. 18-20 1963, Vol. 3; AD 65-11524
51. J. Grigger and H. Miller, "The Compatibility of Structural Materials with Hybaline A-5 and Compound A," Pennsalt Co., Technical Report No. AFML-TR-64-391, Dec. 1964, AD-458159, N65-15579
52. N. A. Tiner, W. D. English and S. M. Toy, "Compatibility of Structural Materials with High Performance O-F Liquid Oxidizers," November 1965, AFML-TR-65-414.
53. N. A. Tiner, W. D. English, and S. K. Asunmaa, "Investigation of Explosive Reactions Involving Oxygen Difluoride," July 1965, AFML-TR-65-222.
54. R. L. Hughes, I. C. Smith, and E. L. Lawless, "Production of the Boranes and Related Research," Academic Press, New York, 1967.
55. Department of the Air Force, "The Handling and Storage of Liquid Propellants," AFM 160-39, March 1961
56. L. B. Piper, "Perchloryl Fluoride," Unit 19, Liquid Propellant Manual, Liquid Propellant Information Agency, January 1963
57. B. Kit and D. S. Evered, "Rocket Propellant Handbook," The Macmillan Co., New York, N.Y., 1960
58. W. English, S. Pohl, and N. Tiner, "Corrosion Behavior of Structural Materials with Fluorine-Containing Liquid Oxidizers," SAMPE Nat'l Symposium on Materials for Space Vehicle Use, 6th, Seattle, Wash., Nov. 18-20, 1963, Vol. 3; AD 65-11524

59. E. W. Cox, "Nitrogen Tetroxide," Unit 1, Liquid Propellant Manual, Liquid Propellant Information Agency, March 1961
60. Allied Chemical, Nitrogen Division, "Nitrogen Tetroxide," Product Bulletin
61. Bell Aerosystems Company, Titan II Storable Propellant Handbook," Bell Report No. 8182-933004 for AFBSD, Contract No. AF04(694)-72, March 1962
62. Arthur D. Little, Inc., "The Problems of Toxicity, Explosivity, and Corrosivity Associated with the WS 107A Mark II Operational Base Facility," Report to the Ralph M. Parsons, Co., May 1960
63. Rocketdyne, "Nitrogen Tetroxide Handling Manual," AF/SSD-TR-61-8, R-3135, September 1961
64. Rocketdyne, "Mechanical System Design-Criteria Manual for Nitrogen Tetroxide," AF/SSD-TR-61-5, R-3131, September 1961
65. Bell Aerosystems Company, "Titan II Storable Propellant Handbook," Bell Report No. 8111-933003, AFFTC TR-61-32, Contract No. AF04(611)-6079, June 1961
66. Aerojet-General Corporation, "Storable Liquid Propellants, Nitrogen Tetroxide/Aerozine 50," Report No. LRP 198, June 1962
67. E. M. Tomlinson, "Material Selection for Propellant Systems," Aerospace Management, 4, 24, February 1961
68. W. D. Smith and O. C. Bender, "Comparison of Storable and Cryogenic Propellants," AIAA Summer Meeting, Los Angeles, Calif., June 1963
69. R. Wallner, B. Williams, and A. Simmons, "Compatibility of Titanium and Nitrogen Tetroxide," Mat'ls. Prot. 4, 55, (1965)
70. AFRPL, "Methods for Elimination of Corrosion Products of Nitrogen Tetroxide," AFRPL-TR-66-209, August 1966
71. R. Wood, "Review of Recent Developments: Titanium and Titanium Alloys," DMIC Technical Note, April 6, 1966
72. G. Curran, "Metallurgical Investigation of Leakage in Missile B-58 Stage I Oxidizer Feed Line Bellows (SIN-47)," Martin Co. Report No. Cr-65-9, 31 Dec. 1964
73. J. Marcus, W. Day, and J. Jelinek, "Design and Development of an Elastomer Seal for Long-Term Hazardous Propellant Storage," SAMPE Journal, 2, 34, (1966)
74. B. M. Bailey, et al., "Handbook for Hydrogen Handling Equipment," WADC TR-59-751, February 1960

75. A. W. Adkins, et al., "Storage, Servicing, Transfer and Handling of Hydrogen," AFFTC TR-61-18, May 1961
76. M. F. Butner, "Final Report - Propellant Lubricating Properties Investigation," Rocketdyne, WADD-TR-61-77, June 1961
77. Department of the Air Force, "The Handling and Storage of Liquid Propellants," AFM 160-39, March 1961
78. Arthur D. Little, Inc., "Liquid Propellant Losses During Space Flight," Contract No. NAS5-664, January 1961
79. S. S. Miller, "Liquid Hydrogen," Unit 6, Liquid Propellant Manual, Liquid Propellant Information Agency, March 1961
80. Arthur D. Little, Inc., "Hydrogen Handbook," AF33(616)-6710, AFFTC TR-60-19, April 1960
81. J. Jackson, "Permeability of Titanium to Hydrogen," DMIC Technical Note, July 29, 1964, AD-609339
82. A. Jeffs, D. Lidster, and F. Luptou, "A Vacuum-Insulated Pipe to Carry Liquid Hydrogen at High Pressure," Rocket Propulsion Establishment (UIC) Technical Memo No. 321, July 1964, AD-454507
83. W. D. Smith and O. C. Bender, "Comparison of Storable and Cryogenic Propellants," AIAA Summer Meeting, Los Angeles, Calif., June 1963
84. Arthur D. Little, Inc., "Liquid Propellant Losses During Space Flight," Contract No. NAS5-664, January 1961
85. Department of the Air Force, "The Handling and Storage of Liquid Propellants," AFM 160-39, March 1961
86. W. K. A. Gallant, "Liquid Oxygen," Unit 8, Liquid Propellant Manual, Liquid Propellant Information Agency, July 1961
87. F. W. Fink and E. L. White, Corrosion Effects of Liquid Fluorine and Liquid Oxygen on Materials of Construction, NACE Paper Submitted at the 16th Annual Conference, 22 March 1960
88. The Martin Company, "Compatibility of Materials with Liquid Oxygen," November 1958, Report No. M-M-MI-58-66
89. A. Landrock, "Properties of Plastics and Related Materials at Cryogenic Temperatures," Picatinny Arsenal Report No. PLASTECH Report 20, July 1965, AD-469126
90. J. Jackson, W. Boyd, and P. Miller, "Reactivity of Metals with Liquid and Gaseous Oxygen," DMIC Memorandum No. 163, Jan. 15, 1963

91. E. Brady, "Compatibility of Metallic Materials with Liquid Oxygen," Aerojet-General Report No. DVR-64-459, 19 Oct. 1964, AD-459269
92. C. Dey and J. Gayle, "Effect of Liquid Nitrogen Dilution on LOX Impact Sensitivity," J. Spacecraft, 3, 274 (1966)
93. D. Weitzel, R. Robbins, and P. Ludtke, "Elastomeric Seals and Materials at Cryogenic Temperatures," AFML Report TDR-64-50, Part 2, March 1965, AD-485555
94. V. Chinberg and H. Perkins, "Preliminary Studies of Liquid Oxygen Explulsion Bladders," NASA Technical Memorandum No. NASA-TM-X-53005, Oct. 12, 1964, N65-12314
95. P. Schuman, "Development of Vulcanizable Elastomer Suitable for Use In Contact with Liquid Oxygen," Peninsular ChemResearch Inc., Gainesville, Fla., 8 June 1965
96. P. S. Gakle, et al., "Design Handbook for Liquid Fluorine Ground Handling Equipment, Aerojet-General Corp., WADD TR-60-159, December 1960
97. J. M. Siegmund, "Research on the Production, Storage and Handling of Liquified Fluorine," Allied Chemical Corp., Con-ract No. AF33(616)-2229, June 1955
98. H. G. Price and H. W. Douglas, "Non-Metallic Material Compatibility with Liquid Fluorine," NACA RM-E57G18, October 1957
99. C. J. Sterner and A. H. Singleton, "The Compatibility of Various Metals with Liquid Fluorine," Air Products, Inc., WADD TR-60-819, March 1961
100. R. L. DeWitt and H. W. Schmidt, "Experimental Evaluation of Liquid Fluorine System Components," Lewis Research Center, NASA TN-D-1727, June 1963
101. H. R. Neumark, "Fluorine and Advanced Rocket Propulsion," Missiles and Space, 7, 18, July 1961
102. Aerojet-General Corp., "Design Handbook for Liquid Fluorine Ground Handling Equipment," 2nd Ed., Technical Report AFRPL-TR-65-133, August 1965
103. W. Osborn, "Investigation of a Liquid-Fluorine Inducer and Main-Stage Pump Combination Designed for a Suction Specific Speed of 20,000," NASA TMX-1070, March 1965
104. W. Hady, G. Allen, H. Sliney, and R. Johnson, "Friction, Wear, and Dynamic Seal Studies in Liquid Fluorine and Liquid Oxygen," NASA TN D-2453, 1964

105. J. Flanagan and F. Stephanson, "Fluorine Propulsion Technology," AIAA Annual Meeting, 2nd, San Francisco, July 1965, AIAA Paper No. 65-536
106. Defense Metals Information Center, "Compatibility of Materials with Fluorine and Fluorine-Base Oxidizers," DMIC Technical Note, April 8, 1965
107. J. Cabiness and J. Williamson, "A Literature Survey of the Corrosion of Metal Alloys in Liquid and Gaseous Fluorine," NASA TM-X-54612; N64-17691, 31 Dec. 1963
108. Allied Chemical, General Chemical Division, "Oxygen Difluoride," Product Data Sheet, July 1962
109. D. S. Smith and D. J. Mann, "OF<sub>2</sub> Looks Promising as Space-Storable Propellant," Space/Aeronautics, 39, 103, January 1963
110. B. E. Dawson, A. F. Lum, and R. R. Schreib, "Investigation of Advanced High Energy Space Storable Propellant System," Thiokol Chemical Corp., RMD Report 5507-F, Contract NASw-449, November 1962
111. B. E. Dawson, A. F. Lum, and R. R. Schreib, "Investigation of Advanced High Energy Space Storable Propellant System - OF<sub>2</sub>/B<sub>2</sub>H<sub>6</sub>," AIAA Summer Meeting, Los Angeles, Calif., June 1963
112. B. Dawson and R. Schreib, "Investigation of Advanced High Energy Space Storable Propellant System - OF<sub>2</sub>/B<sub>2</sub>H<sub>6</sub>," AIAA Summer Meeting, Los Angeles, June 17-20, 1963, Paper No. 63-238
113. J. Cakiness, "Bibliography on Fluorine and Fluorine-Oxygen Oxidizer for Space Applications," 16 Oct. 1964, NASA TM-X-53149
114. General Dynamics/Astronautics, "Feasibility Testing 30% FLOX with Atlas Oxidizer System Components," 24 July 1964, Report No. GD/A-Bgm-64-0021, Final (CONFIDENTIAL)
115. General Dynamics/Astronautics, "Feasibility Testing 50% FLOX with Atlas Oxidizer System Components," 20 Nove. 1964, Report No. GD/A-BHV64-011, Final (CONFIDENTIAL)
116. D. Spicer, "Liquid Fluorine and FLOX Immersion Tests of Alloys Under Static Stress," Laboratory Report No. MP30, 450, Douglas Aircraft Co., Inc., (March 3, 1964)
117. D. Spicer, "Static Immersion of Non-Metallic Materials in Gaseous FLOX," Laboratory Report No. MP30, 451, Douglas Aircraft Co., Inc., (March 23, 1964)
118. General Dynamics/Astronautics, "Atlas 77D Oxidizer Tank Storage Test After Exposure to 30% FLOX," (U) GD/C-CHB65-009, Final (CONFIDENTIAL)

119. Rocketdyne, "Atlas Mark 4 Turbopump Seal FLOX Test Program," (U) Report R-5889, 9 Jan. 1964 (CONFIDENTIAL)
120. Edwards AFB, California, Proceedings of the Metallized Gelled Propellants Conference, June 1963 (CONFIDENTIAL)
121. A. J. Aitken, "Metallized Thixotropic Propellants," Aerojet-General Corporation Report No. 652/SA4-2.2-F1, Vol. 5, Air Force Contract No. AF04(647)-652/SA4, June 1963 (CONFIDENTIAL)
122. W. B. Tarpley, C. D. McKinney and R. Pheasant, "Research and Development Program on Thixotropic Propellants," Aerojects Incorporated, Research Report 62-15, Navy Contract N0w-61-0506-c, May 1962 (CONFIDENTIAL)
123. Packaged Liquid Propulsion Symposium, October 1962, CPIA Publication No. 13, March 1963, (CONFIDENTIAL)
124. J. Chlapek and R. Probst, "Metallized Propellant Simulant Pumping," Technical Report AFRPL-TR-65-67, April 1965
125. CPIA, "2nd Metallized Gelled Propellants Conference, 26-28 August 1964," (U), Silver Spring, Md., Pub. No. 64 (CONFIDENTIAL)
126. The Matheson Company, "Matheson Gas Data Book," Newark, Calif., 1961
127. Muraca, R. F. and J. S. Whittick, "The Results of Long-Term Storage Tests for Compatibility of Nitrogen Tetroxide with Various Spacecraft Materials," JPL Contract No. 951581 (Under NASA NAS 7-100), Special Report No. 2., May 15, 1967.
128. R. F. Muraca and J. S. Whittick, "The Results of Long-Term Storage Tests for Compatibilities of Spacecraft Materials with Hydrazine and Hydrazine Mixtures," JPL Contract No. 951581 (Under NASA NAS 7-100), Special Report No. 951581-6, October 1, 1967.
129. J. H. Simmons, Fluorine Chemistry, Volume 5, Academic Press, New York, N.Y., 1961.
130. M. Stacey, J. C. Tatlow and A. G. Sharpe, Advances in Fluorine Chemistry. Volume 5, Butterworth, Washington, D. C. 1965.
131. Harold W. Schmidt, Handling and Use of Fluorine and Fluorine-Oxygen Mixtures in Rocket Systems, NASA SP-3037, Lewis Research Center, Cleveland, Ohio.

### C. BIBLIOGRAPHY OF FLUORINE REPORTS

1. Aerojet Engineering Corporation, Azusa, California, Investigation of Liquid Rocket Propellants, by S. B. Kilner, et al., Report No. 577 (Annual), 7 February 1952
2. Aerojet-General Corporation, Sacramento, California. Design Handbook for Liquid Fluorine Ground Handling Equipment, WADD Technical Report No. 60-160, February 1961
3. Research Study on Ground Handling Equipment for Transporting Service Storing, and Handling Liquid Fluorine, WADD Technical Report No. 60-160, February 1961
4. Air Products, Inc. Allentown, Pennsylvania. Compatibility of Liquid Fluorine with Various Structural Materials and Carbon, by Alan H. Singleton and Charles J. Sterner, Progress Report VI, August 1960
5. Air Products, Inc., Emmaus, Pennsylvania. Compatibility of Liquid Fluorine with Various Structural Metals and Carbon, by Charles J. Steiner, Bi-Monthly Progress reports 1 through 6, Contract AF33(616)-6515
6. Allied Chemical Corporation, General Chemical Division. Fluorine Elemental F.
7. Allied Chemical and Dye Corporation, General Chemical Division. Fluorine Study for Experimental Rocket Engine Test Laboratory, by J. M. Siegmund, AD 147621, 15 May 1956 (C)
8. Fluorine-Properties and Methods of Handling
9. Research on the Production and Handling of Liquified Fluorine, Vol. I, Research on the Production of Liquified Fluorine, 10 June 1955 (C) AD 77312
10. Fluorine, PD-TA-85413, Revised 15 August 1958
11. Liquid Fluorine Unloading Procedure, PD-TB-85411, July 1958
12. Altman, D. "A Review of Liquid Propellant Oxidizers," Symposium on Liquid Propellants, Vol. I, Office of the Assistant Secretary of Defense, R&D, Washington, D.C., 23-24 May 1955
13. American Medical Association Archives of Industrial Hygiene and Operational Medicine, June 1954, as given in "Threshold Limit Values for 1954," and adopted at the 16th Annual Meeting of the American Conference of Governmental and Industrial Hygienists, Chicago, Illinois, 24-27 April 1954

14. Anonymous. Chemical and Engineering News, 35, 7, 18, March 1957
15. Anonymous. Chemical and Engineering News, 36, 35, 1958
16. Anonymous. "Atomic Weights, 1948," Journal of the American Chemical Society, 70, 11, 1948
17. Aoyama, S. and E. Kanda, "Studies on F<sub>2</sub> at Low Temperatures," Bulletin of the Chemical Society of Japan, 12, 416, 1937
18. Aoyama, S. and E. Kanda, "Studies of Fluorine at Low Temperatures, Vapor Pressure of Fluorine," Bulletin of the Chemical Society of Japan, 12, 417-18, 1937
19. Argonne National Laboratory, Lemont, Illinois, Corrosion of Metals in the Presence of Fluorine at Elevated Temperatures, by M. J. Steindler and R. C. Vogel, January 1957
20. Barrow, R. F. and D. C. Count, "The Ultra-Violet Absorption Spectra of Some Gaseous Alkali-Metal Halides and the Dissociation Energy"
21. Barrow, R. F. and A. D. Count, "The Heat of Solution of Thallous Fluoride and the Dissociation of Fluorine," Transactions of the Faraday Society, 46, 154-6, 1950
22. Battelle Memorial Institute, Columbus, Ohio. Physical Properties and Thermodynamic Functions of Fuels, Oxidizers, and Products of Combustion II, Oxidizers, Report to the Rand Corporation, Santa Monica, California, February 1949
23. Battelle Memorial Institute, Division of Chemical Engineering, Columbus, Ohio, Liquid Propellants Handbook, Volume 3, Experience with Fluorine Systems, December 1958
24. Liquid Propellants Handbook, Volume 2, Properties of Fluorine, Compiled by D. E. Sparrow, 13 August 1956
25. Bell Aerosystems Company, Launch Area Servicing of a Fluorine-Hydrogen Upper Stage, Report No. 8031-982-003, 31 December 1962
26. Areas of Proposed Investigations Rocket Technology, Status Report, August 1962
27. Summary of Bell Fluorine Propulsion Experience and Design Studies, Report No. S-128857, January 1962
28. Research and Development to Advance the State-of-the-Art of Fluorine High-Energy Propulsion Systems, Final Report No. SSD-TR-61-2, 24 July 1961 (C)

29. Research and Development to Advance the State-of-the-Art of Fluorine High-Energy Propulsion Systems, Report No. 8136-920001, (Supplement to SSD-TR-61-2), 24 July 1961 (C)
30. Fluorine Hydrogen Rocket Engine Feasibility Investigations, Report No. 8031-982-002, 28 February 1961 (C)
31. Fluorine-Hydrogen Propulsion Data, Report No. D8217-953001, 3 January 1962 (C)
32. 35,000 Lb Fluorine/Ammonia Thrust Chamber Feasibility Investigation, Final Report No. 123-982-002, May 1958
33. Summary of High Energy Propellant Programs at Bell Aircraft Corporation, Report No. 7-59-0452-001, 30 January 1959 (C)
34. High Energy Propellant Program, Final Report, Report No. 8031-982-001, 1959 (C)
35. Bernstein, R. B. and M. Metlay, "Note of the Electron Affinity of Fluorine," Journal of Chemical Physics, 19, 1612, 1954
36. Bird, R. B., J. O. Herschfelder, and E. L. Spatz, "The Transport Properties of Nonpolar Gases," J. Chem. Physics, 16, 968, 1948
37. Booth, H. S. and J. P. Pinkston, Jr. Chemical Reviews, 41, 421-37, 1947
38. Borg-Warner Corporation, Chicago, Illinois, Investigation of Propellant Systems and Components Utilizing a High-Energy Oxidizer, Final Report, Volume 2, May 1960, AFFTC Technical Report 60-9
39. Bureau of Ordnance. Safety Regulations for Guided Missile Propellants, (Including Revisions of April 21, 1949), prepared by Ad Hoc Committee on Safety Code for Guided Missile Propellants for Inter-Bureau Technical Committee, July 1948
40. Burford, W. D., III, et al. "Solubility of Fluorine Gas in Various Fluorocarbons and Concentrated Acids," as given in Preparation, Properties and Technology of Fluorine and Organic Fluoro Compounds, Chapter II by Slesser (Ed.), McGraw-Hill, New York, 1951
41. Buthov, K. V. and R. B. Rozenbaum, "Vibration Frequency of the Atoms in a Fluorine Molecule, the Thermodynamic Functions of Fluorine and the Equilibrium Constant  $F_2 \rightleftharpoons 2F$  in a Temp Interval of 298.1 to 5000°K," Translation under auspices of State University Research Foundation, Columbus, Ohio, 35th Progress Report, 1 September 1951, p. 11 of translation

42. California Institute of Technology, Jet Propulsion Laboratory, Pasadena, California, The Heat of Dissociation of Fluorine by R. N. Doescher, Report No. 20-61, November 1951; also Journal of Chemical Physics, 20, 334, 1952
43. Gallery Chemical Company, Gallery, Pennsylvania, Background Chemistry for Development of Liquid Rocket Oxidizers, by J. O. Collins, P. A. Joyner and L. S. Stone, Report No. 000-52208-SR-1, 1963
44. Cody, G. H. "Reaction of Fluorine with Water Hydroxides," J. Am. Chem. Soc., 57, 246-9, 1935
45. Cody, G. H. and J. H. Hildebrand, "The Vapor Pressure and Critical Temperature of Fluorine," J. Am. Chem. Soc., 52, 3839-43, 1930
46. Claussen, W. H., "The Vapor Pressure of Fluorine," J. Am. Chem. Soc., 56, 614, 1934
47. Coe, C. S. and G. P. Sutton, "The Effect of Liquid Propellant Properties on Rocket Engine and Missile Design and Operation," Symposium on Liquid Propellants, Office of the Assistant Secretary of Defense, R and D, Washington, D.C., 23-24- May 1955
48. Cole, L. G., G. W. Elverum, Jr., and M. Farber, "Thermodynamic Properties of the Fluorine Atom and Molecule and Hydrogen Fluoride to 5000°K," J. Am. Chem. Soc., 20, 586-90, 1952
49. Davenport, S. J. and G. C. Margis, "Review of Health Hazards of Fluorine and Fluorine Compounds in the Mining and Allied Industries," Bureau of Mines Circular 7687, 1954
50. Doescher, R. N. "The Heat of Dissociation of Fluorine," J. Chem. Phys., 19, 1070-1, 1951
51. Doescher, R. N. and G. W. Elverum, Jr., "Physical Properties of Liquid Fluorine," J. Chem. Phys., 20, 1834-6, 1952
52. Dykstra, J., W. E. Paris, and J. Thompson, "A Twenty-Five Pound per Hour Fluorine Plant," Ind. Eng. Chem., V50, No. 2, February 1958
53. Dykstra, J., A. P. Huber, and B. H. Thompson, "Multi-Ton Production of Fluorine for Manufactur of Uranium Hexafluoride," Second United Nations Internaitonal Conference on the Peaceful Uses of Atomic Energy, Paper No. A/Confidential 15/p/524, U.S.A., 1958
54. Eucken, A. and E. Wieke, "The Dissociation Energy of Fluorine," Die Naturwissenschaften, 36, 233-4, 1950
55. Evans, W. H., T. R. Munson, and W. D. Wagman, "Therodynamic Properties of Some Gaseous Halogen Compounds," J. Res. NBS, 55, 154-4, 1955

56. Evans, M. G., E. Warhust, and E. Whittle, "The Dissociation Energy of Fluorine," J. Chem. Soc. (London), 1524-34, 1950
57. Ferry, J. L., The Toxicity of Fluorine, AEC 3776, 1955, Declassified.
58. Franch, E. V., "A Determination of the Refractive Index of Fluorine Vapor," Die Naturwissenschaften, 41, 36, 1954
59. Fritz, H. and E. Wieke, "The Dissociation Energy of Fluorine by the Explosion Method," Zeitschrift fur Elektrochemie, 57, 9-16-1953, as given in Chemical Abstracts, 1953
60. Gainer, C. S. and D. M. Yost, "An Attempt to Determine the Electrode Potential and Raman Spectrum of Fluorine," J. Am. Chem. Soc., 59, 2738, 1937
61. Gall, John F., "Recent Advances in Fluorine Chemistry and Technology," ARS J., February 1959, Vol. 29, No. 2
62. Gaydon, A. G., Dissociation Energies and Spectra of Diatomic Molecules, John Wiley and Sons, Inc., New York, 1947
63. Gilles, P. W. and J. L. Margrave, "The Dissociation Energy of Fluorine," J. Chem. Phys., 21, 381-2, 1953
64. Glocker, G. Physical Review, 46, 111, 1934
65. Unpublished Results, as given by J. F. Simmons (Ed.) in Fluorine Chemistry, Volume I, Academic Press, Inc., New York, 1950
66. Godwin, T. W. and C. F. Lorenzo, "Ignition of Several Metals in Fluorine," 13th Annual ARS Meeting, Hotel Statler, New York, 17-21 November 1958
67. Harshaw Chemical Company, Cleveland 6, Ohio, Unloading Anhydrous Hydrofluoric Acid from Tank Cars, Manufacturing Chemists Association Manual Sheet TC-5, Reprinted in Hydrofluoric Acid Anhydrous, 1952
68. Hazeldine, R. N. and A. G. Sharpe, Fluorine and Its Compounds, Methuen and Company, London, 1951
69. Hodgman, C. D., Ed. Handbook of Chemistry and Physics, 36th Edition Chemical Rubber Publishing Company, Cleveland, 1955
70. Holloway, F. L. and H. R. Neumark, "Fluorine....Tamed for Rockets," Missiles and Rockets, September 1957
71. Hu, J., H. L. Johnston, and D. White, "Condensed Gas Calorimetry Vs. Heat Capacities, Latent Heats and Entropies of Fluorine from 13 to 85°K; Heats of Transition, Fusion, Vaporization, and Vapor Pressures of the Liquid," J. Am. Chem. Soc., 75, 5642-45, 1953

72. "The Density and Surface Tension of Liquid Fluorine Between 66 and 80°K," J. Am. Chem. Soc., 76, 2584-6, 1954
73. Industrial and Engineering Chemistry, January-June 1947, Vol. 39, Pages 236-434
74. Jarry, R. L. and H. C. Miller, "The Density of Liquid Fluorine 67 and 103°K," J. Am. Chem. Soc., 78, 1552-3, 1956
75. Jones, W. L. and R. J. Lubick, "Performance Characteristics of Hydrogen Fluorine Rocket Engines at Various Chamber Pressures and Nozzle Area Ratios," (paper presented at LPIA JANIS meeting at San Diego, California, November 1960)
76. Kanda, E., "Studies of Fluorine at Low Temperatures, Determination of Dielectric Constants of Condensed Gases," Bull. Chem. Soc. Japan, 12, 477, 1937
77. "Studies of Fluorine at Low Temperatures, Surface Tension of Liquid Fluorine," Bull. Chem. Soc. Japan, 12, 472, 1937
78. "Studies of Fluorine at Low Temperatures, Determination of Molecular Heat, Heat of Fusion of Condensed Fluorine and the Entropy of Fluorine," Bull. Chem. Soc. Japan, 518, 1937.
79. "Studies of Fluorine at Low Temperatures, Viscosity of Fluorine Gas at Low Temperatures," Bull. Chem. Soc. Japan, 12, 463, 1937
80. "Studies of Fluorine at Low Temperatures, Boiling Point of Fluorine," Bull. Chem. Soc. Japan, 12, 463, 1937.
81. Kapustinskii, A. R., "Dissociation Energy of Fluorine Molecules Vs. the Rule of Thermochemical Logarithmicity," Trudy, Moskov, Khim..... ..Tekhnol Inst. im. D. E. Mendelew, 1956, 22, 17-20, as given in Chemical Abstracts, 1957
82. Kimball, G. E. and M. Metlay, "Ionization Processes on Tungsten Filaments, the Absorption of Fluorine on Tungsten," J. Chem. Phys., 16, 779, 1948
83. Landau, R. and R. Rosen, "Industrial Handling of Fluorine," Chapter VII in Preparation, Properties, and Technology of Fluorine and Organic Fluor Compounds by C. Slessor (ed.), McGraw-Hill, New York, 1951, p. 136
84. Leech, H. R., "Some Advances in Fluorine Chemistry," Research, 5, 449-55-1952
85. Liquid Propellant Information Agency, Applied Physics Laboratory, Liquid Propellant Safety Manual, October 1958

86. Arthur D. Little Company, An Investigation and Evaluation of Methods and Equipment to Transport, Transfer, and Store Liquid Fluorine, Report to Army Ballistic Missile Agency, 31 January 1957, C-60516
87. Lubick, R. J. and W. L. Jones, "Performance Characteristics of Hydrogen-Fluorine Rocket Engines at Various Chamber Pressures and Nozzle Area Ratios," Bulletin of 2nd Meeting of Joint Army, Navy, Air Force Liquid Propellant Group, San Diego, California, 1-3 November 1960, LPIA, APL, Johns Hopkins University, Silver Spring, Maryland, p. 437
88. The Martin Company, Baltimore, Liquid Fluorine-Oxidant for Rocket Engines, by James Stebbins and George Morris, RM38, Aug. 1959
89. Murphy, G. M. and J. E. Vana, "Thermodynamic Properties of Hydrogen Fluoride and Fluorine from Spectroscopic Data," J. Chem. Phys., 7, 807, 1939
90. "Standard Entropy of Fluorine Gas," J. Chem. Phys., 18, 1514, 1950
91. Murphy, G. M. and E. Rubin, "The Entropy of Fluorine," J. Chem. Phys., 20, 1179-80, 1952
92. National Advisory Committee for Aeronautics, Lewis Flight Propulsion Laboratory, Cleveland, Ohio, Rocket Laboratory Safety and Design Manual
93. NACA, Theoretical Rocket Performance of JP-4 Fuel with Several Fluorine-Oxygen Mixtures Assuming Equilibrium Composition, NACA RM E57K22, by S. Gordon, 1958
94. NACA, Theoretical Rocket Performance of JP-4 Fuel with Several Fluorine-Oxygen Mixtures Assuming Frozen Composition by S. Gordon and K. S. Drellishak, NACA RM E57G16a, 1957
95. NACA, Theoretical Performance of Liquid NH<sub>2</sub> and Liquid Fluorine as a Rocket Propellant by S. Gordon and V. N. Huff, NACA RM53A26, March 1953
96. NACA, Theoretical Performance of Liquid Hydrazine and Liquid Fluorine as a Rocket Propellant by S. Gordon and V. N. Huff, NACA RM53E12, July 1953
97. NACA, Theoretical Performance of Mixture of Liquid Ammonia and Hydrazine as Fuel with Liquid Fluorine as Oxidant for Rocket Engines by S. Gordon and V. N. Huff, NACA RM53F08, July 1953
98. NACA, Theoretical Performance of JP-4 Fuel with a 70 Percent Fluorine-30 Percent O<sub>2</sub> Mixture as a Rocket Propellant, I-Frozen Composition by S. Gordon and V. N. Huff, NACA RM56A13a, 11 April 1956

99. NACA, Theoretical Performance of JP-4 Fuel with 70-30 Mixture of Fluorine and O<sub>2</sub> as a Rocket Propellant, II-Equilibrium Composition by S. Gordon and V. N. Huff, NACA RM E56F04, 2 October 1956
100. NACA, Theoretical Performance of Lithium and Fluorine as a Rocket Propellant by S. Gordon and V. N. Huff, NACA RM E51C01, May 1957
101. NACA, Theoretical Performance of Liquid Methane with Several Fluorine-Oxygen Mixtures Assuming Frozen Composition by S. Gordon and M. E. Kastner, NACA RM E58B20, 1958
102. NACA, Theoretical Maximum Performance of Liquid F<sub>2</sub> - Liquid O<sub>2</sub> Mixtures with JP-4 Fuel as Rocket Propellants by S. Gordon and R. L. Wilkins, NACA RM E57H09, October 1954
103. NACA, A Study of Injection Processes for 15 Percent Fluorine - 85 Percent O<sub>2</sub> and Heptane in a 200-Pound-Thrust Rocket Engine by M. F. Heidman, NACA RME56J11, 15 January 1957
104. NACA, Theoretical Rocket Performance of JP-4 Fuel with Mixtures of Liquid Ozone and Fluorine by S. Gordon and V. N. Huff, NACA RM E56K14, 28 January 1957
105. NACA, Investigation of Liquid Fluorine and Hydrazine-Ammonia Mixture in 100 Pound-Thrust Rocket Engines by P. M. Ordin, E. A. Rothenberg, and W. H. Rowe, NACA RM E52H22, October 1952
106. NACA, Preliminary Investigation of the Performance and Starting Characteristics of Liquid Oxygen-Liquid Fluorine Mixtures with JP-4 Fuel by P. M. Ordin and E. A. Rothenberg, NACA RM E53J20, January 1954
107. NACA, Experimental Performance of a 500-Pound-Thrust Rocket Chamber Using a 20 Percent Fluorine - 80 Percent Oxygen Mixture with RP-1 by F. J. Kutina, Jr., E. A. Rothenberg, and W. A. Tomanic, NACA RM E57B08, 1957
108. NACA, Compatibility of Metals with Liquid Fluorine at High Pressures and Flow Velocities by H. W. Schmidt, NACA RM E58D11, 1958
109. NACA, Reaction of Fluorine with Carbon as a Means of Fluorine Disposal by H. W. Schmidt, NACA RM E57E02, 1957
110. NACA, Nonmetallic Material Compatibility with Liquid Fluorine by Harold G. Price, Jr., and Howard W. Douglass, NACA RM E57G18, 2 October 1957
111. NACA, Material Compatibility with Gaseous Fluorine by H. W. Douglass and H. G. Price, Jr., NACA RM E56K21, 23 January 1957

112. NACA, Theoretical Performance of Liquid Hydrogen and Liquid Fluorine as a Rocket Propellant for a Chamber Pressure of 600 psia by A. Fortini and V. N. Huff, NACA RM E56L10a, 25 January 1957
113. NACA, Theoretical Performance of Liquid H<sub>2</sub> and Liquid Fluorine as a Rocket Propellant by S. Gordon and V. N. Huff, NACA RM E52L11, February 1953
114. NACA, Investigation of the Liquid Fluorine-Liquid Diborane Propellant Combination in a 100-Pound Thrust Rocket Engine, by H. W. Douglass, P. M. Ordin, and W. H. Roew, NACA RM E51104, November 1951
115. NACA, Investigation of the Liquid Fluorine-Liquid Ammonia Propellant Combination in a 100-Pound Thrust Rocket Engine by H. W. Douglass and E. A. Rothenberg, NACA RM E53E08, July 1953
116. NACA, Experimental Performance of Fluorine-Ammonia in 1000-Pound-Thrust Rocket Engines, by H. W. Douglass, RM E54C17, May 1954
117. NACA, Experimental Performance of Fluorine-Oxygen with JP-4 Fuel in a Rocket Engine, by H. W. Douglass, NACA RM E55D27, July 1955
118. NACA, Experimental Rocket Performance with 15% Fluorine-85% Oxygen and JP-4, by E. A. Rothenberg and W. A. Tomaxic, NACA RM E55D29, 29 August 1955
119. NACA, Investigation of the Corrosion of Metals of Construction by Alternate Exposure to Liquid and Gaseous Fluorine by C. E. Feiler and R. M. Gundzik, NACA TN 333, December 1954
120. NACA, Transportation of Liquid Fluorine by P. M. Ordin, NACA RM E55123, 8 November 1955
121. NACA, Preliminary Evaluation of a Very High Energy Rocket Propellant by Howard W. Douglass, ASTIA No. 152273, for presentation at the Institute of Aeronautical Sciences Annual Flight Propulsion Meeting, Cleveland, 13-14 March 1958
122. NASA, Lewis Research Center, Cleveland, "Hydrogen-Fluorine and Hydrogen-Oxygen Rocket Research" by H. W. Douglass, R. J. Salmo, and W. A. Tomazic for IAS-NASA-Air Force Meeting, 9 March 1961
123. NASA, Investigation of Injectors for a Low-Chamber-Pressure Hydrogen-Fluorine Rocket Engine by R. J. Lubick, H. G. Price, Jr., and A. M. Shinn, Jr., NASA TM X-485, July 1962
124. NASA, Investigation of the Effects of Fluoride on Corrosion at 170°F of 2S-O Aluminum and 347 Stainless Steel in Fuming Nitric Acid by C. E. Feiler and G. M. Morrell, NASA RM E53L17b, February 1954
125. NASA, (Unpublished Data) by Fletcher and Hubbard

126. NASA, Control of Combustion-Chamber Pressure and Oxidant-Fuel Ratio for a Regeneratively Cooled Hydrogen-Fluorine Rocket Engine by R. A. Flage and E. W. Otto, NASA TN D-82, 1959
127. NASA, Rate of Reaction of Gaseous Fluorine with Water by E. A. Fletcher and V. A. Slabery, NASA, Washington, D.C. Report TN 4374, 1958
128. NASA, Ignition of Hydrogen-Oxygen Rocket Engine with Fluorine by E. A. Rothenberg and D. M. Straight, NASA RM X-101, 1959
129. NASA, Analytical Comparison of Hydrazine with Primary Propellants as the Turbine Drive Fluid for Hydrogen-Fluorine and Hydrogen-Oxygen Altitude Stage Rockets by W. T. Wintucky, NASA TN D-78, 1959
130. NASA, Field Experiments on Treatment of Fluorine Spills with Water or Soda Ash by G. R. Kinney, L. C. Leopold, and R. J. Rollbuhler, NASA TN D-63, 1959
131. NASA, Design and Operating Criteria for Fluorine Disposal by Reaction with Charcoal by H. W. Schmidt, NASA Memo 1-27-59E, 1959
132. NASA, Experimental Performance of Liquid Hydrogen and Liquid Fluorine in Regeneratively Cooled Rocket Engines by H. W. Douglass, G. Hennings, and H. G. P-ice, Jr., NASA TM X-87, 1959
133. NASA, Performance of a JP-4 Fuel with Fluorine-Oxygen Mixtures in 1000-Pound-Thrust Rocket Engines, by H. W. Douglass and D. L. Nored, NASA RM E58C18, 1958
134. NASA, Investigation of Small-Scale Hydrazine-Fluorine Injectors by R. J. Rollbuhler and W. A. Tomazic. NASA Memo 1-23-59E. 1959
135. NASA, Analysis of Effects of Rocket-Engine Parameters on Regenerative-Cooling Capabilities of Several Propellants by A. N. Curren, H. W. Douglass, and H. G. Price, Jr., NASA TN D-66. 1959
136. National Bureau of Standards. Circular No. 467
137. National Nuclear Energy Series, Division VI, Vol. I, Pharmacology and Toxicology of Uranium Compounds, Manhattan Project, "Toxicity Following Inhalation of Fluorine and Hydrogen Fluorine" by H. C. Hodge and C. Voegtlin, McGraw-Hill, New York, 1021, 1949
138. Noland, R. L. "Rockets and Missiles," Chem. Eng., 65, 10, 145. 1958
139. North American Aviation, Inc., Fluorine as a Rocket Propellant, by T. F. Dixon, PC-143P, September 1955
140. NAA, A Study of Rocket Engines Using Liquid Fluorine as the Oxidizer by W. R. Edmondson, R-371-4, December 1957 (C)
141. NAA, Development of a Prototype Liquid Fluorine Pump, R-172, March 1956

142. NAA, A survey of Liquid Rocket Propellants by T. F. Dixon, J. W. Parsons, and T. L. Thompson, NAA Report NA-47-95, April 1947 (C)
143. NAA, Rocket Research on Fluorine-Oxygen Mixtures--Final Report by H. Grossaclus, Sl Greenfield, and R. Osborn, PC 21, 1 February 1955 (C)
144. NAA, Evaluation of the Performance of Liquid Fluorine-Ammonia Propellant System, AL-1517-1 through -7 and AL-1800, Contract AF33(616)-62, covering period Sept. 1952 - Oct. 1953
145. NAA, Rocket Research on Fluorine-Oxygen Mixtures, Report PC-74-4, Downey, California, Period Ending Sept. 1955 (C)
146. NAA, Rocketdyne, Component Development and Research for Rocket Engines Using High-Performance Propellants, Report R-371-2, Canoga Park, Calif., Quarterly Progress Report for period ending 31 Dec 1956 (C)
147. NAA, Rocketdyne, Research in Fluorine Chemistry, Summary Report No. R-3505, Canoga Park, Calif., Period 16 March 1961 to 15 March 1962
148. NAA, Rocketdyne, High Energy Upper Stage Propulsion System, Canoga Park, Calif. (C)
149. NAA, Rocketdyne, Nomad Quarterly Technical Program Report, Report No. R-2278-1, Canoga Park, Calif., 30 April 1960 (C)
150. NAA, Rocketdyne, Nomad Monthly Technical Report, Report No. R-1090-8, Canoga Park, Calif., 28 Feb 1959 (C)
151. NAA, Rocketdyne, Rocket Research on Fluorine-Oxygen Mixtures, Final Report No. R-171, 30 March 1956
152. NAA, Rocketdyne, Physical Properties of Fluorine-Oxygen Mixtures, Report No. R-398, 28 Nov 1956
153. NAA, Rocketdyne, Nomad Semiannual Technical Program Report, Contract AF04(647)-171, 31 Dec 1959 (c)
154. NAA, Rocketdyne, Nomad Program Review, Report No. BCI 60-51 7 June 1960 (C)
155. Ohio State Univ., Dept. of Chem., Cryogenic Laboratory, Kinetics, Thermodynamics, Physico-Chemical Properties and Manufacture of Fluorine in Its Volatile Inorganic Compounds, By E. Fultz, H. L. Honston, and D. White, 18 Aug 1952
156. The Ralph M. Parsons Company, Final Report High Energy Test Facility Study, Contract AF04(611)-1047, 30 Nov 1956 (C)

157. Potter, R. L., "Thermodynamic Properties of Oxygen Fluoride and Chlorine Fluoride from Spectroscopic Data," J. Chem. Phys., 17, 957-9, 1949
158. Potter, R. L., "Thermodynamic Properties of Some Simple Fluorine Compounds," J. Chem. Phys., 26, 394-6, 1957
159. Pritchard, H. O., "The Determination of Electron Affinities," Chem. Rev., 52, 529, 1953
160. Pritchard, H. O. and H. A. Skinner, "Extropolation of Electric Affinities," J. Chem. Phys., 22, 1936, 1954
161. Rand Corporation, Propellants for Supersonic Vehicles, Liquid Fluorine, by S. J. Kiehl and J. R. Moore, No. PA-15047, Aug 1947
162. Reaction Motors, Inc., Theoretical, Laboratory and Experimental Investigations of High-Energy Propellants: A Review of the Physical and Chemical Properties of Fluorine and Certain of Its Compounds, by D. Horvitz, Report No. RM1-293-55, Rockaway, New Jersey, Sept 1950 (LP 4755)
163. Republic Aviation Corporation, Cooling Equipment, Design Study Part 8, The Thermodynamics of Oxygen, Hydrazine, and Fluorine by E. F. Fricke, Report No. F-5028-101, Farmingdale, L. I., N.Y.
164. Rogers, M., V. Schomaker, and D. P. Stevenson, "The Internuclear Distance in the Fluorine Molecular," J. Am. Chem. Soc., 63, 2610, 1941
165. Rosen, F. D. "Magnetic Pumps for Corrosive Gases and Liquids," Rev. Sci. Instr., 24, 1061-2, 1953
166. Sanderson, R. T. "The Dissociation Energy of Fluorine," J. Chem. Phys., 22, 345-6, 1954
167. Schmidt, H. W. and E. A. Rothenberg, "Some Problems in Using Fluorine in Rocket Systems," Proceedings of the Propellant Thermodynamics and Handling Conference held at Ohio State University, Columbus, Ohio, Special Report No. 12, June 1960
168. Schram, S. R. and C. Slesser, Preparation, Properties, and Technology of Fluorine and Organic Fluoro Compounds, McGraw-Hill, New York, 1951
169. Sharpe, A. G. "Some General Aspects of the Inorganic Chemistry of Fluorine," Quart. Rev. (London), 49-60, 1957
170. Simons, J. F., Ed. Fluorine Chemistry, Vol. I., Academic Press, Inc., New York, 1950

171. Thompson, G. U. E. "Cost and Availability of High Energy Rocket Propellants," J. Brit. Interplanet. Soc., 11, 333-41, 1952
172. Thompson, F. J., Jr., "Rocket Propellants," Chem. Eng. News, 36, 62-7, 1958
173. Tormey, J. F. "Liquid Rocket Propellants...Is There An Energy Limit?" Ind. Eng. Chem., 49, 1339-43, 1957
174. U. S. Dept. of Commerce, NBS, Selected Values of Chemical Thermodynamic Properties, Circular 500, U. S. Govt. Prtg. Office, Washington, D.C., 1 Feb 1952
175. U. S. Naval Ordnance Test Station, China Lake, Calif. Selection of Oxidizers for Pre-Loaded Liquid Propellant Missiles, by S. Singer, Report No. 2020, Navord Report No. 5881, 5 May 1958
176. Univ. of Rochester, A Study of the Toxicological Effects of the Inhalation of Gaseous Fluorine at a Concentration of Approximately 25 MG/MP; 8 MG/MP; 3 MG/MP (3 reports) by Nils Eriksen, Division of Pharmacology, Reports No. 397, 407 and 427, Manhattan Project, Contract W-7401-eng-49, 1945
177. Univ. of Rochester, A 31-Day Study of the Toxicological Effects of the Inhalation of Gaseous Fluorine at a Concentration of Approximately 0.8 MG/MP, Manhattan Project, Contract W-7401-eng-49, 1945
178. Univ. of Rochester, A Study of the Lethal Effect of the Inhalation of Gaseous Fluorine at Concentrations from 100 ppm to 10,000 ppm, by Nils Eriksen. Manhattan Project, Contract W-7401-eng-49, 1945
179. Wieke, E., "The Dissociation Energy of Fluorine," J. Chem. Phys., 56, 358-60, 1952
180. Wise, H., "Measurement of the Heat of Dissociation of Fluorine by the Effusion Method," J. Phys. Chem., 58, 389-91, 1954, also J. Chem. Phys., 20, 927, 1952
181. Wright-Patterson AFB, Dayton, Ohio, The Thermodynamic Functions of the Halogens and Halogen Halides, by R. Edse, Technical Intelligence Dept. AMC, Technical Report No. F-TR-2250-IA (Preprint), Oct 1948
182. Wright-Patterson AFB, Dayton, Ohio, Simplified Method for Rating Liquid Rocket Propellants, by W. C. Noeggeiath, Technical Report No. F-TR-2191-ND. May 1948
183. Zaehring, A. F., "Propulsion Engineering," Missiles and Rockets, 4, 5, 27, 4 Aug 1958
184. Harold W. Schmidt, Handling and Use of Fluorine and Fluorine-Oxygen Mixtures in Rocket Systems, NASA SP-3037, Lewis Research Center, Cleveland, Ohio.

## II. CLOGGING OF FILTERS AND ORIFICES

Problems identified with flowing  $N_2O_4$  through small clearances were previously investigated by TRW Systems for NASA under Contract NAS 7-107<sup>(1)</sup>. Several instances of valves sticking and jamming, filters clogging and flow stoppage were encountered when flowing  $N_2O_4$ . These problems were attributed to a contaminant residue described as a fine brownish powder. Studies conducted under the NASA program led to postulation that the residue was the result of gel precipitates from  $N_2O_4$ . The gel material, upon drying crystallized to a powdery residue.

Further work was undertaken by TRW Systems for NASA under Contract NAS 7-549<sup>(2)</sup> with the objective of producing the clogging material under laboratory conditions and determining the behavior of the material. The program results showed  $N_2O_4$  formed a gel-like material at the entrance to capillaries and filters causing flow decay to the extent of complete blockage.

Other investigations have also reported flow decay due to the formation of clogging material in  $N_2O_4$ . Rocketdyne under AFRPL sponsorship, Contract AF04(611)11620<sup>(3)</sup>, reported the formation of solid crystalline precipitates from flowing  $N_2O_4$  through a valve orifice. The solid precipitate deposited on a pintle used for throttling the flow. Another case of flow decay was reported to result from the formation of an oily, highly viscous residue found on screens during rocket engine component testing. One other report<sup>(4)</sup> described the formation of gelatinous material in clogging of small orifices during high velocity flow of  $N_2O_4$ . At least two cases of formation of gel-like material have been known to occur in rocket engine components flowing hydrazine fuel.

This section presents a summary of the work performed under the NASA NAS 7-549 contract. [Gel formation was observed to form at the entrance to a 0.005 inch diameter glass capillary during flow with  $N_2O_4$ .] Figure 2-1, taken from Reference 2, is an enlarged photograph at the entrance to the capillary showing the gel formation. The propellant was specification grade MSC-PPD-2A  $N_2O_4$ . Table 2-1 presents a summary of the [test data for several runs made on 0.005 inch and 0.010 inch diameter capillaries.] In several of the test runs the  $N_2O_4$  was temperature conditioned by flowing the propellant through a heat exchanger. [Movies were taken during the flow runs which showed the buildup of blockage material and was described as a slow pulsating, turbulent, twisting of material at the capillary entrance.]

[Gel formation was also observed to form on filters.] Figure 2-3 illustrates the filter condition in the as-received condition. Figure 2-2a is a photograph of the clogged filter and Figure 2-2b is a photograph showing the powdery residue after the gel dried. The filter used was a  $2\mu$  nominal -  $10\mu$  absolute 316 wire mesh cartridge type. A summary of the test run data is presented in Table 2-2 and flow decay curves are presented in Figure 2-4.

[The  $N_2O_4$  used in the filter test runs were MSC-PPD-2A  $N_2O_4$  and MSC-PPD-2A  $N_2O_4$  doped with zinc and iron nitrate. Analyses of the blockage material showed iron was the only metallic constituent detectable in the dried residue from the undoped MSC-PPD-2A  $N_2O_4$  and iron and zinc were the only significant metals found in the residue of the doped  $N_2O_4$ .]

[A gel-like material was found in the line of a rocket engine] at TRW Systems after flowing hydrazine fuel. [The material was deposited on a fitting junction at the entrance of the control valve. [At this time there is no definition as to the mechanism of this formation or to its relationship with the gel formation with  $N_2O_4$ .]

## REFERENCES

1. "Advanced Valve Technology for Spacecraft Engines," Final Report, TRW Report No. 8651-6042-SU-000, Contract No. NAS 7-107, August 1965.
2. "Investigation of the Formation and Behavior of Clogging Material In Earth and Space Storable Propellants," Interim Report No. 08113-6007-R000, Contract No. NAS 7-549.
3. Rocketdyne, "Method for Elimination of Corrosion Products of Nitrogen Tetroxide," Final Report, Contract AF04(611)-11620, July 1967.
4. P. Pomerantz, "Nitrogen Tetroxide for NASA Small-Engine Applications," Special Report (Technical), NASA Western Operations Office, May 17, 1965.

TABLE 2-1. Test Data Summary on Flow Behavior of MSC-PPD-2A N<sub>2</sub>O<sub>4</sub> Using Capillary Test Sections

CAPILLARY I. D. INCHES	ASPECT RATIO (length/dia.)	DIFFERENTIAL PRESSURE ACROSS TEST SECTION, PSI (DOWNSTREAM PRESSURE MAIN- TAINED AT 10 PSIG)	HOLD TANK TEMPERATURE, °C	INLET TEST SECTION TEMP. °C	DIFFERENTIAL TEMPERATURE FROM HOLD TANK TO INLET TEST SECTION, °C	EXIT TEST SECTION TEMP. °C	REMARKS
.005	200	50	22	24	2	24	FLOW BLOCKAGE
.005	200	20	22	22	0	22	FLOW BLOCKAGE
.005	100	54	24	24	0	24	FLOW BLOCKAGE, MOVIES TAKEN
.005	100	62	23	23	0	23	FLOW BLOCKAGE, MOVIES TAKEN
.005	100	91	23	24	1	24	GEL FORMATION, BUT MATERIAL BLOWN THROUGH CAPILLARY, MOVIES TAKEN
.005	100	102	34	22	12	25	GEL FORMED, BUT MATERIAL BLOWN THROUGH
.010	100	10	23	24	1	24	MATERIAL BUILD-UP, BUT BLOWN THROUGH AT HIGHER PRESSURES
.010	100	25	23	23	0	23	MATERIAL BUILD-UP, BUT BLOWN THROUGH AT HIGHER PRESSURES
.010	100	32	23	23	0	23	NO BUILD-UP OR BLOCKAGE
.010	100	52	24	24	0	23	NO BUILD-UP OR BLOCKAGE, MOVIES TAKEN
.010	100	63	59	14	45	18	NO BUILD-UP OR BLOCKAGE
.010	100	60	50	0	50	7	NO BUILD-UP OR BLOCKAGE
.010	100	196	22	22	0	24	NO BUILD-UP OR BLOCKAGE, MOVIES TAKEN


TABLE 2-2. Test Data Summary of Flow Behavior of N<sub>2</sub>O<sub>4</sub> Using 2μ Nominal-10μ Absolute Filters

Run	Hold Tank Temp. °C	Test Section Inlet Temp. °C	Test Section Outlet Temp. °C	Diff. Temp., Hold Tank - Inlet Test Section °C	Test Section Inlet Press., Psia	Test Section Outlet Press., Psia	Diff. Press. Across Test Section, Psia	Original Flow Rate, gal/min	Time For 10% Flow Rate Decay, Sec.*	Time For Complete Blockage (Flow Rate) <0.10 gal/min	Remarks
Neat N <sub>2</sub> O <sub>4</sub>	26	26	26	0	60	50	10	0.40	30+	---	Flow remained constant at 75% of original for rest of run.
Neat N <sub>2</sub> O <sub>4</sub>	26	10	10	16	67	54	10	0.31	30+	240	Cloud formed at 300 seconds; gel clearly seen at 390 seconds.
Doped N <sub>2</sub> O <sub>4</sub>	23	23	23	0	43	27	16	0.77	180	---	Flow had been reduced to 86% of original when N <sub>2</sub> O <sub>4</sub> depleted at 300 seconds.
Doped N <sub>2</sub> O <sub>4</sub>	69	51	51	18	91	62	29	0.76	60+	---	Run terminated at 150 seconds due to cavitation at test section exit.
Doped N <sub>2</sub> O <sub>4</sub>	32	15	13	17	54	18	36	0.30	150	660	No clearly defined cloud observed; gel clearly seen at 600 seconds.


\*Data plotted and smoothed; + indicates flow decayed 10% or more before next data point plotted (normally within 10 seconds).



Figure 2-1. Enlarged View of Gel Formation at Entrance to .005" Diameter Capillary Test Section

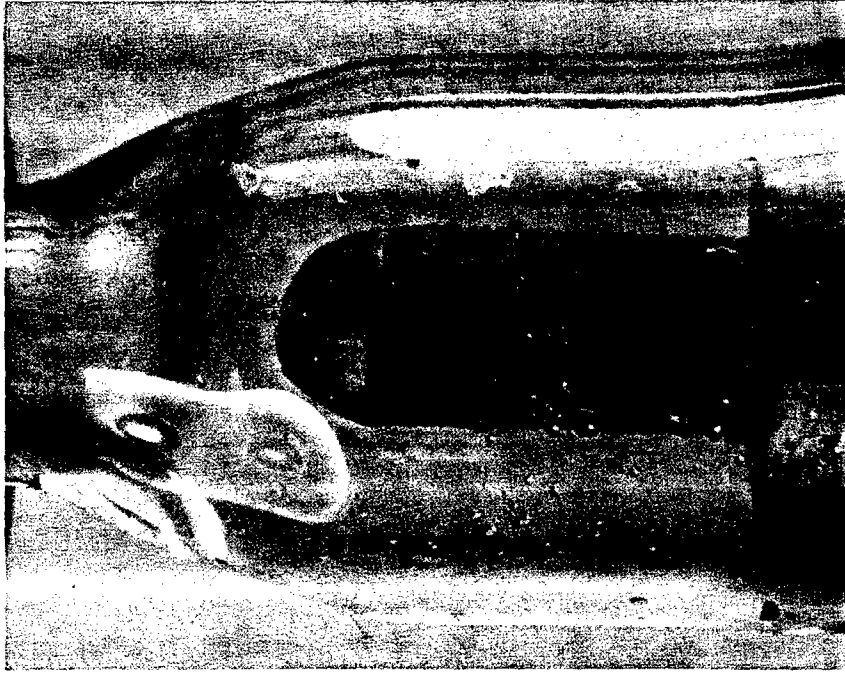

a. Clogged Filter ( $2\mu - 10\mu$ ) Showing Gel Formation During  $N_2O_4$  Flow Runs

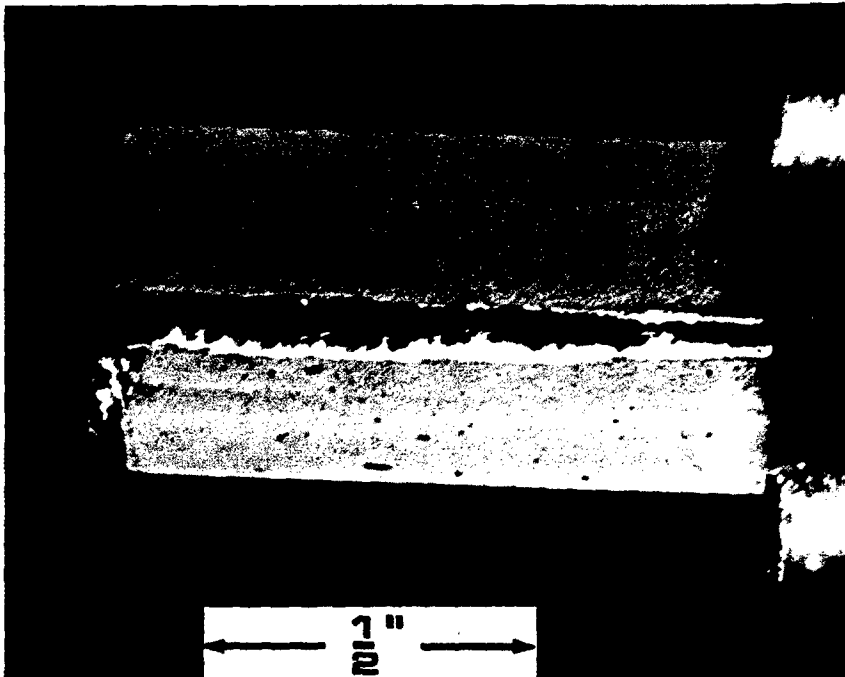

b. Clogged Filter After Drying Showing Powdery Residue

Figure 2-2. Photograph of Clogged Filter Before and After Gel Formation Dri

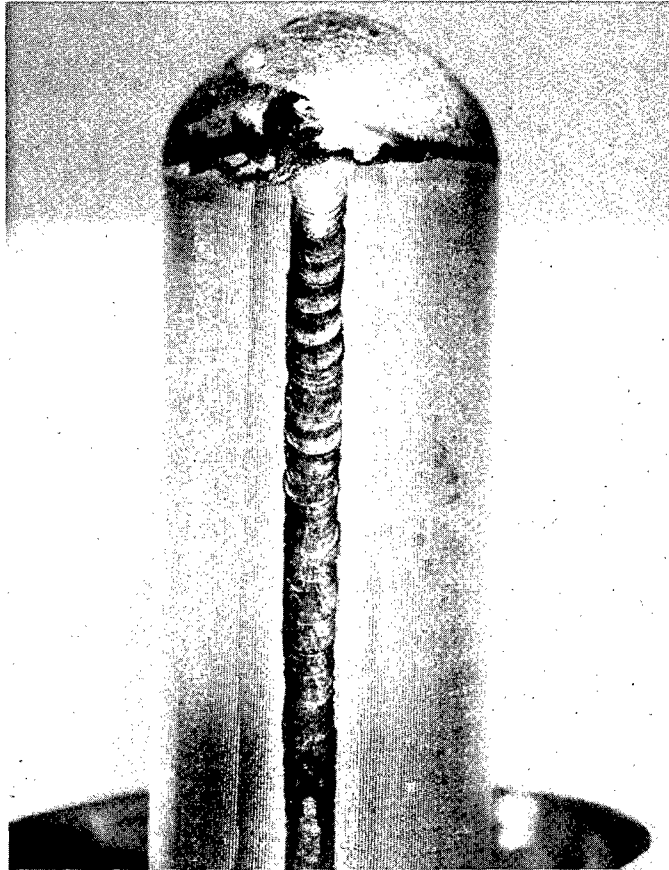


Figure 2-3. Close-up Photograph of Filter

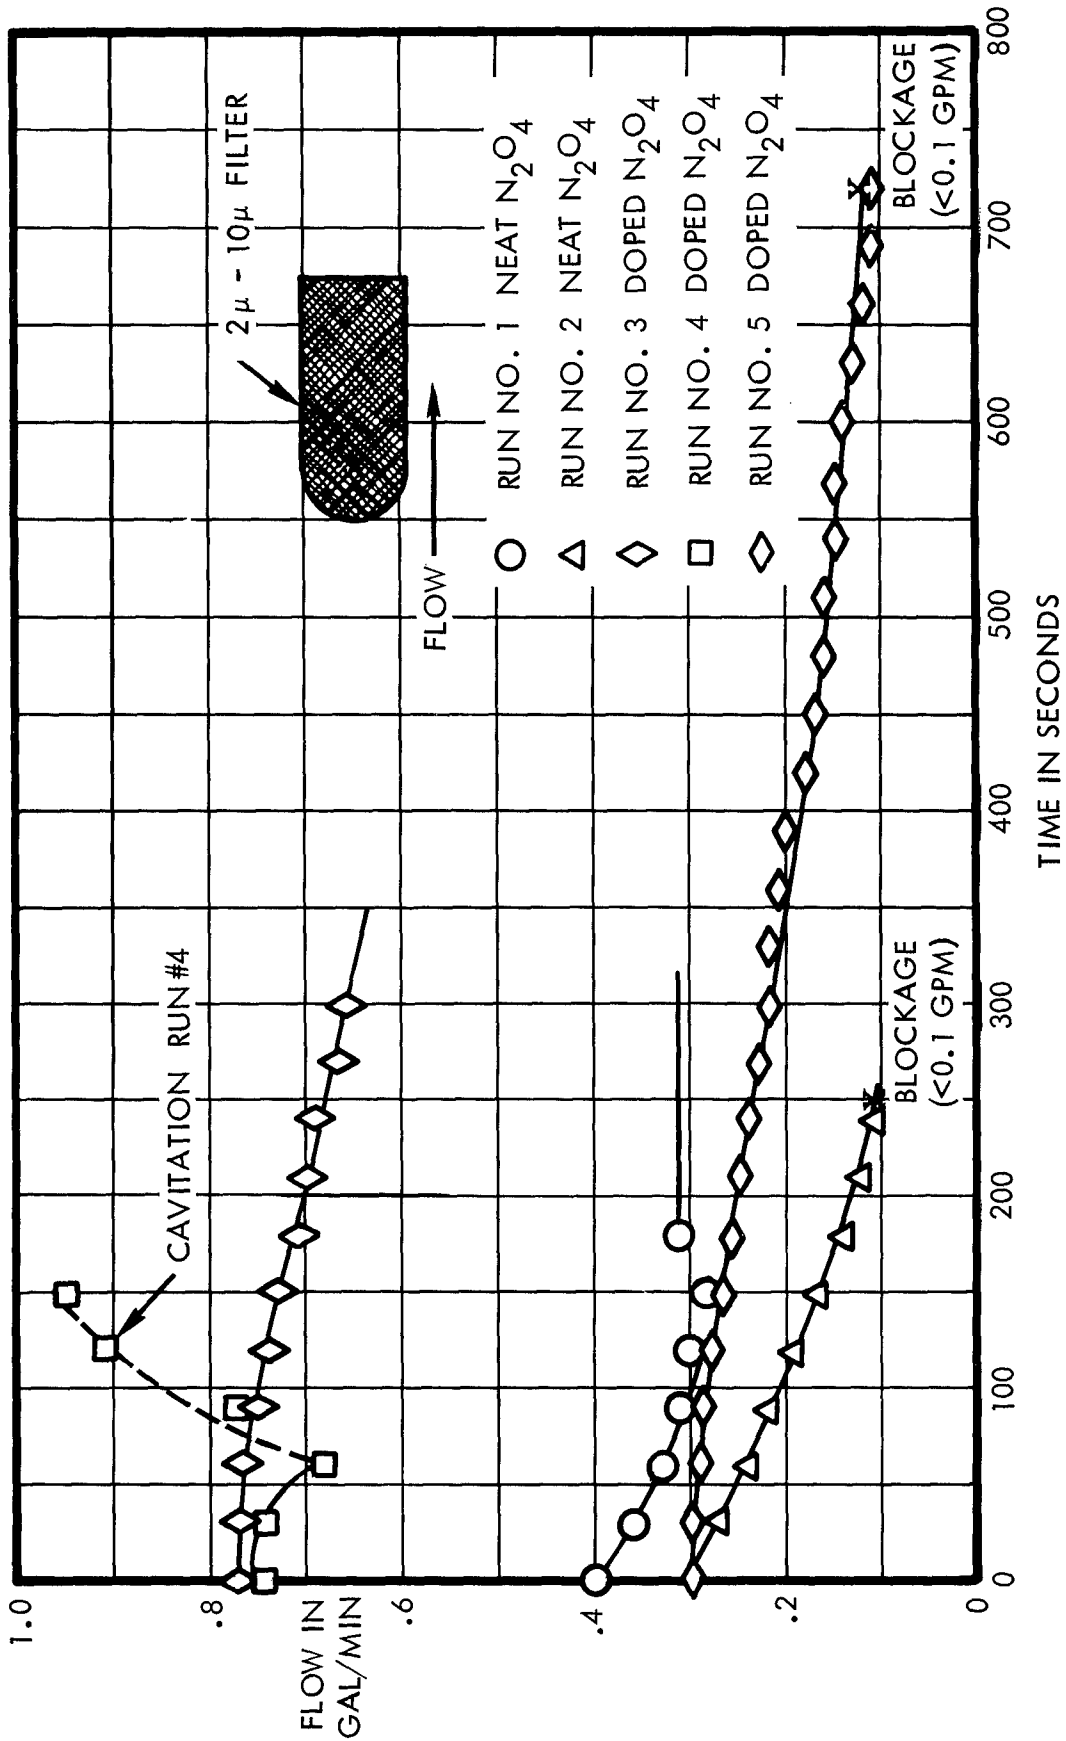


Figure 2-4. Flow Decay Curves for N<sub>2</sub>O<sub>4</sub>

INTERIM REPORT DISTRIBUTION LIST

CONTRACT NAS 7-436

	<u>Copies*</u>
NASA Headquarters Contracting Officer, BCA Patent Office, AGP Washington, D.C. 20546	1
Dr. Robert Levine Chief, Liquid Propulsion Technology NASA Headquarters, Code RPL Washington, D.C. 20546	1
Mr. Frank Compitello Office of Advanced Research and Technology NASA Headquarters Washington, D.C. 20546	1
Mr. Louis Toth Jet Propulsion Laboratory 4800 Oak Grove Drive Pasadena, California 91103	2
NASA Scientific and Technical Information Facility P. O. Box 33 College Park, Maryland 20740	25
Mr. Vincent L. Johnson Director, Launch Vehicles and Propulsion, SV Office of Space Science and Applications NASA Headquarters, Washington, D.C. 20546	1
Mr. Edward Z. Gray Director, Advanced Manned Missions, MT Office of Manned Space Flight NASA Headquarters, Washington, D.C. 20546	1
Mr. Joseph G. Thibodaux, Jr. Code EP, Propulsion and Power Division NASA Manned Spacecraft Center Houston, Texas 77058	1
Mr. Keith D. Chandler, R-P&VE-PA NASA Marshall Space Flight Center Huntsville, Alabama 35812	1

\*(Technical Library unless indicated otherwise)

	<u>Copies*</u>
Mr. Henry Pohl PESD Energy - RCS Branch Chief NASA Manned Spacecraft Center Houston, Texas 77058	1
Mr. Richard Carter Langley Research Center Langley Station Hampton, Virginia 23365	1
Mr. Clarence A. Syvertson Mission Analysis Division NASA Ames Research Center Moffett Field, California 24035	1
 <u>NASA CENTERS</u>	
Ames Research Center Moffett Field, California 94035	1
Goddard Space Flight Center Greenbelt, Maryland 20771	1
Jet Propulsion Laboratory California Institute of Technology 4800 Oak Grove Drive Pasadena, California 91103	1
Langley Research Center Langley Station Hampton, Virginia 23365	1
Lewis Research Center 21000 Brookpark Road Cleveland, Ohio 44135	2
Marshall Space Flight Center Huntsville, Alabama 35812	2
Manned Spacecraft Center Houston, Texas 77058	2
John F. Kennedy Space Center Cocoa Beach, Florida 32931	1

\*(Technical Library unless indicated otherwise)

GOVERNMENT INSTALLATIONS

Copies\*

Aeronautical Systems Division  
Air Force Systems Command  
Wright-Patterson Air Force Base  
Dayton, Ohio 45433

1

Arnold Engineering Development Center  
Arnold Air Force Station  
Tullahoma, Tennessee

1

Space and Missile Systems Organization (SAMSO)  
2400 E. El Segundo  
El Segundo, California 90045

1

Bureau of Naval Weapons  
Department of the Navy  
Washington, D. C.

1

Defense Documentation Center Headquarters  
Cameron Station, Building 5  
Attention: ITSIA  
5010 Duke Street  
Alexandria, Virginia 22314

1

Air Force Rocket Propulsion Laboratory  
Research and Technology Division  
Air Force Systems Command  
Edwards, California 93523

1

U. S. Army Missile Command  
Redstone Arsenal, Alabama 35809

1

U. S. Naval Ordnance Test Station  
China Lake, California 93557

1

CPIA

Chemical Propulsion Information Agency  
Applied Physics Laboratory  
8621 Georgia Avenue  
Silver Springs, Maryland 20910

1

\*(Technical Library unless indicated otherwise)

INDUSTRY CONTRACTORS

Copies\*

Aerojet-General Corporation  
P. O. Box 296  
Azusa, California 91703

1

Aerojet-General Corporation  
P. O. Box 1947  
Technical Library  
Bldg. 2015, Dept. 2410  
Sacramento, California 95809

1

Aeroneutronic - Philco Corporation  
Ford Road  
Newport Beach, California 92663

1

Aerospace Corporation  
2400 East El Segundo Blvd.  
P. O. Box 95085  
Los Angeles, California 90045

1

Arthur D. Little, Inc.  
20 Acorn Park  
Cambridge, Massachusetts 02140

1

Astrosystems International, Inc.  
1275 Bloomfield Avenue  
Fairfield, New Jersey 07007

1

Atlantic Research Corporation  
Edsall Road and Shirley Highway  
Alexandria, Virginia 22314

1

Bell Aerosystems Company  
P. O. Box 1  
Buffalo, New York 14240

1

Bendix Systems Division  
Bendix Corporation  
3300 Plymouth Road  
Ann Arbor, Michigan

1

Boeing Company  
P. O. Box 3707  
Seattle, Washington 98124

1

Boeing Company  
P. O. Box 3707  
Seattle, Washington 98124  
Attn: William W. Kann

1

\*(Technical Library unless indicated otherwise)

	<u>Copies*</u>
Missile and Space Systems Division McDonnell Douglas Corporation 3000 Ocean Park Boulevard Santa Monica, California 90406	1
General Dynamics/Astronautics Library and Information Services (128-00) P. O. Box 1128 San Diego, California 92112	1
Re-Entry Systems Department General Electric Company 3198 Chestnut Street Philadelphia, Pennsylvania 19101	1
Grumman Aircraft Engineering Corporation Bethpage, Long Island, New York	1
Ling-Temco-Vought Corporation Astronautics P. O. Box 5907 Dallas, Texas 75222	1
Lockheed Missiles and Space Company P. O. Box 504 Sunnyvale, California 94088 Attn: Technical Information Center	1
The Marquardt Corporation 16555 Saticoy Street Van Nuys, California 91409	1
Denver Division Martin Marietta Corporation P. O. Box 179 Denver, Colorado 80201	1
McDonnell Douglas Corporation P. O. Box 516 Municipal Airport St. Louis, Missouri 63166	1
Space and Information Systems Division North American Aviation, Inc. 12214 Lakewood Boulevard Downey, California 90241	1

\*(Technical Library unless indicated otherwise)

	<u>Copies*</u>
Rocketdyne (Library 586-306) North American Aviation, Inc. 6633 Canoga Avenue Canoga Park, California 91304	1
Space General Corporation 9200 East Flair Avenue El Monte, California 91734	1
Astro-Electronics Division Radio Corporation of America Princeton, New Jersey 08540	1
Reaction Motors Division Thiokol Chemical Corporation Denville, New Jersey 07832	1
Stanford Research Institute 333 Ravenswood Avenue Menlo Park, California 94025	1
TRW INC TRW Systems Group One Space Park Redondo Beach, California 90278	1
Research Laboratories United Aircraft Corporation 400 Main Street East Hartford, Connecticut 06108	1
Aerospace Operations Walter Kidde and Company, Inc. 567 Main Street Belleville, New Jersey 07109	1
Florida Research and Development Pratt and Whitney Aircraft United Aircraft Corporation P. O. Box 2691 West Palm Beach, Florida 33402	1
Rocket Research Corporation 520 South Portland Street Seattle, Washington 98108	1
Solar Division of International Harvester Company 2200 Pacific Highway San Diego, California	1

\*(Technical Library unless indicated otherwise)

	<u>Copies*</u>
Accessory Products Division of Textron, Inc. 12484 E. Whittier Blvd. Whittier, California 90602	1
Calmec Manufacturing Corporation 5825 District Blvd. Los Angeles, California 90022	1
Carleton Controls Corporation East Aurora, New York 14052	1
J. C. Carter Company 671 W. Seventeenth Street Costa Mesa, California 92626	1
Holex Incorporated 2751 San Juan Road Hollister, California 95023	1
M. C. Manufacturing Company P. O. Box 126 Lake Orion, Michigan 90501	1
Moog Servocontrols, Inc. Proner Airport East Aurora, New York 14052	1
National Waterlift Co. 2220 Palmer Avenue Kalamazoo, Michigan 49001	1
Ordnance Engineering Associates, Inc. 1030 East North Avenue Des Plaines, Illinois	1
Parker Aircraft 5827 W. Century Boulevard Los Angeles, California 90009	1
Pelmec Division Quantic Industries, Inc. 1011 Commercial Street San Carlos, California	1
Pyronetics, Inc. 10025 Shoemaker Avenue Santa Fe Springs, California 90670	1

\*(Technical Library unless indicated otherwise)

	<u>Copies*</u>
Stratos Western Division of Fairchild-Hiller Corporation 1800 Rosecrans Boulevard Manhattan Beach, California	1
Vacco Valve Co. 10350 Vacco Street South El Monte, California	1
Valcor Engineering Corp. 365 Carnegie Avenue Kenilworth, New Jersey 07033	1
Whittaker Corporation 9601 Canoga Avenue Chatsworth, California 91311	1
Wintec Corp. 343 Glasgow Inglewood, California	1

\*(Technical Library unless indicated otherwise)